# SCIENTIFIC REPORTS

# OPEN

SUBJECT AREAS: STEREOCHEMISTRY METHODOLOGY REACTION MECHANISMS COORDINATION CHEMISTRY

> Received 29 April 2013

Accepted 21 August 2013 Published 2 October 2013

Correspondence and requests for materials should be addressed to S.B. (braese@kit.edu) or T.M. (thierry. muller@kit.edu)

# Soccer goes BOXing: Synthetic access to novel [6:0] hexakis[(bisoxazolinyl) methano]fullerenes

Stefan M. Seifermann<sup>1</sup>, Céline Réthoré<sup>1</sup>, Thierry Muller<sup>1</sup> & Stefan Bräse<sup>1,2</sup>

<sup>1</sup>Institute of Organic Chemistry and DFG Center for Functional Nanostructures (CFN), Karlsruhe Institute of Technology (KIT), Campus South, Fritz-Haber-Weg 6, 76131 Karlsruhe, Germany, <sup>2</sup>Institute of Toxicology and Genetics, KIT, Campus North, Hermann-von-Helmholtz-Platz 1, 76344 Eggenstein-Leopoldshafen, Germany.

The syntheses of [6:0] hexakis[(bisoxazolinyl)methano]fullerenes are presented. Two derivatives could be directly obtained using conditions developed by the Sun group. For the remaining products, a two stage protocol had to be developed. All compounds we obtained in synthetically useful scales and were purified via column chromatography with standard achiral phase. These new fullerene adducts bear six metal-chelation sites which are aligned in the three orthogonal space directions and are disposed on a completely rigid scaffold. First experiments indicate that the generation of six-fold metal-complexes is possible with these structures. This makes them very appealing as ligands in asymmetric catalysis and as building blocks in higher supra-molecular assemblies.

Ust about two decades after the discovery of  $C_{60}$  Buckminster fullerene, carbon allotropes – fullerenes, nanotubes and graphene – have become increasingly important in material sciences<sup>1-9</sup>. Fullerenes are widely known and used as electron acceptors. Beside their electro-chemical properties, several fullerene adducts also possess optical activity, which is often beneficial and sometimes essential for applications in asymmetric synthesis or racemic resolution<sup>10-14</sup>.

Over the years, different methods for the functionalization of the fullerene core have appeared<sup>15–22</sup>. Chiral fullerene adducts are either generated through an inherent chiral addition pattern, through chiral addends or a combination of both<sup>10c</sup>. Hirsch was the first to prepare enantiomerically pure bis- and tris[bis(4-phenyl-2-oxazoline)methano]fullerenes with inherent chiral addition arrangements<sup>23,24</sup>. Later, his group extended this strategy to bis(4-phenyl-2-oxazoline) derivatives bearing an inherently chiral [3:3] hexaaddition pattern and used these structures as auxiliaries in stereoselective cyclopropanation reactions<sup>25</sup>. Related systems have also been published by Echegoyen<sup>26</sup> and Rubin<sup>27</sup>.

# Results

Herein, we report the syntheses of the first enantiomerically pure [6:0]hexakis[(bisoxazolinyl)methano]fullerenes 2 and the generation of several six-fold metal-complexes based on these compounds. These fullerene structures are not only aesthetically appealing, but also the first purely organic structures offering six metalchelating sites disposed on a completely rigid scaffold and aligned according to the three orthogonal space directions there are some other completely rigid organic compounds bearing six metal-chelation sites. These do however possess a lower symmetry than the described fullerene adducts<sup>28</sup>. Potential applications should be found in asymmetric catalysis and as tectons in enantiomerically pure self-assembled supra-molecular structures.

#### Discussion

Derivatives **2a**–c were obtained via cyclopropanation of  $C_{60}$  with the corresponding  $C_2$ -symmetrical enantiomerically pure bis(oxazolines) **1a**–c<sup>29</sup> followed by simple silica column chromatography. The reaction conditions initially used by Hirsch to prepare bis- and tris[bis(oxazolinyl)methano]fullerene derivatives were not suitable for six-fold addition<sup>23,25</sup>, as they only yielded mixtures of lower oligo adducts. The latter could not be separated on achiral stationary phases. However, using the conditions reported by Sun with a 100-fold excess of CBr<sub>4</sub> (Conditions A)<sup>30</sup>, both enantiomers of the phenyl derivatives *all-S*-**2a** and *all-R*-**2a** were obtained in 32% and 31% yield respectively (Fig. 3 and Table 1, Entries 1,2).



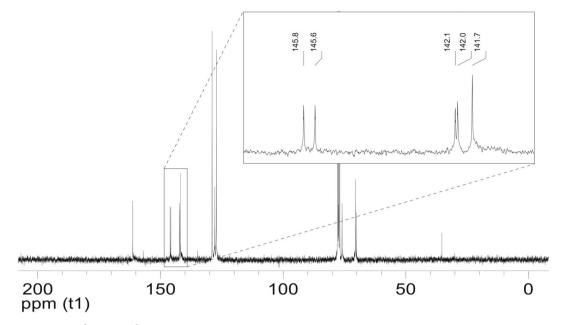



Figure 1 | 13C NMR spectra of compound 2a.

Conditions A proved however to be inadequate for the preparation of compounds **2b–c**. In all cases, no hexakis derivatives bearing the desired geometry could be found. One of the major products was a pentakis adduct with an addition pattern not leading to the desired octahedral hexakis adducts (results not shown)<sup>31</sup>. In order to circumvent this problem, we turned to the 9,10-dimethylanthracene (DMA) template-directed activation developed by Hirsch, which is known to generate exclusively the desired penta- and consequently hexakisregioisomers with an octahedral addition pattern<sup>31</sup>.

With this method hexakis adducts  $2\mathbf{b}-\mathbf{c}$  could be obtained. However, the [5:1] hexakis bis(oxazoline)/DMA adduct was in all cases a major side product in these reactions and could not be completely separated from the [6:0] compound. These [5:1] adducts did not further react under the Hirsch conditions, but yielded the corresponding [6:0] hexakis[bis(oxazolinyl)methano]fullerenes  $2\mathbf{b}-\mathbf{c}$ when first heated to  $60^{\circ}$ C for 30 min and then reacted with CBr<sub>4</sub> (3 eq.), BOX (3 eq.) and DBU (6 eq.) in *o*-DCB (Conditions **B**)  $(Table 1, Entries 3-5)^{30}$ . Hence, applying either protocols A or B gave access to a whole series of hexakis[bis(oxazoline)] adducts in good to excellent overall yields.

<sup>1</sup>H and <sup>13</sup>C NMR analyses confirm the octahedral addition pattern of compounds **2**. The four observed <sup>13</sup>C signals at 142.0, 142.1, 145.5, and 145.9 ppm are in agreement with the chiral tetrahedral (*T*) point group symmetry (Figure 1). These BOX-fullerene adducts are actually less symmetric than most [6:0] hexakis adducts bearing pyritohedral symmetry ( $T_h$ )<sup>32</sup>.

Hirsch proved that a fullerene multi-adduct is obtained as diastereomers if  $C_{60}$  is reacted with enantiomerically pure addends, which arrange in an inherently chiral addition pattern<sup>23b</sup>. Hexakis adducts with an octahedral [6:0] addition pattern have achiral tetrahedral symmetry. Such adducts can consequently only exhibit axial chirality generated through their chiral addends. Thus, all [6:0] hexakis[(bisoxazolinyl)methano]fullerenes generated from enantiomerically pure BOX 1 were obtained as single enantiomer. Optical rotation

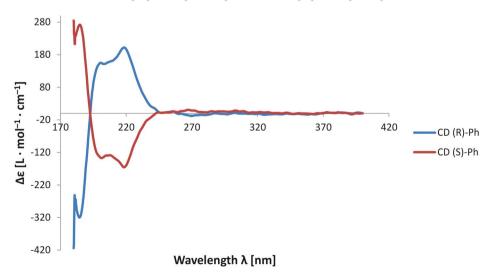

# all-(R)-2a (blue) and all-(S)-2a (red)

Figure 2 | CD spectra of all-S-2a (red) and all-R-2a (blue). Concentrations in trifluoroethanol (TFE): all-R-2a: 0.058 mg/mL, all-S-2a: 0.060 mg/mL.



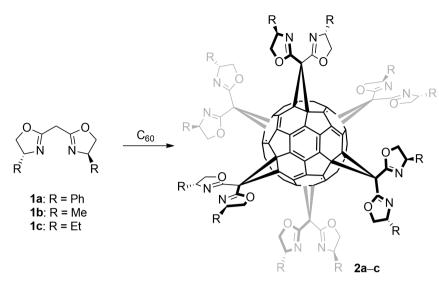


Figure 3 | (Relating to Table 1) Reagents for the six-fold cyclopropanation reaction.

and CD spectra show the enantiomeric relationship of (*all-S-2a/all-R-2a*) and (*all-S-2b/all-R-2b*) (see Figure 2 and SI).

With compounds 2 in hand, we investigated their capacity to build six-fold metal-complexes. Compounds *all-S*-2a and *all-S*-2b were treated with  $[(PhCN)_2PdCl_2]$  (10 eq.) and in a third test *all-S*-2a was reacted with [CuI] (10 eq.). In all three cases, the recovered precipitate proved to be insoluble in conventional solvents. The six-fold complexes could however be detected by mass spectrometry (see SI). In each case, several fragments containing six metal-ions and (6–n) chloride ions were detected (n = 1 to 6). This strongly indicates the formation of six-fold metal-complexes. Due to the weakly bound chloride ions it was not possible to detect the  $[2Pd_6Cl_{12}]$  species.

We have presented the first synthetic access to [6:0] hexakis[(bisoxazolinyl)methano]fullerenes. These compounds provide an all organic rigid scaffold bearing six metal-chelation sites, which are orthogonally directed. Preliminary experiments indicate that the generation of six-fold metal-complexes is possible. We are currently working to improve the solubility of such metal-complexes in order to purify and completely characterize them.

#### Methods

**Synthesis of all-(R)-2a.** BOX derivative (*R*,*R*)-1a (1.28 g, 4.16 mmol, 10.0 eq.), CBr<sub>4</sub> (13.8 g, 41.6 mmol, 100 eq.), C<sub>60</sub> (300 mg, 416 µmol, 1.00 eq.) and DBU (1.25 g, 8.32 mmol, 20.0 eq.) were reacted in dry *o*-DCB (90.0 mL) as described above. After 72 h of stirring at ambient temperature, the reaction mixture was poured into 300 mL of cyclohexane to remove the o-DCB. The precipitate was filtered off and abundantly washed with cyclohexane. After column chromatography (toluene/ethyl acetate (9 : 1) + 5% EtOH + 0.2% NEt<sub>3</sub>) the hexakis fullerene adduct *all-(R)-2a* was obtained as a brown solid in 31% yield. – Mp: decomposition at T > 286°C. – IR (KBr):  $\bar{v} = 2896$  (vw), 2161 (vw), 2043 (vw), 1657 (vw), 1493 (vw), 1452 (vw), 526 (vw), 420 (vw)

Table 1   Reagents a	nd yields	for the	six-fold	cyclopropanation
reaction				

Entry	R	Conditions	Product	Yield (%)
1	Ph	Α	all-S-2a	32
2	Ph	Α	all-R-2a	31
3	Me	В	all-S-2b	19
4	Me	В	all-R-2b	19
5	Et	В	all-S-2c	13

A: C<sub>60</sub> (1 eq.), CBr<sub>4</sub> (100 eq.), BOX-2 (10 eq), DBU (20 eq.), rt, o-DCB.

**B**: C<sub>60</sub> (1 eq.), DMA (10 eq.), oDCB, 1 h, r.t., BOX-**2** (10 eq.), CBr<sub>4</sub> (10 eq.), DBU (20 eq.), after column chromatogrpahy and heating at 60°C for 30 min. in oDCB, CBr<sub>4</sub> (3 eq.), BOX-**2** (3 eq.), DBU (6 eq.).

 $\begin{array}{l} {\rm cm}^{-1}.-{\rm UV}/{\rm VIS}~({\rm CHCl}_3); \lambda_{max}~(\log\epsilon)=181~(7.7), 186~(7.7), 211~(7.4), 272~(6.9)~{\rm nm}.\\ {\rm -}~[z]_{D}^{20}~(c=0.038,{\rm THF}):-101^{\circ}\cdot{\rm mL}\cdot{\rm dm}^{-1}\cdot{\rm g}^{-1}, {\rm -}^{1}{\rm H}\text{-NMR}~(500~{\rm MHz},{\rm CDCl}_3); \delta=4.29~(dd,{}^{3}J=8.3~{\rm Hz}, 12~{\rm H}, 5-{\rm H}), 4.80~(dd,{}^{2}J=10.0~{\rm Hz},{}^{3}J=8.7~{\rm Hz}, 12~{\rm H}, 5-{\rm H}), 5.44~(dd,{}^{2}J=10.0~{\rm Hz}, {}^{3}J=8.7~{\rm Hz}, 12~{\rm H}, 5-{\rm H}), 5.44~(dd,{}^{2}J=10.0~{\rm Hz}, {}^{2}J=8.7~{\rm Hz}, 12~{\rm H$ 

Synthesis of all-R-2b. C<sub>60</sub> (360 mg, 500 µmol, 1.00 eq.) and DMA (1.03 g, 5.00 mmol, 10.0 eq.) were stirred for 1 h in dry toluene (210 mL). Then bisoxazoline (R,R)-1b (911 mg, 5.00 mmol, 10.0 eq.) and CBr<sub>4</sub> (1.66 g, 5.00 mmol, 10.0 eq.) were added and during 20 min DBU (1.52 g, 10.0 mmol, 20.0 eq.) was dropped into the solution. After 72 h of stirring under argon, the solvent was evaporated and the crude product was subjected to column chromatography (toluene/ethyl acetate (9:1) + 20% EtOH + 0.2% NEt<sub>3</sub>). The product obtained that way was dissolved in dichloromethane (3 mL) and precipitated by dropping the solution into diethyl ether (100 mL) to remove the silica that was dissolved by the EtOH. That way, besides the pure product, a mixture consisting of the hexakis derivative and some lower adducts was isolated. In a further reaction under conditions c), the latter was converted into the hexakis adduct vide supra. The purification of the crude product was carried out as for the first product batch by chromatography and precipitation. Finally the hexakis BOX methanofullerene all-(R)-2b was isolated in 19% (168 mg, 90.0 µmol) overall yield. – Mp: decomposition at T  $> 235^{\circ}$ C. – IR (KBr):  $\tilde{v} = 3272$  (br, vw), 2965 (w), 2895 (vw), 1657 (w), 1447 (vw), 1354 (w), 1288 (w), 1195 (w), 1103 (w), 1064 (w), 1022 (w), 976 (w), 942 (w), 844 (vw), 709 (w), 665 (vw), 539 (w), 523 (w) cm<sup>-1</sup>. - UV/ VIS (CHCl<sub>3</sub>):  $\lambda_{max}$  (log  $\epsilon$ ) = 213 (7.0) nm. –<sup>1</sup>H-NMR (400 MHz, CDCl<sub>3</sub>):  $\delta$  = 1.29 (d,  ${}^{3}J = 6.5 \text{ Hz}, 36 \text{ H}, \text{CH}_{3}), 3.94 \text{ (dd, }{}^{3}J = 7.4 \text{ Hz}, 12 \text{ H}, 5-\text{H}), 4.32-4.37 \text{ (m, 12 H, 4-H)},$ 4.43 (dd,  ${}^{2}J$  = 9.2 Hz,  ${}^{3}J$  = 8.0 Hz, 12 H, 5-H) ppm. –  ${}^{13}$ C-NMR (100 MHz, CDCl<sub>3</sub>): δ = 21.3 (CH<sub>3</sub>), 34.4 (Cp- $C_{ap}$ ), 62.0 (C-5), 69.7 ( $\hat{C}_{60}$ - $C_{sp3}$ ), 74.7 (C-4), 141.9 ( $C_{60}$ - $C_{sp2}$ ), 142.1 (C<sub>60</sub>-C<sub>sp2</sub>), 145.1 (C<sub>60</sub>-C<sub>sp2</sub>), 145.3 (C<sub>60</sub>-C<sub>sp2</sub>), 160.0 (C<sub>60</sub>-C<sub>sp2</sub>) ppm. - MS (FAB, 3-NBA) m/z (%): 1801 (13) [M]<sup>+</sup>, 1621 (8) [M-C<sub>9</sub>H<sub>12</sub>N<sub>2</sub>O<sub>2</sub>]<sup>+</sup>, 745 (13), 720 (29), 154 (100) [3-NBA].

- 1. Hirsch, A. The era of carbon allotropes. Nat. Mater. 9, 868-871 (2010).
- 2. Fullerenes Principles and Applications (Eds. : Langa, F., Nierengarten, J.-F.), RCS, Cambridge, 2007.
- Deschenaux, R., Donnio, B. & Guillon, D. Liquid-crystalline fullerodendrimers. New. J. Chem. 31, 1064–1073 (2007).
- Mateo-Alonso, A., Guldi, D. M., Paolucci, F. & Prato, M. Fullerenes: Multitask components in molecular machinery. *Angew. Chem. Int. Ed.* 46, 8120–8126 (2007).
- Bonifazi, D., Enger, O. & Diederich, F. Supramolecular [60] fullerene chemistry on surfaces. *Chem. Soc. Rev.* 36, 390–414 (2007).
- Chaur, M. N., Melin, F., Ortiz, A. L. & Eschegoyen, L. Chemical, Electrochemical, and Structural Properties of Endohedral Metallofullerenes. *Angew. Chem. Int. Ed.* 48, 7514–7538 (2009).
- Holler, M. & Nierengarten, J.-F. Synthesis and Properties of Fullerene-Rich Dendrimers. Aust. J. Chem. 62, 605–623 (2009).
- Giacalone, F. & Martín, N. New Concepts and Applications in the Macromolecular Chemistry of Fullerenes. *Adv. Mater.* 22, 4220–4248 (2010).
- Delgado, J. L., Bouit, P.-A., Filippone, S., Herranz, M<sup>a</sup> Á. & Martín, N. Organic photovoltaics: a chemical approach. *Chem. Commun.* 46, 4853–4865 (2010).

- 10. Wilson, S. R. et al. Chiral non-racemic C60 derivatives: a proposed sector rule for fullerene absolute configuration. Tetrahedron 52, 5131-5142 (1996).
- 11. Kuwahara, S. et al. Conclusive Determination of the Absolute Configuration of Chiral C60-Fullerene cis-3 Bisadducts by X-ray Crystallography and Circular Dichroism. Angew. Chem. Int. Ed. 44, 2262-2265 (2005).
- 12. Thilgen, C. & Diederich, F. Structural Aspects of Fullerene Chemistry. A Journey through Fullerene Chirality. Chem. Rev. 106, 5049-5135 (2006).
- 13. Filippone, S., Maroto, E. E., Martín-Domenech, Á., Suarez, M. & Martín, N. An efficient approach to chiral fullerene derivatives by catalytic enantioselective 1,3dipolar cycloadditions. Nat. Chem. 1, 578-582 (2009).
- 14. Yamada, M., Rivera-Fuentes, P., Schweizer, W. B. & Diederich, F. Optical stability of Axially Chiral Push-Pull Substituted Buta-1,3-dienes: Effect of a Single Methyl Group on the C<sub>60</sub> Surface. Angew. Chem. Int. Ed. 49, 3532-3535 (2010).
- 15. Hirsch, A. & Brettrich, M. Fullerenes: Chemistry and Reaction, Wiley-VCH, Weinheim (2005).
- 16. Diederich, F. & Thilgen, C. Covalent Fullerene Chemistry. Science 271, 317-324 (1996)
- 17. Diederich, F. Covalent Fullerene Chemistry. Pure Appl. Chem. 69, 395-400 (1997).
- 18. Iehl, J. & Nierengarten, J.-F. A Click-Click Approach for the Preparation of Functionalized [5:1]-Hexaadducts of C<sub>60</sub>. Chem. Eur. J. 15, 7306-7309 (2009).
- 19. Iehl, J. & Nierengarten, J.-F. Sequential copper alkyne-azide and thiol-ene click reactions fort he multiple functionalization of fullerene hexaadducts. Chem. Commun. 46, 4160-4162 (2010).
- 20. Compain, P. et al. Glycosidase Inhibition with Fullerene Iminosugar Balls: a Dramatic Multivalent Effect. Angew. Chem. Int. Ed. 49, 5753-5756 (2010).
- . Pierrat, P., Vanderheiden, S., Muller, T. & Bräse, S. Functionalization of Hexakis Methanofullerene Malonate Crown-Ethers: Promising Octahedral Building Blocks for Molecular Networks. Chem. Commun. 1748-1750 (2009).
- 22. Pierrat, P., Réthoré, C., Muller, T. & Bräse, S. Di- and Dodeca-Mitsunobu Reactions on C<sub>60</sub> Derivatives: Post-Functionalization of Fullerene Mono- and Hexakis-Adducts. Chem. Eur. J. 15, 11458-11460 (2009).
- 23. Djojo, F. & Hirsch, A. Synthesis and Chiroptical Properties of Enantiomerically Pure Bis- and Trisadducts of C<sub>60</sub> with an Inherent Chiral Addition Pattern. Chem. Eur. J. 4, 344-356 (1998).
- 24. Djojo, F., Hirsch, A. & Grimme, S. Galactosylated 5-Hydroxylysine Mimetic for glycopeptide Synthesis. Eur. J. Org. Chem. 3027-3039 (1999).
- 25. Djojo, F., Ravanelli, E., Vostrowsky, O. & Hirsch, A. Fullerene Dendrimers and Lipofullerenes with an Inherently Chiral Hexaaddition Pattern. Eur. J. Org. Chem. 1051-1059 (2000).
- 26. Zhang, S., Lukoyanova, O. & Echegoyen, L. Synthesis of Fullerene Adducts with Terpyridyl- or Pyridylpyrrolidine Groups in trans-1 position. Che. Eur. J. 12, 2846-2853 (2006).

- 27. Qian, W. & Rubin, Y. A Parallel Library of all Seven  $A_2 + B_2 + C_2 T_h$ Regioisomeric Hexakisadducts of Fullerne C60: Inspiration from Werner's Octahedral Stereoisomerism. Angew. Chem. Int. Ed. 39, 3133-3137 (2000).
- 28. Plietzsch, O. et al. Synthesis and topological determination of novel hexakissubstituted 1,4-bistritylbenzene and nonakis-substituted 1,3,5-tristritylbenzene derivatives: Building blocks for higher supramolecular assemblies. Eur. J. Org. Chem. 283-299 (2012).
- 29. Hall, J., Lehn, J.-M., DeCian, A. & Fischer, J. Synthesis and Structure of the Copper(II) Complex of a Chiral Bis(dihydrooxazole) Ligand. Helv. Chim. Act. 74, 1-6 (1991).
- 30. Li, H., Kitaygorodskiy, A., Carino, R. A. & Sun, Y.-P. Simple Modification in Hexakis-Addition for Efficient Synthesis of C60-Centered Dendritic Molecules Bearing Multiple Aromatic Chromophores. Org. Lett. 7, 859-861 (2005).
- 31. Lamparth, I., Maichle-Mössmer, C. & Hirsch, A. Reversible Templat-Directed Activation of Equatorial Double Bonds of the Fullerene Framework: Regioselective Direct Synthesis, Crystal Structure, and Aromatic Properties of Th-C<sub>66</sub>(COOEt)<sub>12</sub>. Angew. Chem. Int. Ed. Engl. 34, 1607–1609 (1995)
- 32. Hirsch, A. & Vostrowsky, O. C<sub>60</sub> Hexakisadducts with an octahedral addition Pattern - A New Strucutre Motif in Organic Chemistry. Eur. J. Org. Chem. 829-848 (2001).

# Acknowledgements

This work has been supported by the DFG excellence cluster Center for Functional Nanostructures (CFN), project C1.6.

# Author contributions

T.M., C.R. and S.B. wrote the main manuscript text. S.T.S. prepared all the figures and schemes and wrote the supporting information text. All authors reviewed the manuscript.

# Additional information

Supplementary information accompanies this paper at http://www.nature.com/ scientificreports

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Seifermann, S.M., Réthoré, C., Muller, T. & Bräse, S. Soccer goes BOXing: Synthetic access to novel [6:0] hexakis[(bisoxazolinyl)methano]fullerenes. Sci. Rep. 3, 2817; DOI:10.1038/srep02817 (2013).

This work is licensed under a Creative Commons Attribution-NonCommercial-NoDerivs 3.0 Unported license. To view a copy of this license, visit http://creativecommons.org/licenses/by-nc-nd/3.0