

Journal of Materials Chemistry A

Materials for energy and sustainability

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: Q. Fu, J. Wang, A. Sarapulova, L. Zhu, A. Missyul, E. Welter, X. Luo, Z. Ding, M. Knapp, H. Ehrenberg and S. Dsoke, *J. Mater. Chem. A*, 2021, DOI: 10.1039/D1TA03518E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Electrochemical performance and reaction mechanism investigation of V₂O₅ positive electrode material for aqueous rechargeable zinc batteries

Qiang Fu^{a,*}, Jiaqi Wang^a, Angelina Sarapulova^a, Lihua Zhu^a, Alexander Missyul^c, Edmund Welter^d, Xianlin Luo^a, Ziming Ding^{e,f}, Michael Knapp^a, Helmut Ehrenberg^{a,b}, Sonia Dsoke^{a,b}

^aInstitute for Applied Materials (IAM), Karlsruhe Institute of Technology (KIT), Hermann-von-Helmholtz-Platz 1, D-76344 Eggenstein-Leopoldshafen, Germany

^bHelmholtz Institute Ulm for Electrochemical Energy Storage (HIU), Helmholtzstrasse 11, 89081 Ulm, Germany

^cCELLS-ALBA Synchrotron, E-08290 Cerdanyola del Valles, Barcelona, Spain

^dDeutsches Elektronen-Synchrotron DESY, Notkestraße 85, D-22607 Hamburg, Germany

^eInstitute of Nanotechnology (INT), Karlsruhe Institute of Technology (KIT), Hermann-von-Helmholtz-Platz 1, D-76344 Eggenstein-Leopoldshafen, Germany

^fTechnische Universität Darmstadt, 64289 Darmstadt, Germany

*Corresponding author: qiang.fu@kit.edu (Q. Fu)

Tel: 49-721 608-41445, Fax: 49-721 608-28521.



Abstract

The electrochemical performance and reaction mechanism of orthorhombic V_2O_5 in 1 M $ZnSO_4$ aqueous electrolyte are investigated. V_2O_5 nanowires exhibit an initial discharge and charge capacity of 277 and 432 mAh g^{-1} , respectively, at a current density of 50 mA g^{-1} . The material undergoes quick capacity fading during cycling under both low (50 mA g^{-1}) and high (200 mA g^{-1}) currents. V_2O_5 can deliver a higher discharge capacity at 200 mA g^{-1} than that at 50 mA g^{-1} after 10 cycles, which could be attributed to a different type of activation process under both current densities and distinct degrees of side reactions (parasitic reactions). Cyclic voltammetry shows several successive redox peaks during Zn ion insertion and deinsertion. *In operando* synchrotron diffraction reveals that V_2O_5 undergoes a solid solution and two-phase reaction during the 1st cycle, accompanied by the formation/decomposition of byproducts $Zn_3(OH)_2V_2O_7 \cdot 2(H_2O)$ and $ZnSO_4Zn_3(OH)_6 \cdot 5H_2O$. In the 2nd insertion process, V_2O_5 goes through the same two-phase reaction as that in the 1st cycle, with the formation of the byproduct $ZnSO_4Zn_3(OH)_6 \cdot 5H_2O$. The reduction/oxidation of vanadium is confirmed by *in operando* X-ray absorption spectroscopy. Furthermore, Raman, TEM and X-ray photoelectron spectroscopy (XPS) confirm the byproduct formation and the reversible Zn ion insertion/deinsertion in the V_2O_5 .

Keywords: Orthorhombic V_2O_5 ; *In operando* synchrotron diffraction; *In operando* X-ray absorption spectroscopy; Aqueous rechargeable zinc batteries



1. Introduction

Aqueous rechargeable zinc batteries (ARZBs) have received much attention for application in large-scale energy storage because of their advantages, such as high safety, low cost, and sufficient abundance^{1,2}. Aqueous electrolytes have higher ionic conductivity (up to 1 S cm⁻¹) than that of non-aqueous electrolytes (about 10 mS cm⁻¹), resulting in a higher rate capability¹. Meanwhile, the utilization of aqueous electrolytes can lower the activation energy for charge transfer at the electrode/electrolyte interface. The manufacturing costs of ARZBs are expected to be low since water-based electrolytes are non-toxic, inflammable, and strict humidity control is not required during cell assembling^{3,4}. Moreover, metallic Zn has a high specific capacity (820 mAh g⁻¹) and high volumetric capacity (5854 mAh cm⁻³), making it promising as a negative electrode. It also owns sufficiently high overpotentials with respect to the hydrogen evolution, overcompensating the negative value of -0.76 V vs. SHE that makes it usable in water⁵ and, therefore, can be directly used as the negative electrode in aqueous-based electrolytes. However, the lack of high-performance positive electrode materials, the heavy mass, and the large polarization of divalent Zn²⁺ hinder the practical applications of ARZBs.

Many efforts have been made on the exploration of high-performance positive electrode materials for ARZBs, including the polymorphs of manganese oxide (α -, β -, γ -, δ -MnO₂, and spinel-MnO₂)^{4, 6-17}, Prussian blue analogues¹⁸⁻²¹, vanadium-based oxides (Ca_{0.25}V₂O₅·nH₂O, Zn_{0.25}V₂O₅·nH₂O, Na_{0.33}V₂O₅, V₂O₅·nH₂O, LiV₃O₈, and H₂V₃O₈)^{2, 5, 22-38}, organic compounds^{39, 40}, and other compounds such as Na₃V₂(PO₄)₃⁴¹, Na₃V₂(PO₄)₂F₃⁴², VS₂⁴³, and Mo₆S₈⁴⁴. Among them, vanadium-based oxides are very promising due to their open framework and relatively high capacity as well as operation voltage of around 0.6–1.0 V. For example, Kundu *et al.*⁵ reported Zn_{0.25}V₂O₅·nH₂O positive electrode, which delivers a high initial discharge/charge capacity of 282/278 mAh g⁻¹ at C/6 rate, excellent rate capability, and high cycling stability with a capacity retention of 80% after 1000 cycles at 15 C rate. Xia *et al.*²⁹ demonstrated that Na_{0.33}V₂O₅ nanowires have a high capacity of 367.1 mAh g⁻¹ at 100 mA g⁻¹ when used as the positive electrode in ARZBs. This material also exhibits good rate capability and high capacity retention of 93% after 1000 cycles. Pang *et al.*³⁴ investigated H₂V₃O₈/graphene composite, which shows a high capacity of 394 mAh g⁻¹ at C/3, high rate capability, and excellent cycling stability with a capacity retention of 87% after 2000 cycles. Despite this significant progress, it is still urgently required to deeply understand the electrochemical reaction mechanism of positive electrode materials. Because it is



more meaningful to the development of ARZBs by understanding the reaction mechanism behind good electrochemical performance than trying to improve performance empirically.

Because of its typical layered structure and relatively high capacity, V_2O_5 is considered a promising positive electrode for ARZBs⁴⁵⁻⁴⁸. Despite its good electrochemical performance in ARZBs, the structural changes of V_2O_5 during electrochemical processes are still under debate. Three different viewpoints regarding the structural changes of V_2O_5 in ARZBs have been proposed so far:

(i) Zhou *et al.*⁴⁶ compared the performance of V_2O_5 in different electrolytes (i.e. $Zn(NO_3)_2$, $Zn(CH_3COO)_2$, $ZnCl_2$, and $ZnSO_4$ aqueous-based electrolytes) and with different concentrations of $ZnSO_4$ -based electrolytes. In 3 M $ZnSO_4$, V_2O_5 delivers the best performance with a high capacity of 224 mAh g^{-1} at 100 mA g^{-1} and good cycling stability at the high current densities of 1 and 2 A g^{-1} , respectively. *Ex situ* X-ray diffraction (XRD) demonstrated the formation of a new phase of $Zn_xV_2O_5$ upon Zn insertion into V_2O_5 .

(ii) Zhang *et al.*⁴⁵ also reported a V_2O_5 cathode material with a capacity of 470 mAh g^{-1} at 0.2 A g^{-1} and high capacity retention of 91.1% after 4000 cycles at 5 A g^{-1} in 3 M $Zn(CF_3SO_3)_2$ electrolyte. They proved that this material can work in extreme conditions at both high (50 °C) and low (-10 °C) temperatures. The co-insertion of hydrated Zn ions into the V_2O_5 crystal structure was proposed based on *ex situ* XRD, X-ray photoelectron spectroscopy (XPS), and transmission electron microscopy (TEM).

(iii) Chen *et al.*⁴⁷ proposed a phase transition reaction mechanism *via ex situ* XRD, Raman, and XPS. Orthorhombic V_2O_5 underwent a phase transition to zinc pyrovanadate during the first discharge, where the formed zinc pyrovanadate showed reversible Zn^{2+} (de)insertion during subsequent cycles.

However, the electrochemical reaction mechanism of V_2O_5 in the above-reported works was investigated through *ex situ* techniques. The findings are in controversy with each other and a detailed investigation of the structural changes of V_2O_5 upon Zn-ion insertion/deinsertion is still missing. Moreover, non-equilibrium or intermediate species or states cannot be detected using *ex situ* studies, while *in operando* studies can provide a more reliable understanding of the structural evolution of a battery material in “real use”.

In addition, it has been frequently reported that a mass of complex byproducts was produced/decomposed during the discharge/charge cycling of vanadium oxides such as



$\text{NaV}_3\text{O}_8 \cdot 1.5\text{H}_2\text{O}^2$, $\text{VO}_{1.52}(\text{OH})_{0.77}^{24}$, $\text{Zn}_2\text{V}_2\text{O}_7^{35}$, and $\text{NH}_4\text{V}_4\text{O}_{10}^{49}$. Interestingly, byproducts were not observed in the three works related to the study of V_2O_5 reported above. To better understand the electrochemical mechanism of V_2O_5 in ARZBs *in operando* techniques like diffraction using synchrotron radiation are required. Due to their extremely bright, high flux, and tunable also high energy, synchrotron radiation-based characterizations provide deep penetration into the sample, high-quality data, and real-time diffraction. Particularly, *in operando* synchrotron study can effectively avoid the unpredictable contamination and irreversible changes of highly reactive samples during material preparation, handling, and transportation, which can provide more reliable and precise data for analysis. Hence, in this work, orthorhombic V_2O_5 were prepared by a facile hydrothermal method and the detailed structure evolution and reaction mechanism of orthorhombic V_2O_5 in ARZBs are studied *via in operando* synchrotron diffraction and X-ray absorption spectroscopy (XAS) together with *ex situ* Raman and X-ray photoelectron spectroscopy (XPS).

2. Experimental

Synthesis of V_2O_5 nanowires: V_2O_5 nanowires were prepared *via* a modified hydrothermal method followed by heat treatment^{50, 51}. Briefly, 0.18 g of commercial V_2O_5 powder (Alfa Aesar, 99.99%) was added to 30 ml of deionized water under vigorous stirring for a few minutes to form a light orange suspension. Then, 2.5 ml 30 % hydrogen peroxide (H_2O_2) was dropwise added to the above suspension and kept stirring for 30 mins to get a transparent orange solution. The obtained solution was transferred to a 50 ml Teflon-lined stainless-steel autoclave and kept at 190 °C for 4 days. The precipitate was collected and washed with deionized H_2O several times and dried at 80 °C for 12 h. Finally, the product was annealed at 400 °C for 2 h with a heating rate of 5 °C min^{-1} in air atmosphere.

Preparation of the electrolyte: The 1 M ZnSO_4 electrolyte was prepared by dissolving a corresponding amount of $\text{ZnSO}_4 \cdot 7\text{H}_2\text{O}$ powder in distilled H_2O with vigorous stirring at room temperature.

Morphological and Structural Study: The morphology was studied with a Zeiss Supra 55 Scanning Electron Microscope (SEM) with primary energy of 15 keV. The structural characterization was performed using synchrotron radiation ($\lambda = 0.4132 \text{ \AA}$, 30 keV) at the Material Science and Powder Diffraction beamline (MSPD) of ALBA synchrotron (Barcelona, Spain)⁵². The powder was filled in 0.5 mm \varnothing boro-silicate capillary, and the diffraction pattern was collected



in capillary geometry. A LabRam HR Evolution Raman microscope from Horiba Scientific equipped with HeNe laser (633 nm, 17 mW) and a CCD detector (Horiba) was used to collect the Raman scattering of the samples. Meanwhile, a 600 grating was used to split the measurement signal with a $\times 100$ objective (NA 0.95) for all the pristine and cycled samples. The data were collected for 30 seconds with 4.25 mW of the laser and five measurements were added to reduce signal noise. Transmission electron microscopy (TEM) imaging and high angle annular dark field-scanning TEM (HAADF-STEM) electron dispersive X-Ray (EDX) mapping were acquired by Themis 300 under 300 kV with Ceta camera and Super-X EDX detector, respectively. The last measured screen current for high-resolution TEM (HRTEM) imaging was 998 pA and for EDS mapping was 93.4 pA. X-ray photoelectron spectroscopy measurements were performed using a K-Alpha XPS spectrometer (ThermoFisher Scientific, East Grinstead, UK), applying a micro-focused, monochromated Al K_{α} X-ray source with a spot size of 400 μm . To prevent any localized charge buildup, the K-Alpha⁺ charge compensation system was employed during analysis, using electrons of 8 eV energy and low-energy argon ions. The Thermo Advantage software was used for data acquisition and processing⁵³. The spectra were fitted with one or more Voigt profiles (binding energy uncertainty: ± 0.2 eV). All spectra were referenced to the O 1s peak of vanadium oxide at 530.0 eV binding energy. In addition, the discharged and charged V_2O_5 and discharged and charged Zn electrodes were sealed in an *in situ* Raman cell with a quartz window inside a glovebox. Note the “discharged Zn” refers to the counter electrode of V_2O_5 at the discharged state of 0.3 V from the same cell, while “charged Zn” refers to the counter electrode of V_2O_5 at the charged state of 1.6 V from the same cell.

Electrochemical Characterization: The electrode was prepared by mixing active material V_2O_5 nanowires with Super C65 C (Timcal) and polyvinylidene difluoride (PVDF) binder in a weight ratio of 70:20:10 with N-Methyl-2-pyrrolidone solvent. The dried electrode mixture with mass loading of ~ 1.4 mg cm^{-2} was pressed (4 tons) on a stainless steel mesh of 12 mm and dried at 120 $^{\circ}\text{C}$ overnight under vacuum. CR2032-type coin cells for electrochemical measurements were assembled in air at room temperature. The cells were built with V_2O_5 positive electrode, Zn foil as the negative electrode, 1 M ZnSO_4 as the electrolyte, and a piece of glass microfiber (Whatman) as the separator. The galvanostatic cycling with the potential limitation (GCPL) and cyclic voltammetry (CV) measurements were performed between 0.3 and 1.6 V (vs. Zn^{2+}/Zn) with



a VMP3 potentiostat (BioLogic) at 25 °C. GCPL was performed at different current densities ranging from 50 to 1600 mA g⁻¹ to determine the rate capability of the battery.

In operando synchrotron diffraction and in operando X-ray absorption spectroscopy (XAS): *In operando* synchrotron diffraction was performed at the Material Science and Powder Diffraction beamline (MSPD) at the ALBA synchrotron. The electrochemical cell consists of 2025-type coin cell with glass windows of 5 mm diameter for beam entrance. The positive electrode was prepared by pressing the dried electrode mixture (as described above) on a stainless steel mesh within a 5 mm hole in the center, a Zn foil with a 5 mm hole in the center was used as the negative electrode. *In operando* synchrotron diffraction was conducted with radiation $\lambda = 0.4132 \text{ \AA}$ wavelength (30 keV) and the position-sensitive detector MYTHEN. Data in steps of 0.006° over an angular range of 1.8° - 42° in 2theta were gathered with an effective exposure time of 60 s during the 1.5 cycles with a current density of 50 mA g⁻¹. The coin cell was continuously oscillated +/-5° around the incoming beam direction to improve the powder averaging (i.e. increasing the number of crystallites fulfilling Bragg condition and contributing to the observed reflections). Diffraction data were analyzed by the Rietveld method using the Fullprof software package⁵⁴. *In operando* XAS measurements were performed at beamline P65 at the synchrotron source PETRA III (DESY, Hamburg). XAS was carried out during the first charge/discharge process at the current of 50 mA g⁻¹ in the same coin-cell configuration as above but with a Kapton window. X-ray absorption spectra of vanadium were recorded in quick-XAS (6 min/spectrum) mode in fluorescence geometry using a PIPS (passivated implanted planar silicon) diode. The V K-edge for V₂O₅ was investigated, and the energy was calibrated utilizing vanadium foil as commonly applied in XAS experiments. V₂O₃, VO₂, and V₂O₅ were used as standard materials. All data were collected at room temperature with a Si(111) double crystal monochromator, and all spectra were processed using the DEMETER software package⁵⁵.

3. Results and discussion

3.1 Structural and morphological characterization



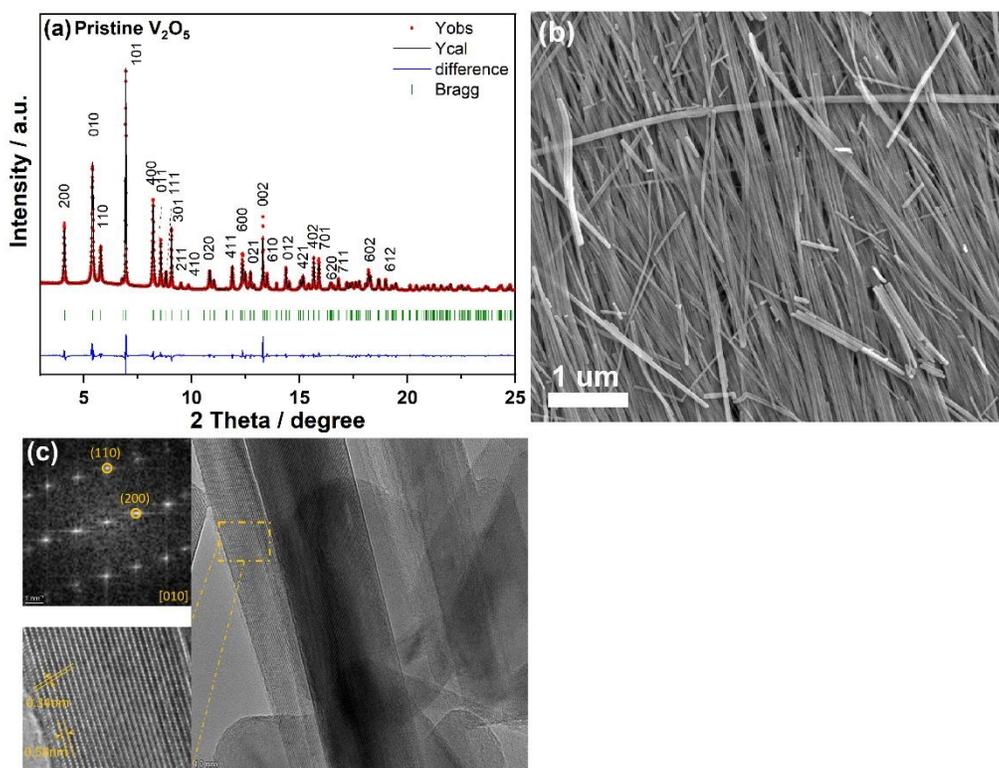


Figure 1 Rietveld refinement based on synchrotron diffraction data (a), SEM (b), and HRTEM image (c) of V_2O_5 nanowires, where fast fourier transform (FFT) was done from the marked orange area

The crystal structure of the prepared V_2O_5 nanowires was investigated by synchrotron diffraction and HRTEM imaging, as displayed in **Figure 1a**. All reflections can be indexed to the orthorhombic V_2O_5 with space group $Pmn2_1$, and the lattice parameters are $a = 11.515(1) \text{ \AA}$, $b = 4.374(1) \text{ \AA}$, $c = 3.566(1) \text{ \AA}$, in good agreement with the previous work⁵⁶. The strong intensities of the reflections confirm the high crystallinity of the obtained V_2O_5 nanowires material. The SEM image (**Figure 1b**) demonstrates that V_2O_5 material is composed of nanowire-like nanostructure with lengths up to several micrometers. TEM imaging further reveals the nanowire-like morphology of V_2O_5 while HRTEM image (**Figure 1c**) displays the highly crystalline sample on the [010] zone axis with lattice fringe of 0.58 nm and 0.34 nm corresponding to the (200) and (110) plane of V_2O_5 , respectively. This fits well with the result obtained from synchrotron diffraction.

3.2 Electrochemical properties



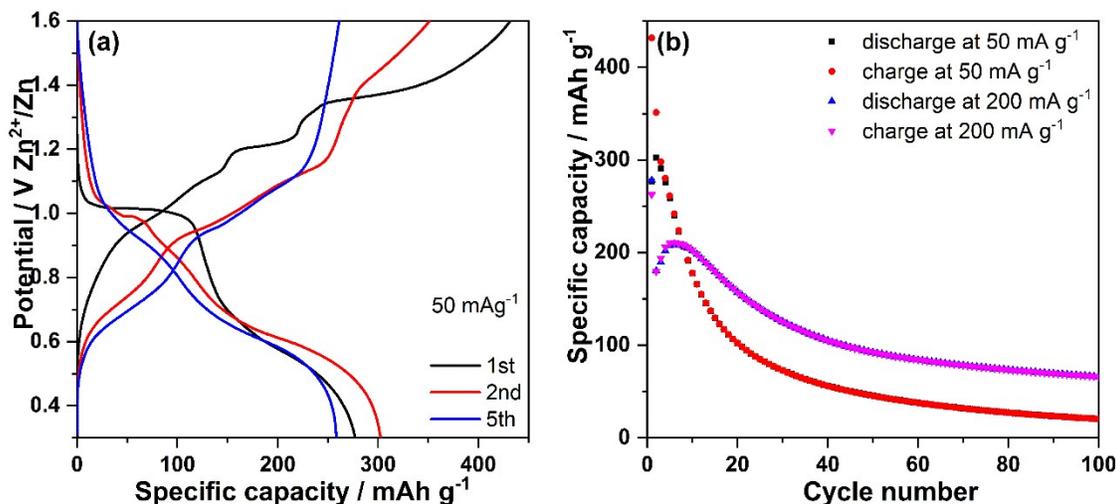


Figure 2 Discharge-charge profiles (a) and cycling performance (b) of V_2O_5 nanowires in 1 M $ZnSO_4$

Figure 2a displays the discharge-charge profiles of V_2O_5 nanowires were at the specific currents of 50 mA g^{-1} in the potential range of 0.30 - 1.60 V vs. Zn^{2+}/Zn . The open-circuit voltage (OCV) of the cell is 1.23 V. During the 1st discharge (Zn ions insertion), V_2O_5 nanowires electrode displays a flat plateau at around 1.00 V, followed by a sloping-like plateau at about 0.50 V. During the 1st charge process (Zn ions de-insertion), a slope and a flat plateau at 1.20 V together with a slope up to 1.6 V can be observed. Compared with the 1st discharge, the 2nd discharge profile shows a shorter plateau at around 1.00 V and similar sloping-like plateau at 0.50 V. In the 2nd charge process, a slope similar to that for the 1st charge is observed, but no clear plateau at 1.20 V can be seen. During cycling, the voltage profiles significantly change: the plateau at 1.20 V completely disappears, and only one slope and a sloping-like plateau at 0.50 V can be observed (see the 5th discharge profile). On the 5th charge profile, two sloping-like plateaus at 0.70 V and 1.0 V are observed. The V_2O_5 nanowires electrode delivers an initial discharge and charge capacity of 277 and 432 mAh g^{-1} , respectively, at a current density of 50 mA g^{-1} . The discharge capacity of 277 mAh/g almost reaches the theoretical one based on the insertion of 1 mol of Zn^{2+} in V_2O_5 (294 mAh g^{-1}). The huge extra charge capacity might be attributed to side reactions such as O_2 evolution from the aqueous-based electrolyte. The electrode delivers a discharge capacity of 302 mAh g^{-1} at the 2nd cycle, a value higher than that for the first cycle, which might be due to an activation of the active material (theoretical capacity of 442 mAh g^{-1} by considering insertion of 1.5 mol of Zn^{2+} into V_2O_5), accompanied by Zn insertion, as also reported by other previous studies^{6, 57}. The V_2O_5



positive electrode exhibits a dramatic decrease of capacity during the following 20 cycles at 50 mA g⁻¹ (94 mAh g⁻¹ at the 22nd cycle) and delivers a discharge capacity of only 21 mAh g⁻¹ after 100 cycles. Moreover, the cycling stability of V₂O₅ positive electrode was studied at a higher specific current of 200 mA g⁻¹, as presented in **Figure 2b**. An initial discharge capacity of 278 mAh g⁻¹ is obtained, followed by a sudden capacity decline down to 180 mAh g⁻¹ at the 2nd cycle. In the following four cycles, the behavior differs from the one of the electrode cycled at 50 mA g⁻¹: it displays a capacity increase, indicating a long activation process of the active material, which is often observed in positive electrode materials for ARZBs^{6, 57}. However, this activation phenomenon takes more cycles under high current density, demonstrating its possible correlation with the involved chemical ion kinetics during cycling²². After 100 cycles, the capacity at 200 mA g⁻¹ is higher (45 mAh g⁻¹) than that delivered at 50 mA g⁻¹. This could be attributed to a different type of activation process under different current densities. The side reactions (parasitic reactions) under low current have more relevance than at high current and, consequently, the degradation is faster. Moreover, a significant difference is observed between the two first charge profiles recorded at both current densities: the charge profile recorded at 200 mA g⁻¹ displays a slope-like plateau (**Figure S1**); a clear flat plateau in the voltage profile is observed at the low current of 50 mA g⁻¹. The difference of voltage profiles suggests a different mechanism reaction and therefore results in a type of activation process under high and low current.

3.3 Electrochemical mechanism



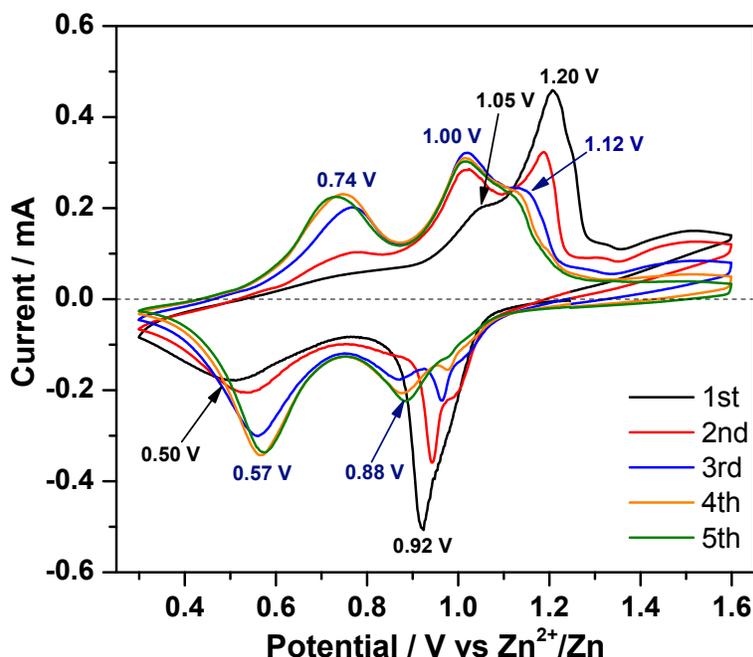


Figure 3 CV curves of V_2O_5 nanowires at a scan rate of 0.1 mV s^{-1} in 1 M ZnSO_4

In order to clarify the Zn-ion storage mechanism in the V_2O_5 material, CV was performed at a scan rate of 0.1 mV s^{-1} in the voltage range of $0.30 - 1.60 \text{ V}$ (vs. Zn^{2+}/Zn). **Figure 3** displays two peaks centered at 0.92 and 0.50 V during the 1st reduction process and a broad peak at 1.20 V with a shoulder at 1.05 V during the 1st oxidation process. In the following scans, three features are observed for both reduction and oxidation processes, respectively. The reduction peak at 0.92 V gradually shifts to higher potential, becomes weaker, and finally disappears. However, a new reduction peak at 0.88 V emerges and grows up and the reduction peak at 0.50 V gradually shifts to 0.57 V , indicating polarization (and resistance) decrease of this process. At the same time, a new oxidation peak appears at 0.74 V . The oxidation peak at 1.05 V shifts to 1.00 V after the first cycle and increases upon cycling. The oxidation peak at 1.20 V shifts to 1.12 V in the 3rd cycle; this shift is accompanied by decreasing in current intensity, indicating the decrease of polarization.

To investigate the structural evolution of V_2O_5 upon Zn-ion insertion/deinsertion, *in operando* synchrotron diffraction was performed during the initial 1.5 cycles. The contour maps of selected diffraction patterns and corresponding voltage-time profiles are provided in **Figure 4**. Note that an electrochemical activation is observed at the high current of 200 mA g^{-1} during the first 5 cycles, with very interesting changes. Here we go deeper on understanding the very initial changes at low



current and in the future, it would be interesting and necessary to study what is happening during the further cycles at higher current density.

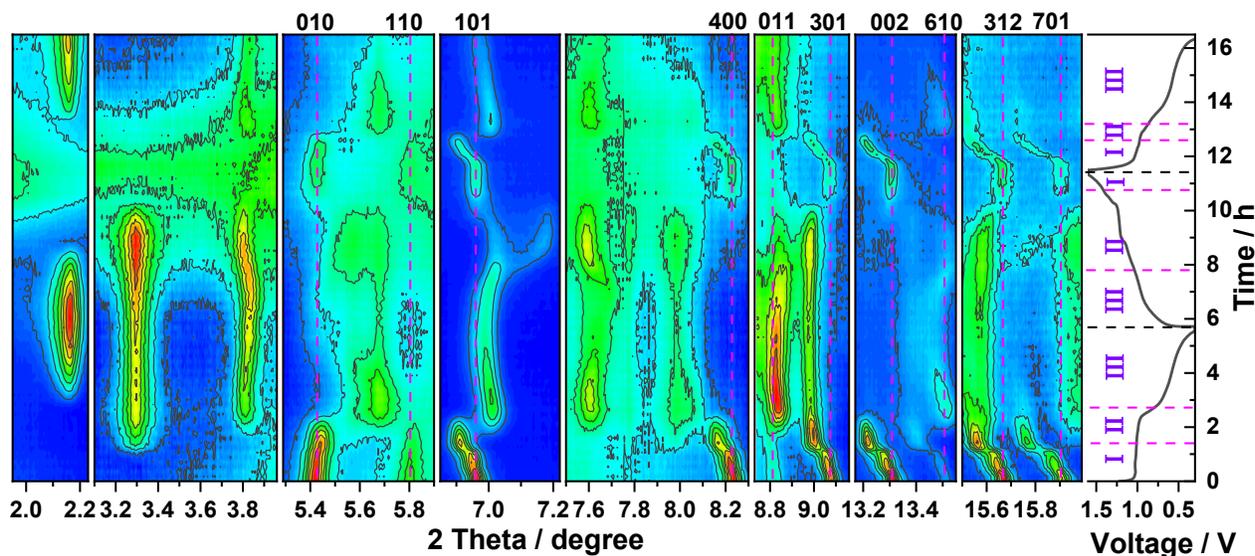


Figure 4 Contour maps of *in operando* synchrotron diffraction of V_2O_5 during the first one and half cycles and the corresponding voltage profile at a current density of 50 mA g^{-1}

Before the discharge (at 1.2 V), all reflections of the parent material can be indexed on the orthorhombic V_2O_5 in the space group $Pmn2_1$ (see **Figure S2a** for the Rietveld refinement of pristine V_2O_5). At the beginning of the 1st discharge (**Region I**), most of the characteristic reflections of V_2O_5 , such as ones at 200 (4.12°), 101 (6.96°), 400 (8.24°), 011 (8.58°), 301 (9.08°), 411 (11.90°), 600 (12.37°), 002 (13.31°), 012 (14.38°), 402 (15.67°), and 701 (15.91°), continuously shift towards lower 2θ , accompanied by a slight reduction of their intensity. Therefore, a solid solution reaction upon Zn ions insertion into the V_2O_5 structure can be proposed up to the stoichiometry $Zn_xV_2O_5$ ($x=0.22$, 65 mAh g^{-1} , black line at the end of **Region I**, **Figure S3**), where lattice parameters a and c increase and b decreases. At the same time, few reflections at 010 (5.42°), 020 (10.85°), and 120 (11.04°) slightly shift to high angles; few other reflections at 110 (5.80°), 320 (12.49°), 021 (12.73°), and 620 (16.46°) keep in the same positions. Upon total discharge capacity of 44 mAh g^{-1} from OCV (1.02 V , $x=0.15$, cyan line in the middle of **Region I**, **Figure S3**), two small reflections at 3.29° and 13.23° emerge, which belong to a new phase of zinc pyrovanadate of 1.2 % (wt/wt), $Zn_{3+\delta}(OH)_2V_2O_7 \cdot 2H_2O$ (see **Figure S2b** for the Rietveld refinement based on the 10th pattern recorded during discharge of V_2O_5). Other reflections related to this phase become visible at 4.49° , 7.78° , 7.99° , 8.46° , 9.57° , 10.20° , 11.16° , 15.97° , and 17.54° along with further Zn ions insertion. At the same time, other reflections at 3.81° , 5.67° , 7.01° ,



7.61°, 11.42°, and 11.66° appear and grow (**Region II**). These reflections are attributed to the formation of the new Zn-rich phase $Zn_xV_2O_5$ ($x=0.44$) through a 2-phase reaction, corresponding to the capacity of 129 mAh g⁻¹. Meanwhile, the reflections of the new Zn-rich phase $Zn_{0.44}V_2O_5$ remain in their positions, together with the decrease of the intensities of the $Zn_{0.22}V_2O_5$ phase. At the end of **Region II** (gray line in **Figure S3**), most of the reflections of $Zn_{0.22}V_2O_5$ phase disappear, and the Zn-rich $Zn_{0.44}V_2O_5$ phase grows up. It implies the 2-phase coexistence transition between $Zn_{0.22}V_2O_5$ and $Zn_{0.44}V_2O_5$ in **Region II** during the Zn ions insertion. The formation of $Zn_{0.44}V_2O_5$ is accompanied by the formation of the byproduct $Zn_3(OH)_2V_2O_7 \cdot 2H_2O$. Note that the x value is determined without the consideration of the consumption of V_2O_5 to form the byproduct $Zn_{3+\delta}(OH)_2V_2O_7 \cdot 2H_2O$ and the possible dissolution of V_2O_5 , where the dissolution and phase transformation mechanisms of V_2O_5 in ARZBs were newly reported⁵⁸. Therefore, the value of $x=0.44$ is an estimate for the lower limit of the inserted Zn content. Upon further Zn ions insertion (**Region III**), some new reflections begin to appear at 2.16°, 4.34°, 9.26°, 9.35°, which are assigned to the byproduct of $ZnSO_4Zn_3(OH)_6 \cdot 5H_2O$ with space group $P-1$. Once the byproduct is formed, all its Bragg reflections remain at the same 2θ -positions throughout the discharge process, but their intensities increase. Meanwhile, most of the reflections maintain their positions along with the increase of their intensities (**Region III**), while only two reflections of $Zn_{0.44}V_2O_5$ at 3.81° and 7.01° shift to high and low angles, respectively. It indicates that a solid solution process happens in **Region III** to form a final phase $Zn_{0.94}V_2O_5$ together with the above-mentioned two byproducts with a total discharge capacity of 277 mAh g⁻¹ (see **Figure S2c** for the Rietveld refinement of 36th pattern at first fully discharged V_2O_5). During the 1st charge, the reflections do not evolve in a symmetric reverse backway, as indicated by the appearance and disappearance of a small reflection at 7.17°, where two 2-phase regions are observed (**Region II**). The reflections return back to their initial 2θ -positions for the pristine V_2O_5 state, but with much lower intensities (see **Figure S2d** for the Rietveld refinement, based on the 69th pattern at fully charged V_2O_5). This is possibly caused by the amorphization of the crystalline active material or by the vanadium dissolution in the electrolyte^{32, 36} (See **Figure S4**). Interestingly, both byproducts disappear again along with the 1st charging process. The evolution of the reflections in the 2nd discharge is analogous to that during the 1st cycle. In **Region I**, the reflections show the same behavior as those for the first discharge process, suggesting a solid solution reaction. In **Region II and III**, the electrode undergoes the same process: a shorter two-phase transition and solid solution than in the first discharge, but



without the appearance of the reflections related to the byproduct $\text{Zn}_{3+\delta}(\text{OH})_2\text{V}_2\text{O}_7 \cdot 2\text{H}_2\text{O}$ (see **Figure S2e** for the Rietveld refinement, based on the 97th pattern at the 2nd fully discharged V_2O_5). The formation of the other byproduct $\text{ZnSO}_4\text{Zn}_3(\text{OH})_6 \cdot 5\text{H}_2\text{O}$ is also detected again during the second discharge process. The $\text{Zn}_{3+\delta}(\text{OH})_2\text{V}_2\text{O}_7 \cdot 2\text{H}_2\text{O}$ has an open layered structure and has been reported by Alshareef *et al.*²⁶ as positive electrode material in ARZBs. The material has a capacity of 213 mAh g⁻¹ at 50 mA g⁻¹ and shows a shift of the reflection 001 during Zn-ions insertion and deinsertion²⁶. This means that the $\text{Zn}_{3+\delta}(\text{OH})_2\text{V}_2\text{O}_7 \cdot 2\text{H}_2\text{O}$ byproduct, generated during cycling, still contributes to the overall capacity of the electrode. Recently, Chen *et al.*⁴⁷ reported that $\text{Zn}_3(\text{OH})_2\text{V}_2\text{O}_7 \cdot 2\text{H}_2\text{O}$ is also formed *via* the 2-phase coexistence transition in an aqueous Zn- V_2O_5 battery, and then it functions as a host structure in the following cycles, where it shows a shift of reflection 001 during Zn ions insertion. However, in our case, the shift of the 001 reflection is not observed, which might suggest that $\text{Zn}_{3+\delta}(\text{OH})_2\text{V}_2\text{O}_7 \cdot 2\text{H}_2\text{O}$ is not active or just the *c*-axis parameter does not change. Furthermore, our results directly show for the first time the formation and decomposition of both byproducts $\text{Zn}_{3+\delta}(\text{OH})_2\text{V}_2\text{O}_7 \cdot 2\text{H}_2\text{O}$ and $\text{ZnSO}_4\text{Zn}_3(\text{OH})_6 \cdot 5\text{H}_2\text{O}$ during cycling.

In order to investigate the variation of the oxidation state and the local electron environment of vanadium during the discharge/charge (i.e. Zn insertion/deinsertion) process, *in operando* XAS was performed on the V_2O_5 nanowires as positive electrode within an *in operando* coin cell. **Figure 5** shows the normalized V K-edge spectra collected during the initial discharging and charging processes and reference spectra of standard vanadium oxides, where V_2O_5 , VO_2 , and V_2O_3 have the oxidation state of +5, +4, and +3, respectively. The edge position of the V K-edge in the pristine V_2O_5 positive electrode overlaps with that of the standard V_2O_5 reference, indicating that the oxidation state of V in V_2O_5 is +5. Moreover, an intense pre-edge peak for the V K-edge of pristine V_2O_5 is observed, which is ascribed to the transitions between the 1s and bound p-hybridized d-states^{59, 60}. Along with progressive discharging, the main absorption edge shifts towards lower binding energies, confirming the reduction of the oxidation state of vanadium upon the Zn-ion insertion. Meanwhile, the pre-peak (A in **Figure 5a**) also shifts gradually to lower binding energy with the simultaneous decrease of intensity, confirming the reduction of V and the deformation of the local V environments during Zn-ions insertion. This is due to the co-existence of a distorted tetragonal pyramid and VO_6 octahedra. The edge resonance (B in **Figure 5a**) displays distinct changes in both intensity and shape, which is caused by the absorption of photons accompanied



by core-electron excitations^{60, 61}. During the discharge process, two broad peaks centered at 5494 eV and 5507 eV shift to lower energy and with a decrease of their intensities, before they converge into one very broad peak centered at 5500 eV from the initial stage to 0.99 V (peak B in **Figure 5a**). After that, the formed broad peak centered at 5500 eV and the peak at 5486.5 eV continuously shift to lower energy accompanied by an increase of both intensities (from 0.99 V to 0.3 V). Two distinct isosbestic points⁶² at ~ 5474 eV and ~ 5502 eV (red arrows in **Figure 5a** and **b**) are observed during both discharge (from 0.99 V to 0.3 V) and charge (from 0.3 V to 1.32 V) processes. This confirms the 2-phase coexistence transitions upon Zn-ions insertion/deinsertion into/from V_2O_5 structure, as already proposed from *in operando* synchrotron diffraction. At the fully discharged state at 0.30 V, the observed energy of the V K-edge lies almost in the middle of those of the V_2O_5 and V_2O_3 reference spectra. This means that the oxidation state of V is very close to V^{4+} , in good agreement with the electrochemical data (see **Figure S5**). However, the energy of the edge does not completely overlap with the spectrum of VO_2 , reflecting structural differences between the discharged state with $x=1.00$ in $Zn_xV_2O_5$ and the reference material VO_2 . During the charging process (Zn-ion deinsertion), a completely reversible behavior can be observed. Pre-peak and edge resonance (A' and B' in **Figure 5a** and **b**) prove a reversible process. At the fully charged state of ~ 1.6 V, the V spectrum returns back to its initial state, indicating that the V ions are fully oxidized to the oxidation state of +5. The evolution of V K-edge spectra reveals that the V ions are reduced and reversibly oxidized during the Zn-ion insertion and deinsertion, respectively, accompanied by the local structural changes around the V ions and in full agreement with *in operando* synchrotron diffraction.

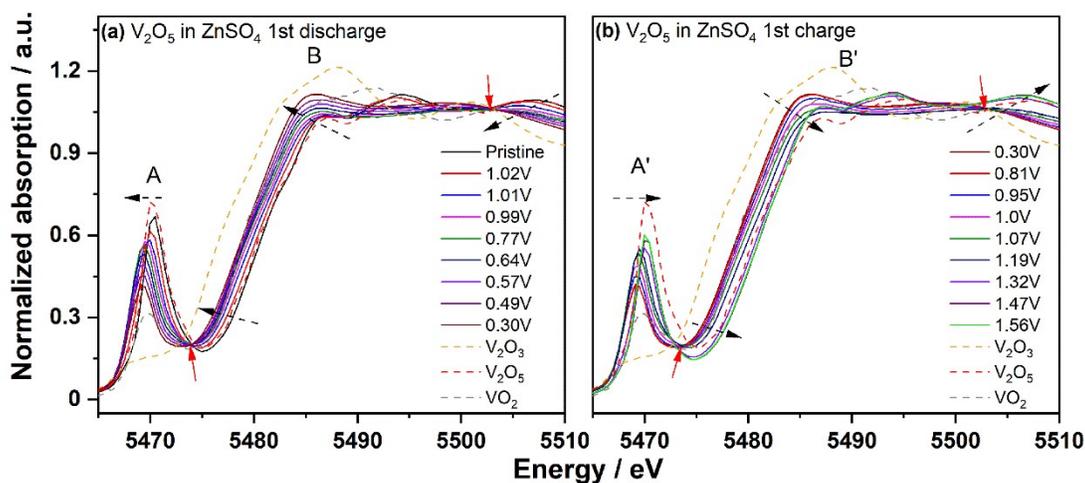


Figure 5 *In operando* V K-edge XANES spectra during the 1st cycle in 1 M ZnSO₄; the isosbestic points are pointed out by red arrows.

Raman spectra were collected to investigate vibration modes as fingerprints of the short-range structure of the samples during Zn-ions insertion/deinsertion, as displayed in **Figure 6** and **Table S1**. In the pristine V₂O₅, oxygen atoms lie in four distinct sites in a [VO₅] pyramid unit, denoted as O(1)–O(4). The stretching mode of V–O(1) bond is located at 994 cm⁻¹ and its bending vibrations are located at 405 and 284 cm⁻¹. Raman peaks at 482 cm⁻¹ and 701 cm⁻¹ are ascribed to the bending vibration of the V–O(3) and the stretching vibration of the V–O(2), respectively. The peaks at 527 and 304 cm⁻¹ are attributed to the stretching and bending vibrations of the V–O(4) bond, respectively. The peaks at lower wavenumbers, 145 and 197 cm⁻¹ are assigned to weak Van der Waals interaction between adjacent [VO₅] slabs. These results are consistent with previous works^{63, 64}. After Zn-ions insertion, significant changes are observed and some peaks related to V₂O₅ at 994, 701, 405, 304, and 284 cm⁻¹ become weak and broad, while those at 527, 482, and 197 cm⁻¹ completely disappear. Meanwhile, some broad and distinct new peaks appear at 1129, 967, 876, 610, and 450 cm⁻¹ for discharged V₂O₅, where peaks at 1129, 967, and 610 cm⁻¹ are attributed to the ν_3 , ν_1 , ν_4 of SO₄²⁻ vibration bands of ZnSO₄Zn₃(OH)₆·nH₂O^{65, 66} and peaks at 876 and 450 cm⁻¹ are related to the V-O and Zn-O bonds in Zn_xV₂O₅ and Zn₃(OH)₂V₂O₇·2H₂O⁶⁷. Therefore, the coexistence of Zn_xV₂O₅ and byproducts, ZnSO₄Zn₃(OH)₆·5H₂O and Zn₃(OH)₂V₂O₇·2H₂O, is concluded in the discharged V₂O₅ electrode. On the other hand, for the Zn counter electrode in a discharged cell, several peaks at 1129, 967, 566, 440, and 398 cm⁻¹ are observed. The peaks appearing at 440 and 566 cm⁻¹ are assigned to the Zn-O vibration of Zn_{1+x}O on the surface of Zn metal^{65, 68}, while 1129, 967, and 398 are assigned to the ν_3 , ν_1 , ν_4 of SO₄²⁻ vibration in the ZnSO₄Zn₃(OH)₆·nH₂O^{65, 66}. Upon charging, the spectrum of fully charged V₂O₅ at 1.6 V returns back to its main original features with less intensity, indicating the disappearance of Zn_xV₂O₅ and the byproducts, ZnSO₄Zn₃(OH)₆·5H₂O and Zn_{3+ δ} (OH)₂V₂O₇·2H₂O. This demonstrates the reversible reaction during Zn-ions insertion and deinsertion as identified by *in operando* synchrotron diffraction and XAS. Moreover, an additional broad peak at 875 cm⁻¹ related to Zn_xV₂O₅ is observed for the counter electrode Zn from a charged cell, compared with that from a discharged one. This indicates that the byproduct ZnSO₄Zn₃(OH)₆·5H₂O does not completely disappear on the surface of Zn metal. Dissolved Zn_xV₂O₅ can pass through the separator and



reaches the surface of Zn metal. This contributes to ongoing degradation and limits the cycling stability.

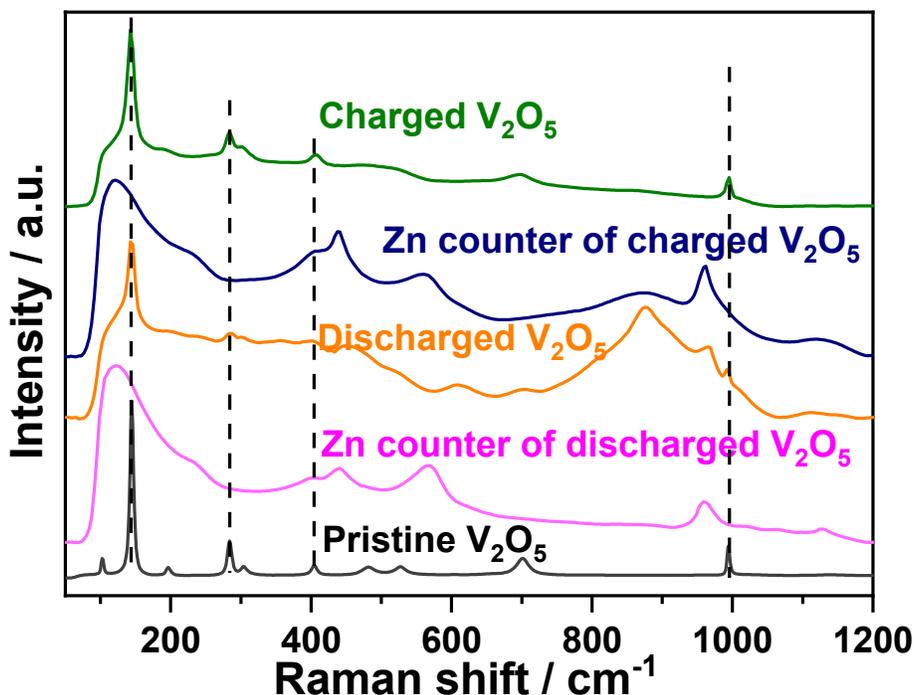


Figure 6 Raman spectra of pristine V₂O₅, the 1st discharged and charged state of V₂O₅ and of the Zn counter electrode from a discharged and charged cell

TEM and elemental mapping were carried out to further study the structural and morphology evolution of V₂O₅ during cycling. It is unable to observe the nanowire-like feature of Zn_xV₂O₅ on the fully discharged electrode, whereas a sheet-like morphology can be clearly seen (**Figure 7a**). **Figure S6** shows that the O, S, V, and Zn elements are uniformly distributed in the sheet-like material. The sheet-like material is probably attributed to the byproducts of ZnSO₄Zn₃(OH)₆·5H₂O, as demonstrated by synchrotron diffraction. **Figure 7b** confirms the disappearance of sheet-like morphology and the recovery of nanowire-like feature of V₂O₅ after the charge process, demonstrating the decomposition of byproducts.



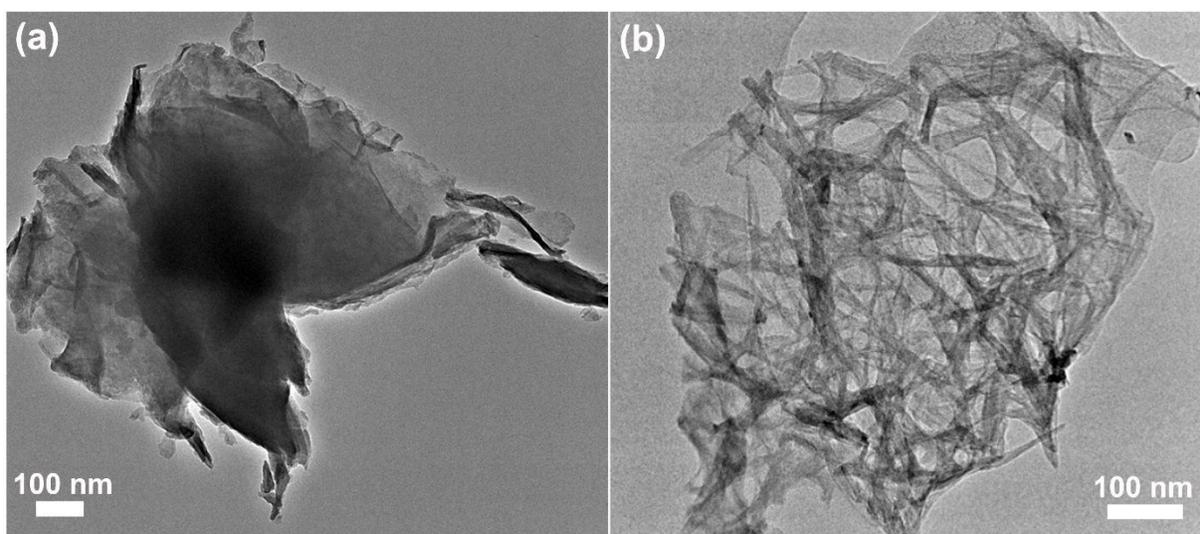


Figure 7 TEM images of discharged (a) and charged V₂O₅ (b)

XPS was applied to investigate the surface chemistry and surface elemental composition of pristine V₂O₅, first discharged V₂O₅, and first recharged V₂O₅. As displayed in **Figure 8**, the V 2p spectrum of pristine V₂O₅ can be fitted with two doublets: a main one with V 2p_{3/2} at 517.6 eV and a second one with weak intensity at 516.3 eV, which demonstrates that V exists mainly in the oxidation state +5 with a minor contribution of vanadium +4. It can be seen that the O 1s spectrum of pristine V₂O₅ can be fitted with one peak at 530.3 eV, corresponding to V–O group. The V 2p spectrum in the discharged state is not visible anymore due to the formation of the byproduct ZnSO₄Zn₃(OH)₆·5H₂O on the surface of the electrode, which blocks photoelectrons. While the V 2p spectrum of the charged state exhibits two V 2p_{3/2} components at 517.7 and 516.4 eV, the spectrum returns back to the one of pristine V₂O₅ after charge. For the discharged state of V₂O₅, a symmetric O 1s spectrum at 532.0 eV is obtained, assigning to the OH⁻ and SO₄²⁻ group of the byproduct ZnSO₄Zn₃(OH)₆·5H₂O, which was formed on the surface of the electrode and makes the O 1s spectrum from buried V–O groups invisible. After charging, the O 1s spectrum of the V–O group is visible again, accompanied by a minor contribution of OH⁻ on the surface of the electrode.



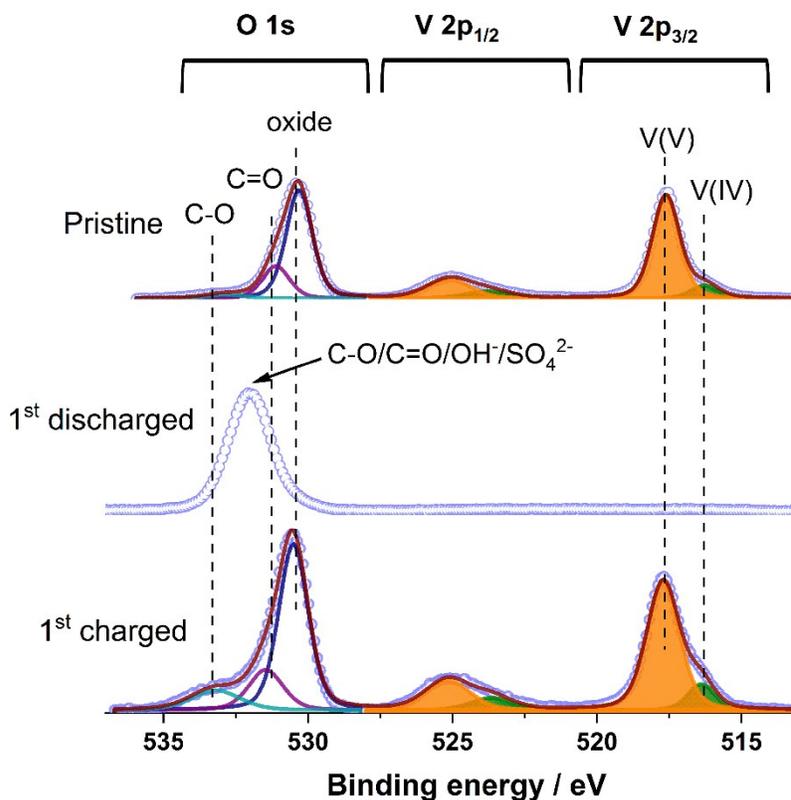


Figure 8 V 2p and O 1s X-ray photoelectron spectra of pristine V_2O_5 , together with the 1st discharged and the 1st charged state.

4. Conclusion

In summary, orthorhombic V_2O_5 nanowires were prepared *via* a facile hydrothermal approach. In the 1 M $ZnSO_4$ electrolyte, V_2O_5 nanowires deliver an initial discharge/charge capacity up to 277 and 432 $mAh\ g^{-1}$, respectively, at a current density of 50 $mA\ g^{-1}$, which almost reaches the theoretical capacity based on 1 Zn^{2+} insertion with two electrons per formula unit V_2O_5 (294 $mAh\ g^{-1}$). The V_2O_5 positive electrode exhibits a dramatic decrease of capacity during the following 20 cycles at 50 $mA\ g^{-1}$ (94 $mAh\ g^{-1}$ for 22nd) and delivers a very low discharge capacity of 21 $mAh\ g^{-1}$ after 100 cycles. Moreover, it delivers an initial discharge capacity of 278 $mAh\ g^{-1}$ at 200 $mA\ g^{-1}$, followed by an activation process of the material. The capacity is higher for 200 $mA\ g^{-1}$ than for 50 $mA\ g^{-1}$, which could be attributed to a different type of activation process under both current densities and different resulting degrees of side reactions (parasitic reactions). CV displays in the first scan two reduction peaks, centered at 0.92 and 0.50 V, and a broad oxidation peak at 1.20 V with a shoulder at 1.05 V. In the following four scans, the CV curves indicate significant changes in both reduction and oxidation peaks. *In operando* synchrotron diffraction focused on the first 1.5



cycles, reveals that V_2O_5 first undergoes a solid solution and 2-phase coexistence transitions upon Zn-ions insertion. It also confirms the formation of two byproducts, $Zn_{3+\delta}(OH)_2V_2O_7 \cdot 2(H_2O)$ and $ZnSO_4Zn_3(OH)_6 \cdot 5H_2O$ during the Zn-ions insertion. The electrode undergoes a reversible process upon Zn-ions deinsertion with the decomposition of both byproducts. The V_2O_5 electrode goes in the 2nd discharge process through the same two-phase reaction as that in the 1st discharge without the formation of the byproduct $Zn_{3+\delta}(OH)_2V_2O_7 \cdot 2(H_2O)$. *In operando* XAS confirms the reduction/oxidation of vanadium during the Zn insertion/deinsertion. Moreover, *ex situ* Raman and XPS also prove the reversibility of the reactions during cycling. The electrochemical performance of V_2O_5 can be improved by electrode engineering such as surface coating with carbon/graphene oxide and electrolyte optimization with more concentrated salt and water-organic solvent.

Acknowledgment

This work contributes to the research performed at CELEST (Center for Electrochemical Energy Storage Ulm-Karlsruhe) and is funded by the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) under Project ID 390874152 (POLiS Cluster of Excellence). Our research work has gained benefit from beamtime allocation at BL04-MSPD at ALBA Synchrotron (2018022738-qfu), Barcelona, Spain, and at PETRA-III beamline P65 (I-20180402) at DESY, Hamburg, Germany. The K-Alpha instrument was supported by the German Federal Ministry of Economics and Technology (grant 03ET6040) based on a decision by the German Bundestag. The authors acknowledge the support of Karlsruhe Nano Micro Facility (KNMF) for the usage of TEM. We thank the help of Dr. Francois Fauth from Experiments Division at ALBA. We thank Mrs. Bettina Hunzinger and Mr. Udo Geckle for their contributions to SEM measurements. We appreciate Dr. Georgian Melinte (HIU) for the helpful discussion regarding TEM result.

Author contributions

Q.F. conceived the idea and discussed with J.W., A.S., L.Z., A.M., E.W., X.L., Z.D., M.K., H.E., and S.D.; Q.F. and J.W. performed material synthesis, sample preparation, characterizations, electrochemical measurements, and analyzed the data. L.Z. performed Raman and analyzed the data. Q.F., J.W., A.S., A.M., E.W., M.K., and H.E. conducted *in operando* measurements and



analyzed the data. X.L. performed XPS measurements and analyzed the XPS data. Z.D. carried out TEM and analyzed the data. Q.F. wrote the preliminary draft with input from J.W.; Q.F., J.W., M.K., H.E., and S.D., discussed the results and revised the manuscript. All authors contributed to interpreting the findings, reviewing, and commenting on the manuscript.

Additional information

Supplementary information is available.

Competing interests

The authors declare no competing financial interests.

Reference

1. H. Kim, J. Hong, K.-Y. Park, H. Kim, S.-W. Kim and K. Kang, *Chemical Reviews*, 2014, **114**, 11788-11827.
2. F. Wan, L. Zhang, X. Dai, X. Wang, Z. Niu and J. Chen, *Nature communications*, 2018, **9**, 1656.
3. M. Song, H. Tan, D. Chao and H. J. Fan, *Advanced Functional Materials*, 2018, **28**, 1802564.
4. C. Xu, B. Li, H. Du and F. Kang, *Angewandte Chemie*, 2012, **51**, 933-935.
5. D. Kundu, B. D. Adams, V. Duffort, S. H. Vajargah and L. F. Nazar, *Nature Energy*, 2016, **1**, 16119.
6. M. H. Alfaruqi, V. Mathew, J. Gim, S. Kim, J. Song, J. P. Baboo, S. H. Choi and J. Kim, *Chemistry of Materials*, 2015, **27**, 3609-3620.
7. B. K. Wu, G. B. Zhang, M. Y. Yan, T. F. Xiong, P. He, L. He, X. Xu and L. Q. Mai, *Small*, 2018, **14**, 1703850.
8. M. H. Alfaruqi, J. Gim, S. Kim, J. Song, J. Jo, S. Kim, V. Mathew and J. Kim, *Journal of Power Sources*, 2015, **288**, 320-327.
9. B. Lee, C. S. Yoon, H. R. Lee, K. Y. Chung, B. W. Cho and S. H. Oh, *Scientific reports*, 2014, **4**, 6066.
10. J. Lee, J. B. Ju, W. I. Cho, B. W. Cho and S. H. Oh, *Electrochimica Acta*, 2013, **112**, 138-143.
11. C. Xu, S. W. Chiang, J. Ma and F. Kang, *Journal of The Electrochemical Society*, 2013, **160**, A93-A97.



12. W. Sun, F. Wang, S. Hou, C. Yang, X. Fan, Z. Ma, T. Gao, F. Han, R. Hu, M. Zhu and C. Wang, *Journal of the American Chemical Society*, 2017, **139**, 9775-9778.
13. M. H. Alfaruqi, J. Gim, S. Kim, J. Song, D. T. Pham, J. Jo, Z. Xiu, V. Mathew and J. Kim, *Electrochemistry Communications*, 2015, **60**, 121-125.
14. S. Islam, M. H. Alfaruqi, V. Mathew, J. Song, S. Kim, S. Kim, J. Jo, J. P. Baboo, D. T. Pham, D. Y. Putro, Y. K. Sun and J. Kim, *Journal of Materials Chemistry A*, 2017, **5**, 23299-23309.
15. M. H. Alfaruqi, S. Islam, J. Gim, J. Song, S. Kim, D. T. Pham, J. Jo, Z. Xiu, V. Mathew and J. Kim, *Chemical Physics Letters*, 2016, **650**, 64-68.
16. B. Lee, H. R. Lee, H. Kim, K. Y. Chung, B. W. Cho and S. H. Oh, *Chemical communications*, 2015, **51**, 9265-9268.
17. H. Pan, Y. Shao, P. Yan, Y. Cheng, K. S. Han, Z. Nie, C. Wang, J. Yang, X. Li, P. Bhattacharya, K. T. Mueller and J. Liu, *Nature Energy*, 2016, **1**, 16039.
18. R. Y. Wang, C. D. Wessells, R. A. Huggins and Y. Cui, *Nano Letters*, 2013, **13**, 5748-5752.
19. K. Lu, B. Song, Y. X. Zhang, H. Y. Ma and J. T. Zhang, *Journal of Materials Chemistry A*, 2017, **5**, 23628-23633.
20. R. Trócoli and F. La Mantia, *ChemSusChem*, 2015, **8**, 481-485.
21. L. Zhang, L. Chen, X. Zhou and Z. Liu, *Advanced Energy Materials*, 2015, **5**, 1400930.
22. M. H. Alfaruqi, V. Mathew, J. Song, S. Kim, S. Islam, D. T. Pham, J. Jo, S. Kim, J. P. Baboo, Z. Xiu, K.-S. Lee, Y.-K. Sun and J. Kim, *Chemistry of Materials*, 2017, **29**, 1684-1694.
23. P. He, Y. L. Quan, X. Xu, M. Y. Yan, W. Yang, Q. Y. An, L. He and L. Q. Mai, *Small*, 2017, **13**, 1702551.
24. J. H. Jo, Y.-K. Sun and S.-T. Myung, *Journal of Materials Chemistry A*, 2017, **5**, 8367-8375.
25. X. Chuan, G. Jing, L. Peng, Z. Xixiang and A. H. N., *Angewandte Chemie International Edition*, 2018, **57**, 3943-3948.
26. X. Chuan, G. Jing, L. Yongjiu, L. Hanfeng, Z. Chao and A. H. N., *Advanced Materials*, 2018, **30**, 1705580.
27. X. Dai, F. Wan, L. Zhang, H. Cao and Z. Niu, *Energy Storage Materials*, 2018, **17**, 143-150.
28. J. Ding, Z. Du, L. Gu, B. Li, L. Wang, S. Wang, Y. Gong and S. Yang, *Advanced Materials*, 2018, **30**, 1800762.
29. P. He, G. Zhang, X. Liao, M. Yan, X. Xu, Q. An, J. Liu and L. Mai, *Advanced Energy Materials*, 2018, **8**, 1702463.
30. P. Hu, T. Zhu, X. Wang, X. Wei, M. Yan, J. Li, W. Luo, W. Yang, W. Zhang, L. Zhou, Z. Zhou and L. Mai, *Nano Letters*, 2018, **18**, 1758-1763.
31. D. Kundu, S. Hosseini Vajargah, L. Wan, B. Adams, D. Prendergast and L. F. Nazar, *Energy & Environmental Science*, 2018, **11**, 881-892.
32. Y. Mengyu, H. Pan, C. Ying, W. Shanyu, W. Qiulong, Z. Kangning, X. Xu, A. Qinyou, S. Yi, S. Yuyan, M. K. T., M. Liqiang, L. Jun and Y. Jihui, *Advanced Materials*, 2018, **30**, 1703725.
33. J. S. Park, J. H. Jo, Y. Aniskevich, A. Bakavets, G. Ragoisha, E. Streltsov, J. Kim and S. T. Myung, *Chemistry of Materials*, 2018, **30**, 6777-6787.



34. P. Qiang, S. Congli, Y. Yanhao, Z. Kangning, Z. Ziyi, V. P. M., C. Gang, W. Yingjin and W. Xudong, *Advanced Energy Materials*, 2018, **0**, 1800144.
35. B. Sambandam, V. Soundharrajan, S. Kim, M. H. Alfaruqi, J. Jo, S. Kim, V. Mathew, Y. K. Sun and J. Kim, *Journal of Materials Chemistry A*, 2018, **6**, 3850-3856.
36. B. Sambandam, V. Soundharrajan, S. Kim, M. H. Alfaruqi, J. Jo, S. Kim, V. Mathew, Y. K. Sun and J. Kim, *Journal of Materials Chemistry A*, 2018, **6**, 15530-15539.
37. C. Shen, X. Li, N. Li, K. Xie, J.-g. Wang, X. Liu and B. Wei, *ACS applied materials & interfaces*, 2018, **10**, 25446-25453.
38. V. Soundharrajan, B. Sambandam, S. Kim, M. H. Alfaruqi, D. Y. Putro, J. Jo, S. Kim, V. Mathew, Y. K. Sun and J. Kim, *Nano Letters*, 2018, **18**, 2402-2410.
39. D. Kundu, P. Oberholzer, C. Glaros, A. Bouzid, E. Tervoort, A. Pasquarello and M. Niederberger, *Chemistry of Materials*, 2018, **30**, 3874-3881.
40. W. H. Qing Zhao, Zhiqiang Luo, LuoJia Liu, Yong Lu, Yixin Li, Lin Li, Jinyan Hu, Hua Ma and Jun Chen,, *Science Advances*, 2018, **4**, eaao176.
41. L. Li, S. Peng, H.-Y. Chen, X. Han, F. Cheng, M. Srinivasan, S. Adams, S. Ramakrishna and J. Chen, *Nano Energy*, 2016, **19**, 307-317.
42. W. Li, K. Wang, S. Cheng and K. Jiang, *Energy Storage Materials*, 2018, **15**, 14-21.
43. P. He, M. Yan, G. Zhang, R. Sun, L. Chen, Q. An and L. Mai, *Advanced Energy Materials*, 2017, **7**, 1601920.
44. Y. Cheng, L. Luo, L. Zhong, J. Chen, B. Li, W. Wang, S. X. Mao, C. Wang, V. L. Sprenkle, G. Li and J. Liu, *ACS applied materials & interfaces*, 2016, **8**, 13673-13677.
45. N. Zhang, Y. Dong, M. Jia, X. Bian, Y. Wang, M. Qiu, J. Xu, Y. Liu, L. Jiao and F. Cheng, *ACS Energy Letters*, 2018, **3**, 1366-1372.
46. J. Zhou, L. Shan, Z. Wu, X. Guo, G. Fang and S. Liang, *Chemical communications*, 2018, **54**, 4457-4460.
47. X. Chen, L. Wang, H. Li, F. Cheng and J. Chen, *Journal of Energy Chemistry*, 2019, **38**, 20-25.
48. D. M. Xu, H. W. Wang, F. Y. Li, Z. C. Guan, R. Wang, B. B. He, Y. S. Gong and X. L. Hu, *Advanced Materials Interfaces*, 2019, **6**.
49. B. Y. Tang, J. Zhou, G. Z. Fang, F. Liu, C. Y. Zhu, C. Wang, A. Q. Pan and S. Q. Liang, *Journal of Materials Chemistry A*, 2019, **7**, 940-945.
50. G. Li, S. Pang, L. Jiang, Z. Guo and Z. Zhang, *The Journal of Physical Chemistry B*, 2006, **110**, 9383-9386.
51. T. Zhai, H. Liu, H. Li, X. Fang, M. Liao, L. Li, H. Zhou, Y. Koide, Y. Bando and D. Golberg, *Advanced Materials*, 2010, **22**, 2547-2552.
52. F. Fauth, I. Peral, C. Popescu and M. Knapp, *Powder Diffraction*, 2013, **28**, S360-S370.
53. K. L. Parry, A. G. Shard, R. D. Short, R. G. White, J. D. Whittle and A. Wright, *Surface and Interface Analysis*, 2006, **38**, 1497-1504.
54. J. Rodríguez-Carvajal, in *Commission on Powder Diffraction (IUCr). Newsletter*, 2001, **26**, 12-19.
55. B. Ravel and M. Newville, *Journal of Synchrotron Radiation*, 2005, **12**, 537-541.
56. V. Shklover, T. Haibach, F. Ried, R. Nesper and P. Novák, *Journal of Solid State Chemistry*, 1996, **123**, 317-323.
57. N. Zhang, F. Cheng, Y. Liu, Q. Zhao, K. Lei, C. Chen, X. Liu and J. Chen, *Journal of the American Chemical Society*, 2016, **138**, 12894-12901.



58. K. Zhu, T. Wu and K. Huang, *Chemistry of Materials*, 2021, DOI: 10.1021/acs.chemmater.1c00715.
59. T. Tanaka, H. Yamashita, R. Tsuchitani, T. Funabiki and S. Yoshida, *Journal of the Chemical Society, Faraday Transactions 1: Physical Chemistry in Condensed Phases*, 1988, **84**, 2987-2999.
60. J. Wong, F. W. Lytle, R. P. Messmer and D. H. Maylotte, *Physical Review B*, 1984, **30**, 5596-5610.
61. H. D. Yoo, Y. Liang, H. Dong, J. Lin, H. Wang, Y. Liu, L. Ma, T. Wu, Y. Li, Q. Ru, Y. Jing, Q. An, W. Zhou, J. Guo, J. Lu, S. T. Pantelides, X. Qian and Y. Yao, *Nature communications*, 2017, **8**, 339.
62. X. Liu, D. Wang, G. Liu, V. Srinivasan, Z. Liu, Z. Hussain and W. Yang, *Nature communications*, 2013, **4**, 2568.
63. R. Baddour-Hadjean, J. P. Pereira-Ramos, C. Navone and M. Smirnov, *Chemistry of Materials*, 2008, **20**, 1916-1923.
64. G. Gershinsky, H. D. Yoo, Y. Gofer and D. Aurbach, *Langmuir*, 2013, **29**, 10964-10972.
65. H. Marchebois, S. Joiret, C. Savall, J. Bernard and S. Touzain, *Surface & Coatings Technology*, 2002, **157**, 151-161.
66. J. Kasperek and M. Lenglet, *Rev. Met. Paris*, 1997, **94**, 713-719.
67. S. Ni, G. Zhou, S. Lin, X. Wang, Q. Pan, F. Yang and D. He, *Materials Letters*, 2009, **63**, 2459-2461.
68. R. Zhang, P.-G. Yin, N. Wang and L. Guo, *Solid State Sciences*, 2009, **11**, 865-869.

