

Energy consumption of current and future production of lithium-ion and post lithium-ion battery cells

Received: 1 August 2022

F. Degen¹✉, M. Winter^{2,3}, D. Bendig⁴ & J. Tübke^{1,5}

Accepted: 16 August 2023

Published online: 28 September 2023

 Check for updates

Due to the rapidly increasing demand for electric vehicles, the need for battery cells is also increasing considerably. However, the production of battery cells requires enormous amounts of energy, which is expensive and produces greenhouse gas emissions. Here, by combining data from literature and from own research, we analyse how much energy lithium-ion battery (LIB) and post lithium-ion battery (PLIB) cell production requires on cell and macro-economic levels, currently and in the future (until 2040). On the cell level, we find that PLIB cells require less energy than LIB cells per produced cell energy. On the macro-economic level, we find that the energy consumption for the global production of LIB and PLIB cells will be 130,000 GWh if no measures are taken. Yet, it is possible to optimize future production and save up to 66% of this energy demand.

Global warming is a serious threat to our society¹. Thus, policymakers are increasingly addressing environmental and social sustainability. In Europe, the European Commission plans to reduce greenhouse gas (GHG) emissions substantially by 2030 (ref. 2) and to be GHG emission neutral by 2050 (ref. 3). A major enabler for achieving this goal is the transition from cars with internal combustion engines to electric vehicles⁴. Many global car companies already have declared that they will no longer produce internal combustion engine cars in the mid-term^{5,6}. As a result, the demand for battery cells is increasing markedly. The World Economic Forum predicted that the global battery demand will be 2,600 GWh in 2030 (ref. 7). Figure 1 shows the expected global battery demand from 2021 to 2040 (refs. 7–13) for different Shared Socioeconomic Pathway (SSP) scenarios, as well as the forecasted market shares of different battery chemistries¹⁴.

The SSP is a framework of possible narratives for possible the future of humanity until the year 2100 (ref. 15). Five different possible futures of humanity are described, that is, sustainability (SSP1), middle of the road (SSP2), regional rivalry (SSP3), inequality (SSP4) and fossil fuel (SSP5)¹⁵. For the future demand for batteries, scenarios SSP1, SSP2 and SSP5 are the most important¹⁰.

Figure 1 shows that, in the SSP2 scenario (middle way), the global demand for battery cells will reach approximately 5,500 GWh in 2040 (refs. 10,12). In the SSP1 (sustainable) scenario, the demand for battery cells could reach 10,000 GWh in 2040, and in the SSP5 scenario (fossil-fuelled), battery cell demand will reach only approximately 2,900 GWh (refs. 10,12). According to market share forecasts from ref. 14, lithium–iron–phosphate (LFP) battery cells will become more important in the future and nickel–manganese–cobalt (NMC) battery cells with high nickel content will have a notable market share in 2040 (ref. 14). Furthermore, the market share of new types of battery cells, respectively post lithium-ion battery (PLIB) cells, will become important in 2030 and reach a market share of approximately 39% in 2040 (ref. 14), still what types of PLIB cells are meant is not specified. However, Xu et al. suggested further possible future market share scenarios for 2040, such as a >95% NCX (X stands for any suitable element) market share scenario, a 60% LFP market share scenario and a 60% PLIB market share scenario¹⁶. Therefore, the market shares shown in Fig. 1, which are based on ref. 14, are a mix of different, more extreme scenarios of ref. 16.

Currently, lithium-ion batteries (LIBs) are the state-of-the-art battery cell type¹⁶ owing to their high energy density (up to 750 Wh l⁻¹) and

¹Fraunhofer Research Institution for Battery Cell Production FFB, Münster, Germany. ²Münster Electrochemical Energy Technology, University of Münster, Münster, Germany. ³Helmholtz Institute Münster (IEK-12/HI MS), Forschungszentrum Jülich GmbH, Jülich, Germany. ⁴School of Business and Economics, University of Münster, Münster, Germany. ⁵Institute of Mechanical Process Engineering and Mechanics (MVM), Karlsruhe Institute of Technology, Karlsruhe, Germany. ✉e-mail: florian.degen@ffb.fraunhofer.de

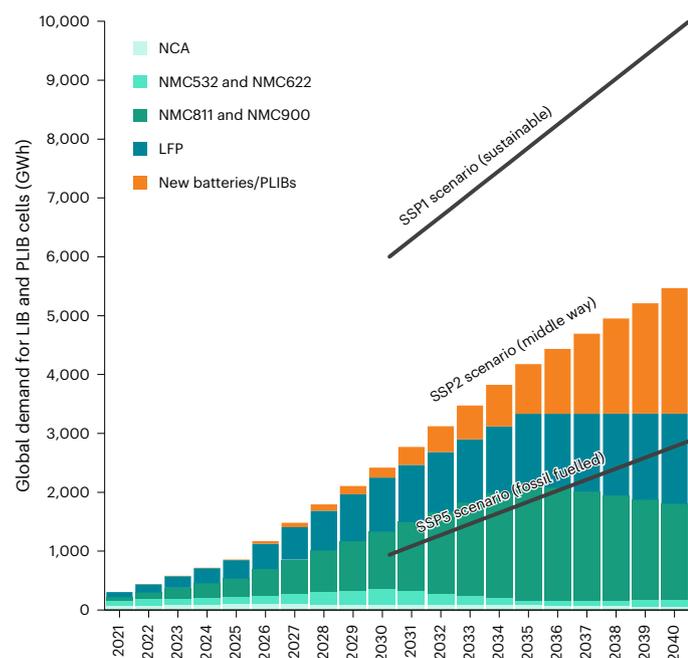


Fig. 1 | Development of the global demand for LIB and PLIB cells. The numbers are based on market demand forecasts for 2021–2030 (refs. 7–9,11,13) and 2030–2040 (refs. 10,12) combined with a forecast of market share of cathode chemistries¹⁴. All market data and calculations can be found in Source Data Fig. 1. NCA, nickel–cobalt–aluminium.

long cycle life (1,000–6,000 cycles), despite several controversially discussed disadvantages^{17,18}. To overcome these disadvantages, current cell research and development are focused on increasing energy density while decreasing cost, environmental footprint and safety concerns. Thus, cathode development trends lean towards higher nickel contents, such as NMC900, to improve the energy density^{19,20}, while anode development trends lean towards higher shares of Si and SiO (refs. 21,22). To foster sustainability and safety as well as reduce cost, development trends are moving towards LFP cells because they do not require the use of cost-intensive nickel and cobalt^{23,24}.

To further improve battery cells, new types of battery cells, such as PLIB cells, are being developed. One group of PLIB cells is metal-ion battery cells, in which lithium is replaced by, for example, sodium, magnesium, aluminium or zinc²⁵. Another group of PLIB cells uses lithium metal on the anode side instead of graphite or silicon or silicon/graphite. Some examples include solid state battery (SSB) cells with a sulfidic, oxidic or polymer-based solid electrolyte (SE). Other PLIB cells with lithium metal are lithium/sulfur battery (LSB) and lithium oxygen/air battery (LAB) cells. Within these cell chemistry classes, a wide range of various PLIB types are possible.

The types of PLIB cells that will reach industrial-scale production currently are unknown. Bhandari et al. forecasted three major technology steps¹⁴: first, PLIB cell generation will have lithium metal on the anode side combined with state-of-the-art cathode materials in an SE. According to Schmalz et al., polymer-based SSBs will be commercially available first, and they will be followed by oxidic SSBs and then sulfidic SSBs¹². The second step involves PLIB cell generation LSB cells, and the third step involves the generation of PLIB LAB cells^{26,27}. In addition, it has been predicted that sodium ion battery (SIB) cells will be commercialized within the next few years^{18,28}. Other PLIB types are in development, but they are not yet considered in most mid-term battery forecasts²⁹. For example, for aluminium-ion, aluminium/air and zinc/air batteries, several challenges must be overcome³⁰. Thus, improved LIB cells as well as SIB, SSB, LSB and LAB cells are believed today to be

the types of battery cells with the highest commercialization potential in the mid-term^{16,18,26,27,29}.

To produce today's LIB cells, calculations of energy consumption for production exist, but they vary extensively. Studies name a range of 30–55 kWh_{prod} per kWh_{cell} of battery cell when considering only the factory production and excluding the material mining and refining^{31–33}. A comprehensive comparison of existing and future cell chemistries is currently lacking in the literature. Consequently, how energy consumption of battery cell production will develop, especially after 2030, but currently it is still unknown how this can be decreased by improving the cell chemistries and the production process. This is essential, as energy is a valuable resource and probably will continue to be for the foreseeable future.

In this Analysis, our aim is to determine how much energy is required for the current and future production of LIB and PLIB cells on a battery cell level and on a macro-economic level. Material mining and refining were excluded from this study due to their complexity.

The analysis was conducted as follows: First, it was determined how the energy consumption in production would change relatively if PLIB cells were produced instead of LIB cells. Then it was calculated how much energy is needed to produce 1 kWh_{cell} of cell energy according to the current state of the art. Subsequently, it was analysed how techno-economic effects will affect future energy consumption. On this basis, it was then calculated how much energy is needed to produce 1 kWh_{cell} of cell energy in the future. Finally, it was calculated how much energy is needed to produce the worldwide demand for batteries from today until 2040.

Energy consumption changes to produce PLIB cells

In the first step, we analysed how the energy consumption of a current battery cell production changes when PLIB cells are produced instead of LIB cells. As a reference, an existing LIB factory model was used^{31,34}, which is provided in Supplementary Fig. 1 and Supplementary Table 1. How future PLIB production technology routes might look and which technology routes we used as references in this study are shown in Supplementary Fig. 2. However, to be able to quantify the percentage of the change in energy consumption between LIB and PLIB cell production, we conducted workshops in which experts rated each single production step. Details about this work are provided in Methods and in Supplementary Note 1. The results that were obtained are shown in Fig. 2.

Energy consumption for today's production on cell level

Based on the numbers in Fig. 2, the energy consumption of PLIB cell production is calculated. Figure 3 shows the energy consumption for each production step of all relevant LIB¹⁴ and PLIB cells likely to be commercially relevant from now until 2040 (ref. 26). The energy necessary to produce 1 kWh_{cell} of cell energy for nickel-cathode-based LIB cells ranges between 20 kWh_{prod} and 29 kWh_{prod}. The energy consumption of LIB cell production decreases as the energy density increases. NMC900 cells with carbon-based and silicon anodes have the lowest energy demand in LIB cell production, with approximately 20.3 kWh_{prod}. Notably, LFP cells, with 37.5 kWh_{prod}, have the highest production energy demand of all of the battery cells that were analysed. Furthermore, in LIB cell production today, the largest amount of energy is consumed by the three production steps of coating, drying and formation, with the dry rooms being the largest energy consumer.

Regarding PLIB cells, Fig. 3 shows that SIB cells are likely to have an energy demand of 23.0 kWh_{prod}, based on today's production technology and know-how for LIB production. This is on a level that is similar to current NMC811 cells. SSB energy consumption in production varies depending on the SE that is used because this notably affects the required production infrastructure¹⁸. Polymer-based SSBs have the lowest energy demand (10.6 kWh_{prod}), followed by oxidic SSBs (11.8 kWh_{prod}), and sulfidic SSBs have the highest energy demand

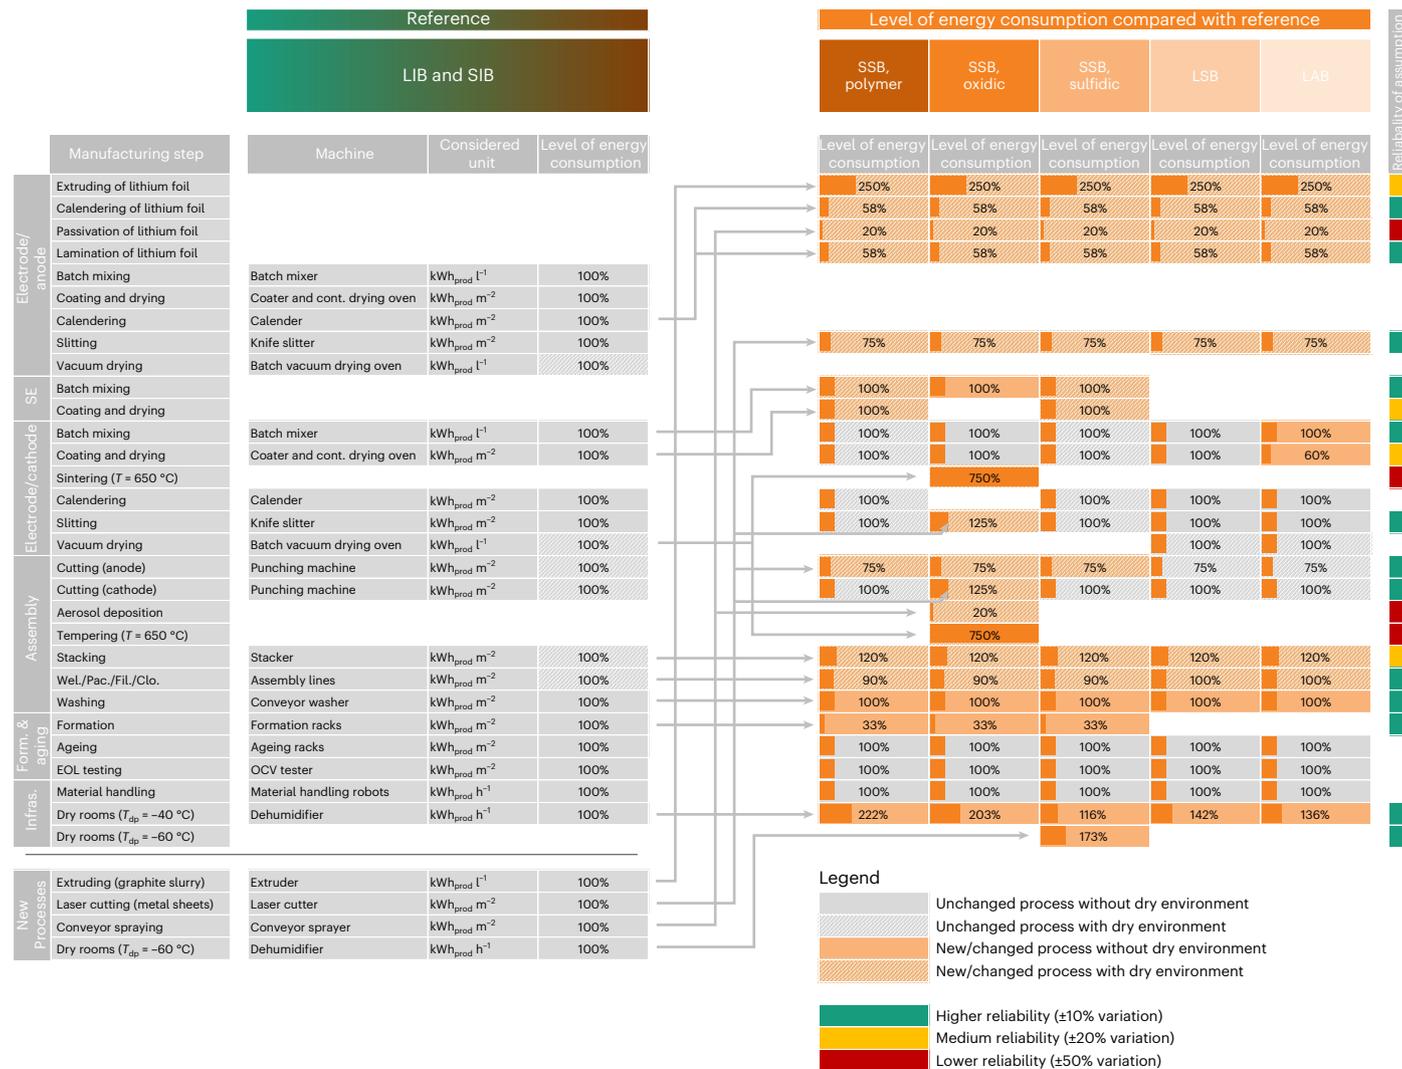


Fig. 2 | Estimated changes in energy consumption when producing PLIB cells instead of LIB cells. LIB and PLIB cell design and qualitative estimates of which production processes will be changed when producing PLIBs by Duffner et al.¹⁸; technical data and energy consumption on a state-of-the-art LIB factory by Degen and Schütte³¹. The used technology routes can be found in Supplementary Fig. 1. The quantitative changes are the results of this study. Further details can be found in Source Data Fig. 2. The production output of each LIB/PLIB

production step is assumed to be constant. Reliability refers to only new/changed production processes. Note: to achieve a constant dew point of $T_{\text{dp}} = -40\text{ }^{\circ}\text{C}$, the air supply has to have a dew point of $T_{\text{dp}} = -60\text{ }^{\circ}\text{C}$ ($T_{\text{dp}} = 70\text{ }^{\circ}\text{C}$ air supply for a constant dew point of $T_{\text{dp}} = -60\text{ }^{\circ}\text{C}$). EOL, end of line; OCV, open circuit voltage; T_{dp} , dew point temperature; Wel., welding; Pac., packaging; Fil., electrolyte filling; Clo., closing; cont., continuous; Form., formation; Infrast., infrastructure.

($17.5\text{ kWh}_{\text{prod}}$). Based on today's production technology, LSB cells will require $13.4\text{ kWh}_{\text{prod}}$ and LAB cells will require $20.9\text{ kWh}_{\text{prod}}$. However, these results are affected by the different areal energy density ($\text{kWh}_{\text{prod}} \text{per m}^2_{\text{cell}}$) of the analysed cell chemistry. The material flow of a battery cell factory is assumed to be constant (in particular m^2 of produced and processed electrodes), and Fig. 4 shows how much energy is required per area of electrode material produced and processed (in $\text{kWh}_{\text{prod}} \text{per m}^2_{\text{cell}}$).

Figure 4 shows that all LIB cells and SIB cells have the same average energy consumption of $5.2\text{ kWh}_{\text{prod}} \text{per m}^2_{\text{cell}}$ in production. That means that, for LIB and SIB cells, the different energy consumption per produced cell energy ($\text{kWh}_{\text{prod}} \text{per kWh}_{\text{cell}}$) from Fig. 3 results solely from the different areal energy densities ($\text{kWh}_{\text{cell}} \text{per m}^2_{\text{cell}}$) of the cell chemistries. However, PLIB cells also show different energy consumptions per material throughput from those of LIB and SIB cells due to their different production infrastructure. For SSB cells, the energy consumption per produced and processed electrode area ($\text{kWh}_{\text{prod}} \text{per m}^2_{\text{cell}}$) is higher than it is for LIB cells. But due to the higher areal energy

densities ($\text{kWh}_{\text{cell}} \text{per m}^2_{\text{cell}}$) of the SSB cells compared with the LIB cells, lower energy consumption per produced cell energy ($\text{kWh}_{\text{prod}} \text{per kWh}_{\text{cell}}$) is the result. For LSB and LAB cells, the opposite is true, that is, notably less energy is required per produced and processed electrode area, but due to the lower areal energy densities of the LSB and LAB cells, their energy consumption per produced cell energy ($\text{kWh}_{\text{prod}} \text{per kWh}_{\text{cell}}$) is comparable to LIB cells.

Techno-economic effects on future's energy consumption

There are natural uncertainties in any market forecasts and energy modelling, which so far have not been considered. In addition, it can be assumed that the production of battery cells will be improved in the future through new technologies. Therefore, in this analysis, we calculated the impact of new production and material technologies on the future energy consumption of production as shown in Table 1. In particular, we selected those technologies that have notable impacts on the main energy consumers in the production of battery cells, for

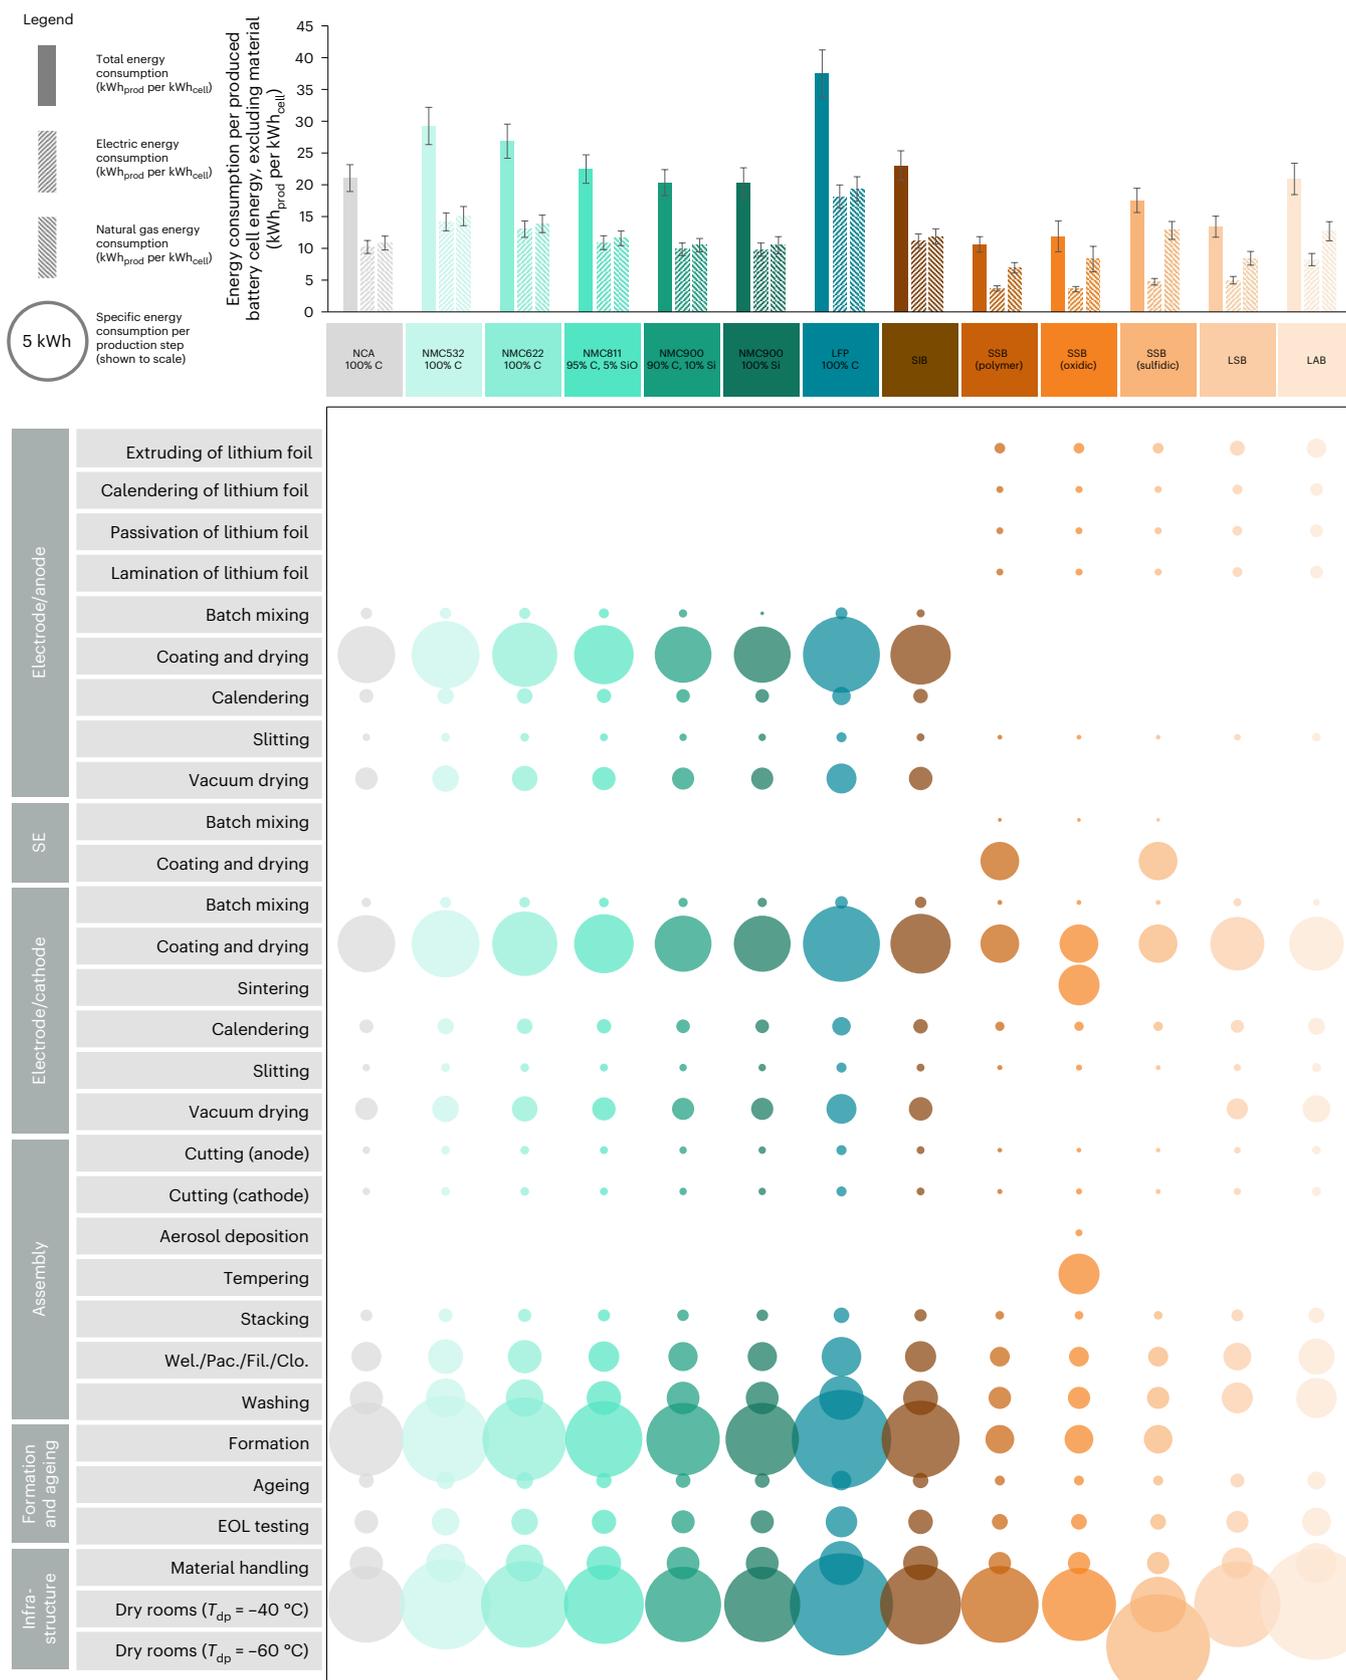


Fig. 3 | Calculated energy consumption (kWh_{prod}) for LIB and PLIB cell production per produced kWh_{cell} of cell energy with today's production technology. The different sizes of the circles represent the different sums of energy (kWh_{prod}) of electricity and natural gas. Detailed numbers can be found in Source Data Fig. 3. The main bars show the calculated mean value. The error

bars show the s.d. resulting from the uncertainties in the expert assessments. Sixty experts were interviewed ($n = 60$). Any battery materials are excluded from the assessment. EOL, end of line; T_{dp} , dew point temperature. Wel., welding; Pac., packaging; Fil., electrolyte filling; Clo., closing.

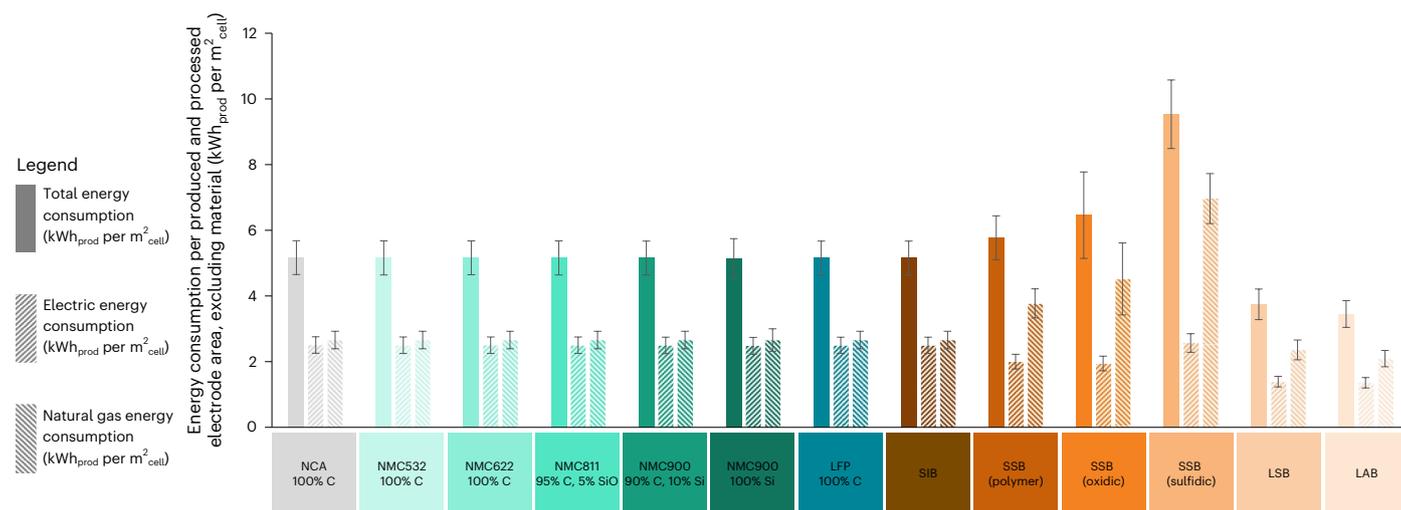


Fig. 4 | Calculated energy consumption for LIB and PLIB cell production (kWh_{prod}) per produced and processed electrode area (m²_{cell}) of a battery cell factory. Detailed numbers can be found in Source Data Fig. 4. The main bars

show the calculated mean value. The error bars show the s.d. resulting from the uncertainties in the expert assessments. Sixty experts were interviewed ($n = 60$).

example, drying, dry room, formation and sintering/tempering and might be industrialized and used extensively by 2040. The calculations for this are available in Source Data Table 1. Further information can be found in Supplementary Note 2. It has been shown that when new technologies are fully (100%) industrialized and applied by 2040, between 42.5% and 57.0% savings in energy consumption per produced and processed electrode area can be achieved. This corresponds to an annual saving of 3.0–4.3%, depending on the cell chemistry.

In addition to the further development of production and material technologies, there are other techno-economic effects that can reduce energy consumption in production, such as the use of heat pumps, learning effects and economies of scale³⁵. How these improvements can affect global energy consumption in the production of battery cells in 2040 is shown in Fig. 5. Figure 5 also shows how uncertainties in market growth, market distribution and energy demand modelling can affect global energy consumption in battery cell production in 2040. Figure 5 shows that the largest future uncertainties are market growth and the market distribution of future cell chemistries. It also shows that the largest energy savings are possible through new technologies (31–52%) and the use of heat pumps (11–20%). Learning effects (14–26%) and economies of scale (8–16%) also are relevant, but they are less important.

Energy consumption for future's production on cell level

How these improvements affect the energy consumption of the production of a single LIB or PLIB cell until 2040 is shown in Fig. 6. Due to technology improvements, use of heat pumps, learning effects and economies of scale for the production of LIB and PLIB cells, the energy demand will be notably lower in 2040 than with today's production technology and know-how. For instance, to produce an LFP cell today, 37.5 kWh_{prod} per kWh_{cell} is necessary; in 2040, only 12.9 kWh_{prod} per kWh_{cell} will be necessary. However, due to the uncertainties associated with future developments, a wide range between 8.2 and 20.1 kWh_{prod} per kWh_{cell} is possible for LFP cells. Nevertheless, for all analysed LIB and PLIB cells, a reduction of energy consumption for production of 62–71% is forecasted, depending on the cell chemistry.

Energy consumption on macro-economic level

Figure 7 shows how energy demand for global production of LIB and PLIB cells probably will develop from today to 2040 in the SSP2

(middle way) scenario. This is done for a mixed, an LFP, an NMX and a PLIB market share scenario. Techno-economic effects, such as technology improvements, the use of heat pumps, learning effects and economies of scale, are considered now. In addition, uncertainties regarding these effects and energy modelling are examined and illustrated by error bars. As a reference, the energy demand forecast is illustrated on the basis of today's technology level.

Figure 7 shows that, based on the analysed techno-economic effects, the energy consumption of LIB and PLIB cell production will be notably lower than when extrapolating today's energy demands in LIB and PLIB cell production to future market demands and shares. According to our calculations, for a mixed scenario in 2040, instead of approximately 130,000 GWh_{prod} (today's technology extrapolated to the future), 44,600 GWh_{prod} will be necessary for LIB and PLIB cell production per year, excluding material. This is a decrease of 85,400 GWh_{prod} per year or 66% due to the improvement of production.

Figure 7 also shows that in a possible future scenario where PLIBs have even higher market shares, for example, in 2040, only 33,800 GWh_{prod} per year will be necessary for global cell production, which is a further decrease of 10,800 GWh_{prod} compared with the mixed scenario. However, in a mixed scenario, we identified a peak in 2031, where energy demand in LIB and PLIB cell production stops increasing, although the global battery demand is still growing. Afterwards, according to our calculations, even a minor decrease in energy consumption for global LIB and PLIB cell production is possible in the future.

However, Fig. 7 also shows that PLIB cells favour low energy demands in global production, while LFP cells disfavour these. In an NMX scenario the future energy demand is similar to the mixed scenario, where NMX, LFP and PLIB cells have similar market shares in 2040. The GHG emissions resulting from the calculated energy consumption are shown in Supplementary Figs. 4 and 5.

Discussion

The results show that, by today's production technology and today's know-how, PLIB cell production will require less energy (10.6–23.0 kWh_{prod} per kWh_{cell}) than LIB cell production (20.3–37.5 kWh_{prod} per kWh_{cell}), when excluding the material from this calculation. We show that these results are affected strongly by the areal energy density of the specific cell chemistry. When relating the energy consumption only to the area of produced and processes electrodes, LIB and SIB cells require

Table 1 | Analysis of energy savings per produced and processed area of electrodes, due to new production technologies and material technologies

New production technology	Affected production step	LIB	SIB	SSB (polymer)	SSB (oxidic)	SSB (sulfidic)	LSB	LAB	Summary of physical effect of technology regarding energy consumption, compared with the reference process	Assumed electric energy consumption of machine	Assumed thermal energy consumption of machine
Coating of high-solid slurry		-7.2%	-7.2%	-6.5%	-2.9%	-3.9%	-5.0%	-3.2%	Less liquid solvent requires less drying, more solid required more mechanical force	+50%	-33%
Laser drying		-12.3%	-12.3%	-11.1%	-4.9%	-6.7%	-8.5%	-5.5%	Laser drying is more efficient, but laser generation requires more electricity	+566%	-100%
Near-infrared (NIR) drying	Drying of electrode (reference: convective drying)	-12.3%	-12.3%	-11.1%	-4.9%	-6.7%	-8.5%	-5.5%	NIR drying is more efficient, but NIR beam generation requires more electricity	+566%	-100%
Dry coating		-18.2%	-18.2%	-16.4%	-7.3%	-9.9%	-12.6%	-8.2%	No liquid has to be dried anymore, but material has processed by mechanical force	+310%	-100%
Smart dry rooms		-3.7%	-3.7%	-7.4%	-6.1%	-10.4%	-7.3%	-7.9%	Air is dehumidified only when required	-15%	-15%
Macro-environments	Dry rooms (reference: full room with -40 °C dew point)	-7.4%	-7.5%	-14.8%	-12.1%	-20.8%	-14.6%	-15.8%	Less air is dehumidified	-30%	-30%
Micro-environments		-16.1%	-16.2%	-32.2%	-26.3%	-45.1%	-31.6%	-34.3%	Much less air is dehumidified	-65%	-65%
Water-insensitive electrolytes		-22.3%	-22.4%	n/a	n/a	n/a	n/a	n/a	No air is dehumidified, but air still has to be cleaned (clean room) and chilled	-90%	-90%
Prelithiation		-2.3%	-2.3%	-0.7%	-0.6%	-0.4%	n/a	n/a	Slightly less energy required for formation and solid electrolyte interphase generation	-10%	-10%
High c-rate formation	Formation of cells (reference: 3 cycles at Ø0.25C)	-5.8%	-5.8%	-1.7%	-1.5%	-1.0%	n/a	n/a	Less cycle and less energy demand, but more heat losses due to higher currents	-25%	-25%
Adaptive formation with partial cycles		-11.5%	-11.6%	-3.4%	-3.1%	-2.1%	n/a	n/a	Less cycle and less energy demand, but more heat losses due to higher currents and controls	-50%	-50%
Improved oxidic SE precursor	Sintering and tempering	n/a	n/a	n/a	-7.5%	n/a	n/a	n/a	Instead of 650 °C, sintering and tempering takes place at 450 °C		-30%
Combination of technologies with highest energy saving potential		-52.1%	-52.2%	-51.9%	-44.1%	-57.1%	-44.1%	-42.5%	Combination of dry coating, adaptive formation with partial cycles and water-insensitive cell chemistry (LIB and SIB) or micro-environments (SSB, LSB and LAB)		
Average annual savings (2021-2040)		-3.80%	-3.81%	-3.78%	-3.02%	-4.36%	-3.02%	-2.87%	For 100% use of above-mentioned technologies in 2040		
		-2.80%	-2.80%	-2.79%	-2.26%	-3.16%	-2.27%	-2.16%	For 80% use of above-mentioned technologies in 2040		
		-1.95%	-1.96%	-1.95%	-1.60%	-2.18%	-1.61%	-1.54%	For 60% use of above-mentioned technologies in 2040		

We selected those technologies that have a notable impact on the main energy consumers in the production of battery cells (drying, dry room, formation and sintering/tempering) and might be industrialized and used extensively by 2040. Detailed numbers can be found in Source Data Table 1, n/a, not applicable.

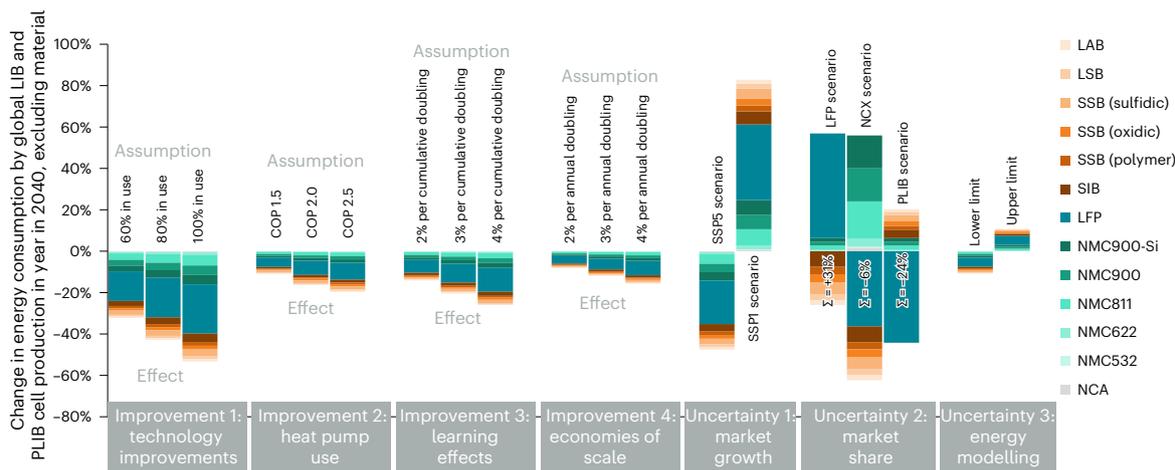


Fig. 5 | Analysis regarding decreased energy consumptions due to techno-economic effects and improvements and uncertainties of our assumptions. We assumed that battery cell production will be improved markedly in the

future, so the demand for energy will decrease. The most important effects are technology improvements, use of heat pumps, learning effects and economies of scale³⁵. The calculations are in Source Data Fig. 5.

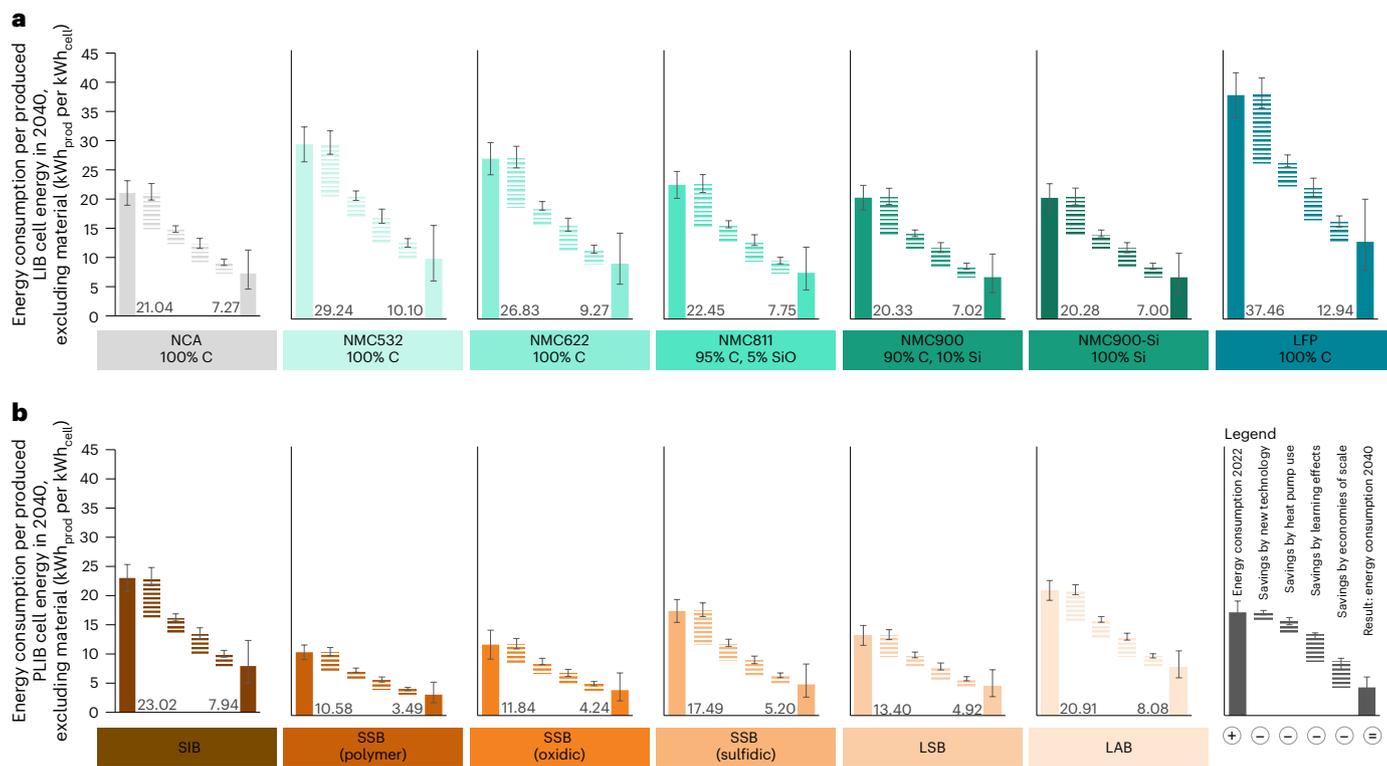


Fig. 6 | Calculated energy consumption (kWh_{prod}) for LIB cell and PLIB cell production per produced kWh_{cell} of cell energy based on today's (2022) technology level and for the technology level of 2040. a, b, Energy consumption for LIB cell (a) and PLIB cell (b) production. It is assumed that the current energy consumption will be improved substantially by technology

improvements, heat pump use, learning effects and economies of scale. Detailed numbers can be found in Source Data Fig. 6. The main bars show the calculated mean value. The error bars show the s.d. resulting from the uncertainties in the expert assessments. Sixty experts were interviewed ($n = 60$).

5.2 kWh_{prod} per m²_{cell}. SSB cells require 5.8 – 9.6 kWh_{prod} per m²_{cell}. LSB cells 3.7 kWh_{prod} per m²_{cell} and LAB cells 3.5 kWh_{prod} per m²_{cell}.

However, when considering future developments, by various techno-economic effects, until 2040 a reduction of energy demand between 62% and 70% is possible resulting in 7.0–12.9 kWh_{prod} per kWh_{cell} for LIB cells and 3.5–7.9 kWh_{prod} per kWh_{cell} for analysed PLIB cells. Thus, in a mixed scenario in 2040 a total 44,600 GWh_{prod} (10,932 ktCO₂eq GHG emissions) will be necessary for global LIB and PLIB cell production,

instead of 130,000 GWh_{prod} (41,213 ktCO₂eq GHG emissions), which are necessary with today's production technology and know-how. By accelerating PLIB cell industrialization and market shares, a further decrease of 10,800 GWh_{prod} to 33,800 GWh_{prod} (8,191 ktCO₂eq GHG emissions) per year is possible. In addition, in 2031, the increase in energy consumption for global LIB and PLIB cell production might reach a peak of approximately 44,860 GWh_{prod} and might even decline afterwards, although the battery market will still be growing.

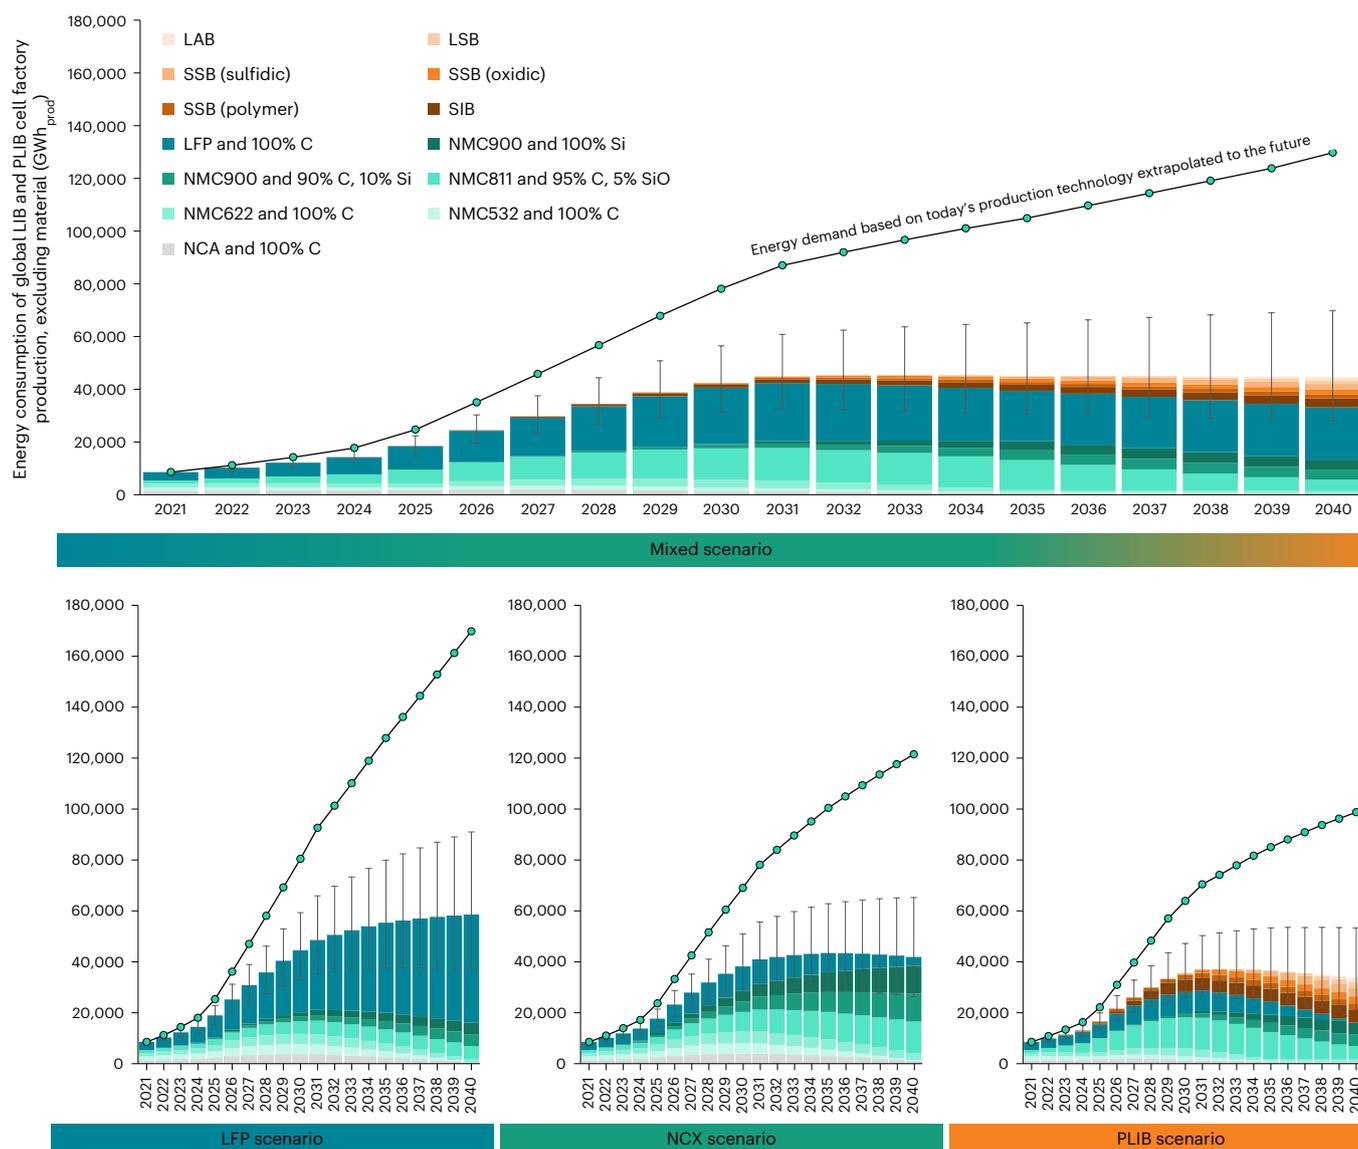


Fig. 7 | Energy consumption of global LIB and PLIB cell production. The figure shows the forecast once based on today's technology and know-how level, and once when considering technology improvements, heat pump use and learning effects, as well as economies of scale. This is done for a scenario in which market

shares are mixed (based on ref. 14) and for LFP, NCX and PLIB scenarios (based on Xu et al.⁴⁶). Detailed numbers can be found in Source Data Fig. 7. The main bars show the calculated mean value. The error bars show the s.d. resulting from the uncertainties in the expert assessments. Sixty experts were interviewed ($n = 60$).

These results lead to the following statements based on the analysed cell chemistries in this paper. First, the production infrastructure for SSB cells requires more energy, whereas less energy is required for LSB and LAB cells, both compared with LIB cells. Second, energy consumption for production, related to cell energy (kWh_{prod} per kWh_{cell}) is lower for PLIB cells than for LIB cells. Third, due to their low areal energy densities, LFP cells and SIB cells have the highest ratio of kWh_{prod} to kWh_{cell} among the types of cells that were analysed. This is notable since both cell types are discussed as sustainable alternatives to nickel-based LIB cells in particular due to their easier material availability^{23,24}. Fourth, owing to large investments in battery production infrastructure, research and development, the resulting technology improvements and techno-economic effects promise a reduction in energy consumption per produced cell energy by two-thirds until 2040, compared with the present technology and know-how level. Fifth, on a global level, the energy consumption in 2040 for battery cell production will be 130,000 GWh_{prod} , with today's technology and know-how

level, which is equal to the annual electric energy demand of Norway or Sweden (in 2021)³⁶. Sixth, it is possible to improve the production of battery cells so that, in 2040, 85,400 GWh_{prod} could be saved per year (-66%), which is the electric energy demand of Belgium or Finland (in 2021)³⁶. Seventh, by improving the areal energy density, for example, by accelerating the industrialization of PLIB cells and increasing its market shares, in 2040 an additional 10,800 GWh_{prod} for global battery cell production could be saved per year. Eighth, through the analysed improvements, it is likely that, in 2031, energy consumption for LIB and PLIB cell global will reach a peak and might even decline afterwards, despite the additional growth of the market.

The results discussed above lead to the following implications in terms of energy consumption in cell production. First, a high areal energy density of the specific cell chemistry is key for a low ratio of kWh_{prod} to kWh_{cell} , at least for production. This can be achieved by SSB cells but also by further developed LIB cells with their high nickel contents. Second, when it comes to energy consumption for production,

LFP and SIB cells might not be as sustainable as often advertised. LIB and SIB cells should be questioned as sustainable cells. Third, improvements in production-related technology matters substantially, not just for PLIB cells but also, or even especially, for LIB cells. Therefore, resources should be invested not only in cell development, but also in the development of production technology. Fourth, by a combination of the measures mentioned above, the increase in energy demand for global LIB and PLIB production can be reduced or even stopped. This is vital for a reduction of battery production related GHG emissions and to reduce global warming.

Besides production, material accounts for a high share of energy consumption in the life cycles of batteries³⁷. Because materials and their production were excluded from this study, and also their mining and refining is very energy consuming (50–70% of total energy consumption)^{38,39}, in future studies, it is very important to extend our research with values from material mining, the use phase, and the recycling of battery cells. This is highly recommended for LFP and SIB cell chemistries to validate how sustainable they are in terms of energy consumption. Furthermore, we recommend that LIB cell technology and its production be optimized. Both LIBs and PLIBs will have the opportunity to be relevant types of battery cells and will be vitally important for reducing energy consumption in 2040.

Methods

Energy consumption changes to produce PLIB cells

First, we analysed how electrical and natural gas power (P) of production machines will change, when producing PLIB parts instead of LIB parts at a constant material flow rate (Q). For this, an adjustment parameter λ_j is defined as

$$\lambda_j = \frac{\text{increase (+)}}{\text{decrease (-)}} \text{ change of machine power (\%)} + 1. \quad (1)$$

λ_j is obtained once for electrical power and once for natural gas power. To obtain λ_j , 60 battery cell experts evaluated in workshops the quantitative impact of the changed production infrastructure on required machine power. The workshops were conducted in two phases, with the experts split into two groups: first phase—calculating the relative changes in energy consumption from LIB to PLIB production only for the single defined production step/machine (expert group 1); second phase—reviewing and adapting the results from phase 1 in the context of all obtained results (expert group 2).

Each workshop in the first phase followed the same structure: first, investigating the energy consumption for today's LIB production; second, identifying the main energy consumers and thermomechanical effects that cause the largest energy consumption; third, identifying how requirements for the machine are changed when producing PLIB components instead of LIB components; fourth, identifying what technical changes in the machine are necessary to be able to process PLIB components; fifth, estimating what these changes to the machine mean in terms of energy consumption; sixth, estimating how reliable the assumptions are.

In the second phase workshops, the results were presented to the second group of experts, who had to review the previous, process-specific assumptions from expert group 1 in the context of all other results. The structure was as follows: first, giving an overview of the obtained results; second, explaining the calculations of expert group one; third, identifying similar production processes compared with the process that is in focus (reference process); fourth, comparing the calculations between the focus process and the reference process; fifth, questioning the estimations/calculations made by the expert group one; sixth, adapting the calculations from first phase if necessary; seventh, estimating how reliable the made calculations are.

A total of 60 experts were questioned, 30 in phase 1 and 30 in phase 2. Each workshop consisted of one to three experts. Each workshop

took approximately 1 h on average. In total, 26 workshops were conducted. Each expert was asked how reliable they think their made estimations are. The experts could choose between lower, medium, and higher reliability. They also were asked why they made their choice. The following risk factors, η_j , are defined: high reliability ($\eta_j = 0.1$), medium reliability ($\eta_j = 0.2$), low reliability ($\eta_j = 0.5$).

Energy consumption for today's production on cell level

For this study, an LIB factory model of Degen and Schütte was used, which provides energy consumption of each production machine as well as the machining parameter³¹. An extended version of the model was given by Degen and Krätzig³⁴. Following relevant parameters are used: The electrical power of production machine ($P_{j,\text{electric}}$), the natural gas power of production machine ($P_{j,\text{gas}}$), the produceable material flow rate ($Q_{j,\text{cell}}$) for each specific process step (j). By the data from the factory model, it is possible to calculate the energy consumption per material flow that is produced ($E_{j,\text{electric}}, E_{j,\text{gas}}$):

$$E_j = \frac{P_j}{Q_{j,\text{cell}}} \text{ in [kWh}_{\text{prod}} \text{ per m}_{\text{cell}}^2]. \quad (2)$$

This, in combination with the cell chemistry specific areal electrode stack energy content ($\text{kWh}_{\text{cell}} \text{ per m}_{\text{cell}}^2$), makes it possible to calculate the ratio of kWh_{prod} to kWh_{cell} ratio, $i_{j,\text{energy}}$, for each production step:

$$i_{j,\text{energy}} = \frac{(E_{j,\text{electric}} + E_{j,\text{gas}})}{\text{Areal energy content}} \text{ in [kWh}_{\text{prod}} \text{ per kWh}_{\text{cell}}]. \quad (3)$$

The overall i_{energy} , existing for each cell chemistry, is the sum of all production processes within the value chain:

$$i_{\text{energy}} = \sum_{i=\text{mixing}}^{\text{EOL testing}} i_{j,\text{energy}}. \quad (4)$$

Bottleneck of our used factory model is the assembly line with:

$$Q_{\text{assembly,cell}} = 840 \text{ m}^2 \text{ min}^{-1}. \quad (5)$$

This is equal to 200 cylindrical cells or 50 pouch cells per minute. Thus, all other production steps are adapted to this lead material flow rate, either by reducing the production speed or by not using the machine. A linear relationship is assumed between the required machine power and the produced material flow.

The power of the production machines for PLIB cell production is then calculated as follows:

$$P_j^{\text{PLIB}} = \lambda_j \times P_j^{\text{LIB}}. \quad (6)$$

$$P_j^{\text{PLIB}}(\text{max}) = \lambda_j \times P_j^{\text{LIB}} \times (1 + \eta_j). \quad (7)$$

$$P_j^{\text{PLIB}}(\text{min}) = \lambda_j \times P_j^{\text{LIB}} \times (1 - \eta_j). \quad (8)$$

Techno-economic effects on future's energy consumption

To calculate the energy consumption required to produce a single LIB and a single PLIB cell with $1 \text{ kWh}_{\text{cell}}$ of cell energy, in addition to the battery cell type, four techno-economic effects were addressed: technology improvements^{29,35,40–43}, use of heat pumps^{31,44}, learning effects^{35,43,45} and economies of scale^{43,46,47}. The made assumptions can be found in Supplementary Table 2.

Technology improvements. To estimate how technological developments may affect future energy consumption in cell production, first

the main energy consumers in cell production were analysed. These are coating and drying, dry rooms, formation, and sintering and tempering (of oxidic SSB cells). Then, the process experts gathered in workshops and discussed the existing alternative technologies, the new technologies that were in development, and which of the technologies might have notable impacts on the energy consumption of the LIB cells, and PLIB cell production. Afterwards, for each of the gathered technologies, it was estimated how electrical and natural gas power (P) of production machines will change when changing the production process. The material flow rate (Q) is kept constant. For this a technology adjustment parameter ε_j is defined, once for electric energy ($\varepsilon_{j,\text{electric}}$) and once for natural gas ($\varepsilon_{j,\text{gas}}$), which is calculated by

$$\varepsilon_j = \frac{\text{increase}(+)}{\text{decrease}(-)} \text{ change of machine power } (\%) + 1. \quad (9)$$

By that, the machine power can be calculated as follows:

$$P_j^{\text{new}} = \varepsilon_j \times P_j^{\text{reference}}. \quad (9)$$

By the new obtained P_j^{new} , it is possible to calculate E_j^{new} :

$$E_j^{\text{new}} = \frac{P_j^{\text{new}}}{Q_{j,\text{cell}}} \text{ in [kWh}_{\text{prod}} \text{ per m}^2_{\text{cell}}], \quad (10)$$

and then

$$E^{\text{new}} = \sum_{i=\text{mixing}}^{\text{EOL Etesting}} E_j^{\text{new}} \text{ in [kWh}_{\text{prod}} \text{ per m}^2_{\text{cell}}]. \quad (11)$$

Then the energy saving potential can be calculated as shown below:

$$s = \frac{E^{\text{new}}}{E^{\text{reference}}} - 1. \quad (12)$$

This is for the case that the reference technology is completely (100%) substituted by the new technology. According to the expert workshops, it might be unlikely that until 2040 all analysed technologies will be fully industrialized and have a market share of 100%. Thus, we assume this to be the maximum scenario (large effect). We assume lower market shares of 80% in a trend scenario (medium effect) and 60% in a minimum scenario (small effect).

The results that were obtained were compared afterwards with the results from the literature; in particular, the studies of von Drachenfels et al., Mauler et al. and Degen were used^{29,35,40}. The studies analysed the impact of technology improvements on cost²⁹ and on the energy consumption the production of battery cells^{35,40}. For example, an energy reduction of 2–3% per year was reported for an NMC622 cell with high power configuration (41 μm thickness of cathode active material)³⁵. Thus, our results are in the same range as the literature results.

Use of heat pumps. For improved energy sourcing, it is assumed that electricity is used instead of natural gas and that heat pumps are used for the generation of heat. For the calculations of the use of heat pumps, a coefficient of performance (COP) between 1.5 and 2.5 was used for temperatures above 100 °C (ref. 44). We assumed that 60% of the factories will be equipped with heat pumps in 2040.

Learning effects. Learning effects result from experience in production, such as reducing scrap rates and using machines and tools more efficiently. It is described by a percentual cost reduction by doubling the cumulated production output. According to the National Aeronautics and Space Administration, learning effects in the field of ‘repetitive electronics manufacturing’ are 5% for cost⁴⁵. We assumed a reduction

of energy consumption of 3–5% by doubling the cumulative production output³⁵.

Economies of scale. By economies of scale, the effect is described that the effort (cost) to produce a product is reduced with increased scale in its production. This is achieved by synergy effects and by fixed cost depression. The effect of economies of scale does not affect only the economic cost, but it also affects other costs, for example energy consumption⁴⁶. It is described by a percentual cost reduction by doubling the annual production output⁴³. Here a reduction of energy between 3% and 5% was assumed when doubling the annual production output^{35,48}.

Energy consumption for future’s production on cell level

For each year y , between 2021 until 2040, a reduction factor f is calculated for percentual savings per year due to new technologies ($f_{\text{technology},y}$), for percentual savings per year due to higher market share of heat pump use ($f_{\text{heatpump},y}$), for percentual savings per year due to increase of cumulative production ($f_{\text{learning},y}$) and for percentual savings per year due to increase of annual production ($f_{\text{scale},y}$). By this for each year y , a percentual saving f_{sum} can be calculated as

$$f_{\text{sum},y} = 1 - (1 - f_{\text{technology},y}) \times (1 - f_{\text{heatpump},y}) \times (1 - f_{\text{learning},y}) \times (1 - f_{\text{scale},y}). \quad (13)$$

Then i_{energy} can be calculated for each future year, y (here for 2040) as

$$i_{\text{energy},2040} = i_{\text{energy}} \times (1 - f_{\text{sum},2021}) \times (1 - f_{\text{sum},2022}) \dots (1 - f_{\text{sum},2040}). \quad (14)$$

Energy consumption on macro-economic level

For the calculation, the following parameters are defined: the total market demand (D , in GWh_{cell}), the cell-specific market demand (D_k , in GWh_{cell}), the cell-specific market share (S_k , in %), the total energy demand of production to meet the market demand (ED, in GWh_{prod}) and the cell-specific energy demand of production to meet the market demand (ED_k , in GWh_{prod}).

The cell-specific market demand is calculated as follows:

$$D_k = D \times S_k. \quad (15)$$

The energy demand of production to meet the cell-specific market demand is calculated as followed (for electricity, natural gas and both):

$$\text{ED}_k = D_k \times i_{k,\text{energy}}. \quad (16)$$

The energy demand of production to meet the total market demand is calculated as follows:

$$\text{ED} = \sum_{k=\text{NCA}}^{\text{LAB}} \text{ED}_k. \quad (17)$$

This was calculated for all years from 2021 to 2040 (note that D , S_k and $i_{k,\text{energy}}$ are different for each year).

We also calculated the GHG emissions resulting from global LIB and PLIB cell production, from 2021 until 2040. The results are shown in Supplementary Figs. 4 and 5. For the calculation, the following parameters are defined: the GHG emissions caused by ED (GD, in ktCO_2eq), the GHG emissions caused by ED_k (GD_k , in ktCO_2eq), the GHG emissions per electric energy ($m_{\text{electricity}}$, in $\text{kgCO}_2\text{eq per kWh}_{\text{prod}}$) and the GHG emissions per natural gas energy (m_{gas} , in $\text{kgCO}_2\text{eq per kWh}_{\text{prod}}$). The calculation of ED_k is as follows:

$$\text{GD}_k = m_{\text{electricity}} \times \text{ED}_k^{\text{electricity}} + m_{\text{gas}} \times \text{ED}_k^{\text{gas}}. \quad (18)$$

The calculation of ED is as follows:

$$ED = \sum_{k=NCA}^{LAB} ED_k. \quad (19)$$

This was calculated for all years from 2021 to 2040. We used $m_{\text{electricity}}(2021) = 0.459 \text{ kgCO}_2\text{eq per kWh}_{\text{prod}}$ (ref. 49), $m_{\text{electricity}}(2050) = 0.160 \text{ kgCO}_2\text{eq per kWh}_{\text{prod}}$ (ref. 49) and $m_{\text{gas}} = 0.2 \text{ kgCO}_2\text{eq per kWh}_{\text{prod}}$. $m_{\text{electricity}}$ is linearly interpolated between 2021 and 2050.

System boundaries and further made assumptions

This analysis was a gate-to-gate analysis. The material was excluded, and only the energy consumption of a battery cell factory was considered. It is assumed for PLIB and new LIB cells that the technical challenges in cell chemistry, cell design and production technology will be overcome and that production will take place on an industrial scale without scrap rates. Economical costs were not considered in this study.

Reporting summary

Further information on research design is available in the Nature Portfolio Reporting Summary linked to this article.

Data availability

The dataset generated during the current study is available within the article, its supplementary information and source data files. Source data are provided with this paper.

References

- Jenu, S. et al. Reducing the climate change impacts of lithium-ion batteries by their cautious management through integration of stress factors and life cycle assessment. *J. Energy Storage* **27**, 101023 (2020).
- 2030 climate and energy framework. *European Commission* https://ec.europa.eu/clima/policies/strategies/2030_en (2021).
- 2050 long-term strategy. *European Commission* https://ec.europa.eu/clima/policies/strategies/2050_en (2021).
- Sommerville, R. et al. A qualitative assessment of lithium ion battery recycling processes. *Resour. Conserv. Recycl.* **165**, 105219 (2021).
- GM plans to phase out gas and diesel cars by 2035. *Forbes* <https://www.forbes.com/wheels/news/gm-phase-out-gas-diesel-cars-2035/> (2021).
- VW to end sales of combustion engines in Europe by 2035. *Reuters* <https://www.reuters.com/business/sustainable-business/vw-end-sales-combustion-engines-europe-by-2035-2021-06-26/> (2021).
- A Vision for a Sustainable Battery Value Chain in 2030. Unlocking the Full Potential to Power Sustainable Development and Climate Change Mitigation* (World Economic Forum, 2019).
- B3 (LIB Materials Market Bulletin, 2021).
- Global Li-Ion Battery Materials Market, Forecast to 2026* (Frost & Sullivan, 2020).
- Marscheider-Weidemann, F. et al. Raw materials for emerging technologies 2021. *Deutsche Rohstoffagentur* https://www.deutsche-rohstoffagentur.de/DE/Gemeinsames/Produkte/Downloads/DERA_Rohstoffinformationen/rohstoffinformationen-50-en.pdf?__blob=publicationFile&v=2 (2021).
- Lithium-Ion Batteries, Outlook to 2030* (Roskill, 2021).
- Schmaltz, T. et al. Solid-state battery roadmap 2035+. *Fraunhofer* https://www.isi.fraunhofer.de/content/dam/isi/dokumente/cct/2022/SSB_Roadmap.pdf (2022).
- 2019–2020: Current Status and Future Prospects of LiB Material Market, Major Four Components* (Yano Research Institute, 2020).
- Bhandari, N. B. et al. Batteries: the greenflation challenge. *Goldman Sachs* <https://www.goldmansachs.com/insights/pages/gs-research/batteries-the-greenflation-challenge/report.pdf> (2022).
- Riahi, K. et al. The Shared Socioeconomic Pathways and their energy, land use, and greenhouse gas emissions implications: an overview. *Global Environ. Change* **42**, 153–168 (2017).
- Xu, C. et al. Future material demand for automotive lithium-based batteries. *Commun. Mater.* **1**, 99 (2020).
- Betz, J. et al. Theoretical versus practical energy: a plea for more transparency in the energy calculation of different rechargeable battery systems. *Adv. Energy Mater.* **9**, 1803170 (2019).
- Duffner, F. et al. Post-lithium-ion battery cell production and its compatibility with lithium-ion cell production infrastructure. *Nat. Energy* **6**, 123–134 (2021).
- Greenwood, M., Wentker, M. & Leker, J. A region-specific raw material and lithium-ion battery criticality methodology with an assessment of NMC cathode technology. *Appl. Energy* **302**, 117512 (2021).
- Wang, X., Ding, Y.-L., Deng, Y.-P. & Chen, Z. Ni-Rich/Co-poor layered cathode for automotive Li-ion batteries: promises and challenges. *Adv. Energy Mater.* **10**, 1903864 (2020).
- Eshetu, G. G. et al. Production of high-energy Li-ion batteries comprising silicon-containing anodes and insertion-type cathodes. *Nat. Commun.* **12**, 5459 (2021).
- Sick, N., Krätzig, O., Eshetu, G. G. & Figgemeier, E. A review of the publication and patent landscape of anode materials for lithium ion batteries. *J. Energy Storage* **43**, 103231 (2021).
- Fichtner, M. Recent research and progress in batteries for electric vehicles. *Batter. Supercaps* **5**, e202100224 (2022).
- Gucciardi, E., Galceran, M., Bustinza, A., Bekaert, E. & Casas-Cabanias, M. Sustainable paths to a circular economy: reusing aged Li-ion FePO₄ cathodes within Na-ion cells. *J. Phys. Mater.* **4**, 34002 (2021).
- Liang, Y., Dong, H., Aurbach, D. & Yao, Y. Current status and future directions of multivalent metal-ion batteries. *Nat. Energy* **5**, 646–656 (2020).
- Bhandari, N. B. et al. Batteries: the greenflation challenge II. *Goldman Sachs* <https://www.goldmansachs.com/insights/pages/gs-research/batteries-the-greenflation-challenge-2/report.pdf> (2022).
- Kim, T., Song, W., Son, D.-Y., Ono, L. K. & Qi, Y. Lithium-ion batteries: outlook on present, future, and hybridized technologies. *J. Mater. Chem. A* **7**, 2942–2964 (2019).
- CATL unveils its latest breakthrough technology by releasing its first generation of sodium-ion batteries. *Contemporary Amperex Technology Co.* <https://www.catl.com/en/news/665.html> (2021).
- Mauler, L., Duffner, F., Zeier, W. G. & Leker, J. Battery cost forecasting: a review of methods and results with an outlook to 2050. *Energy Environ. Sci.* **14**, 4712–4739 (2021).
- Ma, J. et al. The 2021 battery technology roadmap. *J. Phys. D* **54**, 183001 (2021).
- Degen, F. & Schütte, M. Life cycle assessment of the energy consumption and GHG emissions of state-of-the-art automotive battery cell production. *J. Clean. Prod.* **330**, 129798 (2022).
- Jinasena, A., Burheim, O. S. & Strømman, A. H. A flexible model for benchmarking the energy usage of automotive lithium-ion battery cell manufacturing. *Batteries* **7**, 14 (2021).
- Kallitsis, E. On the energy use of battery Gigafactories. *J. Clean. Prod.* **364**, 132573 (2022).
- Degen, F. & Krätzig, O. Modeling large-scale manufacturing of lithium-ion battery cells: impact of new technologies on production economics. *IEEE Trans. Eng. Manage.* <https://doi.org/10.1109/TEM.2023.3264294> (2023).
- Degen, F. Lithium-ion battery cell production in Europe: scenarios for reducing energy consumption and greenhouse gas emissions until 2030. *J. Ind. Ecol.* **27**, 964–976 (2023).

36. Electricity net consumption (billion kWh). *US Energy Information Administration* <https://www.eia.gov/international/data/world> (2023).
37. Lai, X. et al. Critical review of life cycle assessment of lithium-ion batteries for electric vehicles: a lifespan perspective. *eTransportation* **12**, 100169 (2022).
38. Romare, M. & Dahllöf, L. *The Life Cycle Energy Consumption and Greenhouse Gas Emissions from Lithium-Ion Batteries. A Study with Focus on Current Technology and Batteries for Light-Duty Vehicles* (IVL Swedish Environmental Research Institute Ltd., 2017); <https://www.energimyndigheten.se/globalassets/forskning--innovation/transporter/c243-the-life-cycle-energy-consumption-and-co2-emissions-from-lithium-ion-batteries-.pdf>
39. Whattoff, P. et al. *Shifting the Lens: the Growing Importance of Life Cycle Impact Data in the Battery Material Supply Chain* (Minviro Ltd, 2021); <https://www.minviro.com/wp-content/uploads/2021/10/Shifting-the-lens.pdf>
40. Drachenfels, N. von, Husmann, J., Khalid, U., Cerdas, F. & Herrmann, C. Life cycle assessment of the battery cell production: using a modular material and energy flow model to assess product and process innovations. *Energy Tech.* **11**, 2200673 (2022).
41. Michaelis, S. & Rahimzei, E. *Roadmap Batterieproduktionsmittel 2030. Update 2020* (VDMA, 2020).
42. Degen, F. & Kratzig, O. Future in battery production: an extensive benchmarking of novel production technologies as guidance for decision making in engineering. *IEEE Trans. Eng. Manag.* <https://doi.org/10.1109/TEM.2022.3144882> (2022).
43. Few, S. et al. Prospective improvements in cost and cycle life of off-grid lithium-ion battery packs: an analysis informed by expert elicitations. *Energy Policy* **114**, 578–590 (2018).
44. Arpagaus, C., Bless, F., Uhlmann, M., Schiffmann, J. & Bertsch, S. S. High temperature heat pumps: market overview, state of the art, research status, refrigerants, and application potentials. *Energy* **152**, 985–1010 (2018).
45. Stewart, R. D., Wyskida, R. M. & Johannes, J. D. *Cost Estimator's Reference Manual* 2nd edn (Wiley, 1995).
46. O'Sullivan, A., Cooper, K. H. & Sheffrin, S. M. *Economics: Principles in Action* (Pearson Prentice Hall, 2002).
47. Schlich, E. & Fleissner, U. The ecology of scale: assessment of regional energy turnover and comparison with global food (5 pp). *Int. J. Life Cycle Assess* **10**, 219–223 (2005).
48. Mauler, L., Duffner, F. & Leker, J. Economies of scale in battery cell manufacturing: the impact of material and process innovations. *Appl. Energy* **286**, 116499 (2021).
49. *World Energy Outlook 2022* (International Energy Agency, 2022).

Acknowledgements

This research was funded by the German Federal Ministry of Education and Research (grant no. 03XP0256). We thank all experts who participated in the assessment.

Author contributions

F.D. conceived the idea for the manuscript and designed the study. F.D. and D.B. have designed the methodical procedure together. F.D., J.T. and M.W. collected and reviewed the data. F.D. analysed the quantitative and qualitative data. F.D. wrote and revised the article. M.W., D.B. and J.T. edited the manuscript and provided comments on the manuscript.

Funding

Open access funding provided by Fraunhofer-Gesellschaft zur Förderung der angewandten Forschung e.V.

Competing interests

The authors declare no competing interests.

Additional information

Supplementary information The online version contains supplementary material available at <https://doi.org/10.1038/s41560-023-01355-z>.

Correspondence and requests for materials should be addressed to F. Degen.

Peer review information *Nature Energy* thanks Evangelos Kallitsis, Chris Yuan and the other, anonymous, reviewer(s) for their contribution to the peer review of this work.

Reprints and permissions information is available at www.nature.com/reprints.

Publisher's note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2023

Reporting Summary

Nature Portfolio wishes to improve the reproducibility of the work that we publish. This form provides structure for consistency and transparency in reporting. For further information on Nature Portfolio policies, see our [Editorial Policies](#) and the [Editorial Policy Checklist](#).

Statistics

For all statistical analyses, confirm that the following items are present in the figure legend, table legend, main text, or Methods section.

- | n/a | Confirmed |
|-------------------------------------|---|
| <input type="checkbox"/> | <input checked="" type="checkbox"/> The exact sample size (n) for each experimental group/condition, given as a discrete number and unit of measurement |
| <input type="checkbox"/> | <input checked="" type="checkbox"/> A statement on whether measurements were taken from distinct samples or whether the same sample was measured repeatedly |
| <input checked="" type="checkbox"/> | <input type="checkbox"/> The statistical test(s) used AND whether they are one- or two-sided
<i>Only common tests should be described solely by name; describe more complex techniques in the Methods section.</i> |
| <input checked="" type="checkbox"/> | <input type="checkbox"/> A description of all covariates tested |
| <input checked="" type="checkbox"/> | <input type="checkbox"/> A description of any assumptions or corrections, such as tests of normality and adjustment for multiple comparisons |
| <input checked="" type="checkbox"/> | <input type="checkbox"/> A full description of the statistical parameters including central tendency (e.g. means) or other basic estimates (e.g. regression coefficient) AND variation (e.g. standard deviation) or associated estimates of uncertainty (e.g. confidence intervals) |
| <input checked="" type="checkbox"/> | <input type="checkbox"/> For null hypothesis testing, the test statistic (e.g. F , t , r) with confidence intervals, effect sizes, degrees of freedom and P value noted
<i>Give P values as exact values whenever suitable.</i> |
| <input checked="" type="checkbox"/> | <input type="checkbox"/> For Bayesian analysis, information on the choice of priors and Markov chain Monte Carlo settings |
| <input checked="" type="checkbox"/> | <input type="checkbox"/> For hierarchical and complex designs, identification of the appropriate level for tests and full reporting of outcomes |
| <input checked="" type="checkbox"/> | <input type="checkbox"/> Estimates of effect sizes (e.g. Cohen's d , Pearson's r), indicating how they were calculated |

Our web collection on [statistics for biologists](#) contains articles on many of the points above.

Software and code

Policy information about [availability of computer code](#)

Data collection

Data analysis

For manuscripts utilizing custom algorithms or software that are central to the research but not yet described in published literature, software must be made available to editors and reviewers. We strongly encourage code deposition in a community repository (e.g. GitHub). See the Nature Portfolio [guidelines for submitting code & software](#) for further information.

Data

Policy information about [availability of data](#)

All manuscripts must include a [data availability statement](#). This statement should provide the following information, where applicable:

- Accession codes, unique identifiers, or web links for publicly available datasets
- A description of any restrictions on data availability
- For clinical datasets or third party data, please ensure that the statement adheres to our [policy](#)

Research involving human participants, their data, or biological material

Policy information about studies with [human participants or human data](#). See also policy information about [sex, gender \(identity/presentation\), and sexual orientation](#) and [race, ethnicity and racism](#).

Reporting on sex and gender	<input type="text" value="n/a"/>
Reporting on race, ethnicity, or other socially relevant groupings	<input type="text" value="n/a"/>
Population characteristics	<input type="text" value="n/a"/>
Recruitment	<input type="text" value="n/a"/>
Ethics oversight	<input type="text" value="n/a"/>

Note that full information on the approval of the study protocol must also be provided in the manuscript.

Field-specific reporting

Please select the one below that is the best fit for your research. If you are not sure, read the appropriate sections before making your selection.

Life sciences Behavioural & social sciences Ecological, evolutionary & environmental sciences

For a reference copy of the document with all sections, see [nature.com/documents/nr-reporting-summary-flat.pdf](https://www.nature.com/documents/nr-reporting-summary-flat.pdf)

Life sciences study design

All studies must disclose on these points even when the disclosure is negative.

Sample size	<input type="text" value="n/a"/>
Data exclusions	<input type="text" value="n/a"/>
Replication	<input type="text" value="n/a"/>
Randomization	<input type="text" value="n/a"/>
Blinding	<input type="text" value="n/a"/>

Behavioural & social sciences study design

All studies must disclose on these points even when the disclosure is negative.

Study description	<input type="text" value="n/a"/>
Research sample	<input type="text" value="n/a"/>
Sampling strategy	<input type="text" value="n/a"/>
Data collection	<input type="text" value="n/a"/>
Timing	<input type="text" value="n/a"/>
Data exclusions	<input type="text" value="n/a"/>
Non-participation	<input type="text" value="n/a"/>
Randomization	<input type="text" value="n/a"/>

Ecological, evolutionary & environmental sciences study design

All studies must disclose on these points even when the disclosure is negative.

Study description	<input type="text" value="n/a"/>
Research sample	<input type="text" value="n/a"/>
Sampling strategy	<input type="text" value="n/a"/>
Data collection	<input type="text" value="n/a"/>
Timing and spatial scale	<input type="text" value="n/a"/>
Data exclusions	<input type="text" value="n/a"/>
Reproducibility	<input type="text" value="n/a"/>
Randomization	<input type="text" value="n/a"/>
Blinding	<input type="text" value="n/a"/>

Did the study involve field work? Yes No

Reporting for specific materials, systems and methods

We require information from authors about some types of materials, experimental systems and methods used in many studies. Here, indicate whether each material, system or method listed is relevant to your study. If you are not sure if a list item applies to your research, read the appropriate section before selecting a response.

Materials & experimental systems

n/a	Involvement in the study
<input checked="" type="checkbox"/>	<input type="checkbox"/> Antibodies
<input checked="" type="checkbox"/>	<input type="checkbox"/> Eukaryotic cell lines
<input checked="" type="checkbox"/>	<input type="checkbox"/> Palaeontology and archaeology
<input checked="" type="checkbox"/>	<input type="checkbox"/> Animals and other organisms
<input checked="" type="checkbox"/>	<input type="checkbox"/> Clinical data
<input checked="" type="checkbox"/>	<input type="checkbox"/> Dual use research of concern
<input checked="" type="checkbox"/>	<input type="checkbox"/> Plants

Methods

n/a	Involvement in the study
<input checked="" type="checkbox"/>	<input type="checkbox"/> ChIP-seq
<input checked="" type="checkbox"/>	<input type="checkbox"/> Flow cytometry
<input checked="" type="checkbox"/>	<input type="checkbox"/> MRI-based neuroimaging