

IUPAC Technical Report

Roger C. Hiorns*, Jiří Vohlídal*, Ray Boucher, Chin H. Chan, Christopher M. Fellows, Michael Hess, Richard G. Jones, Pavel Kratochvíl, Christine K. Luscombe, John B. Matson, Graeme Moad, Olga E. Philippova, Stan Slomkowski, Natalie Stingelin, Patrick Théato, Jean-Pierre Vairon and Michel Vert

A brief guide to polymer terminology (IUPAC Technical Report)

<https://doi.org/10.1515/pac-2023-0304>

Received March 27, 2023; accepted September 19, 2025

Abstract: The correct use of IUPAC terminology can facilitate clarity in scientific publications, litigation, and education. This document summarizes IUPAC's recommendations for polymer terminology. In the version attached in the Supplementary Information, hyperlinks lead to the original source material, and screen-tips give the definitions as published by IUPAC.

Keywords: IUPAC polymer division; polymer chemistry.

CONTENTS

1	Introduction	xxx
2	Macromolecules and polymers	xxx
3	Configuration and stereoisomerism	xxx
4	Polymerizations	xxx

Deceased: Chin H. Chan, Richard G. Jones, Pavel Kratochvíl.

***Corresponding authors:** Roger C. Hiorns, CNRS/Univ Pau & Pays Adour, Institut des Science Analytiques et Physico-Chimie pour l'Environnement et les Matériaux, UMR5254, 64000, Pau, France, e-mail: roger-clive.hiorns@cnrs.fr. <https://orcid.org/0000-0002-9887-5280> (R.C. Hiorns); and Jiří Vohlídal, Faculty of Sciences, Department of Physical and Macromolecular Chemistry, Charles University, Albertov 2030, 128 40 Prague 2, Czech Republic, e-mail: vohlidal@natur.cuni.cz

Ray Boucher, John Wiley & Sons Ltd, The Atrium, Southern Gate, Chichester PO19 8SQ, UK

Chin H. Chan, Faculty of Applied Sciences, Universiti Teknologi MARA, 40450 Shah Alam Selangor, Malaysia. <https://orcid.org/0000-0003-0990-0155>

Christopher M. Fellows, School of Science and Technology, University of New England, Armidale, NSW 2351, Australia

Michael Hess, Department of Physics, University of North Texas, Denton, TX, USA

Richard G. Jones, Functional Materials Group, School of Physical Sciences, University of Kent, Canterbury, CT2 7NH, UK

Pavel Kratochvíl, Institute of Macromolecular Chemistry Academy of Sciences of the Czech Republic, Heyrovského náměstí 2, CZ 162 06 Praha 6, Czech Republic

Christine K. Luscombe, pi-Conjugated Polymers Unit, Okinawa Institute of Science and Technology Graduate University, 904-0495 Okinawa, Japan. <https://orcid.org/0000-0001-7456-1343>

John B. Matson, Department of Chemistry, Virginia Tech Center for Drug Discovery, and Macromolecules Innovation Institute, Virginia Tech, Blacksburg, VA, USA. <https://orcid.org/0000-0001-7984-5396>

Graeme Moad, CSIRO Materials Science and Engineering, Bag 10, Clayton South, VIC 3169, Australia. <https://orcid.org/0000-0002-4375-5580>

Olga E. Philippova, Faculty of Physics, M. V. Lomonosov, Moscow State University, GSP-1, 1-2 Leninskie Gory, Moscow 119991, Russia

Stan Slomkowski, Centre of Molecular and Macromolecular Studies Polish Academy of Sciences, Sienkiewicza 112, 90-363 Łódź, Poland

Natalie Stingelin, Department of Materials and Centre of Plastic Electronics (CPE), Imperial College, Exhibition Road, London SW7 2AZ, UK

Patrick Théato, Institute for Chemical Technology and Polymer Chemistry, Karlsruhe Institute of Technology, Bldg. 11.23 Engesserstr. 18/20 76131 Karlsruhe, Germany

Jean-Pierre Vairon, Comité National de la Chimie Sorbonne Université – Faculté des Sciences et Ingénierie UMR 8232 – IPCM, Chimie des Polymères T43-53, 4eme étage, Mailbox 185, 4 place Jussieu, 75252 Paris Cedex 05, France

Michel Vert, University Montpellier-CNRS, Montpellier, France. <https://orcid.org/0000-0002-5751-2520>

5	Polymer modifications and degradations	XXX
6	Macromolecules in solutions, assemblies, and bulks	XXX
7	Crystalline <i>versus</i> amorphous polymers	XXX
8	Thermal and thermomechanical properties	XXX
9	Functional polymers	XXX
10	Biorelated polymers	XXX
	Membership of sponsoring bodies	XXX
	References	XXX

1 Introduction

The International Union of Pure and Applied Chemistry (IUPAC) publishes definitions of terms to enable communication of information worldwide. Definitions of terms commonly used in polymer chemistry are paraphrased here with hyperlinks and screen-tips to approved definitions in the Gold and Purple Books, or the original source documents. This document complements the Brief Guides to Polymer Nomenclature,¹ Polymerization Terminology,² and Polymer Characterization.³

2 Macromolecules and polymers^{4,5}

The terms macromolecule and polymer do not mean the same thing. A polymer is a substance composed of macromolecules of high molar mass (M). An oligomer molecule is of intermediate molar mass such that a change in the number of units will noticeably alter its properties. The degree of polymerization (X) indicates the number of monomeric units making up a macromolecule. Each sample normally contains a range of chain lengths. Dispersity ($\mathcal{D}$) quantifies the breadth of this distribution and is defined by $\mathcal{D} = M_w/M_n$.⁶ The number-average molar mass (M_n) and mass-average molar mass (M_m or M_w) (unit g mol^{-1}), can be calculated using the equations, respectively:

$$M_n = \frac{1}{\sum_M (w_M/M)} \text{ and } M_m \equiv M_w = \sum_M w_M M$$

in which w_M is the mass fraction of molar mass M .

A constitutional unit (CU) consists of one or more atoms and makes up an essential part of a macromolecular structure. A monomeric unit is the largest CU that can be identified as coming from a monomer molecule. Importantly, constitutional repeating units (CRUs) are the smallest CUs that can be used to identify the structure of the whole chain. A regular macromolecule can be described by a single CRU joined in the same way throughout, whereas an irregular macromolecule comprises more than one CU or a non-uniformly connected CU. Macromolecules can also be described using machine-readable IUPAC International Chemical Identifiers.

Polymers are classified by their macromolecular skeletal structure, i.e., the sequence of atoms that defines their essential topological representation, as shown in Fig. 1. Those with CUs joined by two atoms are single-strand, and those with connected rings such as ladder and spiro macromolecules are double-strand. A block macromolecule is composed of linear sequences of blocks joined at a junction unit. A star macromolecule has at



Fig. 1: Classes of macromolecular structures. Left to right: single-strand, ladder, spiro, block, star, graft, and comb macromolecules; a network and a macrocycle. Image: H. C. Piva.

least three chains at the junction unit. The graft macromolecule has one or more side-chains connected to a main chain, with different structural features from the main chain. However, a comb macromolecule typically has a higher density of side chains which do not need to be different from the main chain. A network polymer is highly interconnected, bonding each CU with many others. A macrocycle can be a cyclic macromolecule or just a cyclic part of a structure. Other structures include the branched polymer which has branch points. This structure is noticeably different from the dendritic macromolecule which is tree-like and carries one or more dendrons.⁷ A related class is that of macromonomer which has an end-group allowing it to act as a monomer.

A homopolymer is made from one real or apparent monomer, whereas a copolymer contains two or more. The monomeric units in statistical and random copolymers, respectively, are distributed following statistical laws or placed independently from the nature of the adjacent units. A periodic copolymer has more than two monomeric units in a regular sequence, while an alternating copolymer has only two units in strict alternation.

An ionic polymer is made of macromolecules containing ionic or ionizable groups.⁸ An ionomer and a polyelectrolyte are composed of macromolecules, respectively, with a small or a substantial number of CUs carrying ionic or ionizable groups or both. An ampholytic polymer contains both anionic and cationic groups, or corresponding ionizable groups. A zwitterionic polymer contains ionic groups of opposite signs, often on the same pendant group.

3 Configuration and stereoisomerism^{9–11}

Isomers have the same atomic composition but different line or stereochemical formulae. An isomerization is a reaction that yields a product that is isomeric to the reactant. Configuration is a spatial arrangement of atoms or groups about a stereoisomeric center. This can be a chiral center, a rigid group, or a cyclic moiety, as exemplified in Fig. 2. Rigid centers are described using the preferred stereodescriptors *Z* and *E*, respectively, denoting the lesser preferred terms, *cis* and *trans*. Asymmetric carbons are described using *R* and *S* in accordance with Cahn–Ingold–Prelog (CIP) priority rules. Diastereoisomers are stereoisomers that are not mirror images.

A CU having one or more stereoisomeric sites is termed a configurational unit, whereas a CRU with at least one stereoisomer is called a configurational base unit (CBU). The smallest series of CBUs that describe a configurational repetition of stereoisomerism in the main chain is a configurational repeating unit (CFRU). A CRU having stereoisomeric configurations at all main chain sites is a stereorepeating unit (SRU). The tacticity of a polymer defines the orderliness of CFRUs in the main chain (see Fig. 3). A tactic macromolecule has identical CFRUs, while isotactic and syndiotactic macromolecules have CBUs with chiral atoms in the main chain uniquely or alternately arranged with respect to their adjacent CUs, respectively. An atactic macromolecule has CBUs in a random sequence. A diad comprises two stereoisomeric centers next to each other. When they are the same, *m* is used as a descriptor, and when they are different *r* is used.¹² Thus, syndiotactic chains have only *r* diads, isotactic chains are all *m* diads, while atactic chains have both *m* and *r* diads in a random sequence.

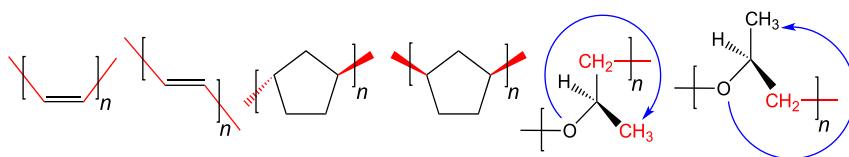


Fig. 2: Example stereodescriptors (left to right): poly[(*Z*)-ethene-1,2-diyl] and poly[(*E*)-ethene-1,2-diyl]; poly[(*Z*)-cyclopentane-1,3-diyl] and poly[(*E*)-cyclopentane-1,3-diyl]; and poly[(*R*)-oxy(1-methylethane-1,2-diyl)] and poly[(*S*)-oxy(1-methylethane-1,2-diyl)].



Fig. 3: The position of CBUs in stereoisomeric polymers.

Table 1: Four major classes of polymerization with example reactions.

Growth mechanism	Propagation stoichiometry	
	Condensation reaction	Addition reaction
Monomers (M) react with reactive sites on polymer chains (PA*)	Condensative chain polymerization $P_nA^* + M \rightarrow P_{n+1}A^* + X$	Chain polymerization $P_nA^* + M \rightarrow P_{n+1}A^*$
Monomers, oligomers and polymers react together	Polycondensation $*AP_nA^* + *BP_mB^* \rightarrow *AP_{n+m}B^* + X$	Polyaddition $*AP_nA^* + *BP_mB^* \rightarrow *AP_{n+m}B^*$

4 Polymerizations^{13–15}

A polymerization converts monomers into a polymer, whereas a depolymerization reverses this process. Unzipping occurs sequentially along the chain. A copolymerization converts two or more monomers to alternating, random, periodic, or statistical copolymers. Four types of polymerization are shown in Table 1. In chain polymerizations, reactive sites are regenerated after each propagation step. The term living polymerization is specific to reactions where irreversible deactivation by termination or chain transfer do not happen. If chains are deactivated reversibly, the polymerization is a reversible-deactivation polymerization. A controlled polymerization indicates control of a kinetic feature of the reaction or a structural aspect of the resulting polymer. Polyadditions and polycondensations involve reactions of monomer, oligomer, and polymer molecules of all sizes, with the latter class of reaction eliminating small molecules.

The rate of polymerization is a measure of the consumption of monomers or of a functional group in chain polymerizations and of functional groups in polyadditions and polycondensations. Radical, anionic, and cationic polymerizations, respectively, have a radical, an anion, or a cation as an active center. A ring-opening polymerization of a cyclic monomer yields a polymer that is acyclic or has fewer cycles. Conversely, a cyclopolymerization raises the number of cycles in the polymer with respect to the monomer molecule.

Polymerizations can also be classified as homogeneous, for example bulk or solution, and heterogenous, such as dispersion, precipitation, suspension, emulsion, or solid-state.^{12,16}

5 Polymer modifications and degradations^{17,18}

Chemical modification is a process by which a polymer's chemical constitution is changed. Examples of this include crosslinking between macromolecules which results in sites with at least four emanating chains, and amplification, where species that catalyze further reactions are generated. At surfaces, covalent bonds can be generated through surface grafting, while a polymer-supported reaction can occur *via* a range of polymer interactions.

Degradation results in the loss of desirable properties, while biodegradation arises from enzymatic processes.¹⁹ Aging processes, such as photo-oxidative aging, occur over a specific period of time, and can give rise to, for example, abrasion, cracking, and crazing. The durability of a polymer describes its ability to retain its initial properties. The use of an inhibitor stops a chemical reaction, while a retarder can decrease the rate.

6 Macromolecules in solutions, assemblies, and bulks^{20,21}

A freely rotating chain is unhindered by a short- or long-range intramolecular interaction. Chain stiffness describes an unperturbed distance from end-to-end with respect to a model chain and can be measured as a persistence length. In solution, a domain is the smallest volume containing a macromolecule in its average shape. A dilute solution of a polymer occurs when the total volume of occupied domains is much less than that of the

solution. In contrast, a concentrated solution exists when the occupied domains overlap. When a solution is in a theta state, the polymer is an unperturbed random coil. Precipitation fractionation employs the changing solution power of a solvent to separate macromolecular species. Alternatively, the method of size-exclusion chromatography can be used to differentiate between macromolecules by their hydrodynamic size.

Miscibility is the capability of a mixture to form a single phase over certain ranges of temperature, pressure, and composition. The lower and upper critical solution temperatures are, respectively, the points at which any composition of a mixture are immiscible or miscible. The reptation of chains in solutions or in the bulk is described using a model of a hypothetical tube created by neighboring chains.

A blend is a macroscopically homogeneous mixture, whereas a composite has phase domains of which at least one is continuous. A laminate consists of more than one layer and separates by delamination. Impregnation is a process of penetration of liquids into assembled fibers, and intercalation is where a substance is transferred into pre-existing spaces of molecular dimensions. Adhesion holds two bodies together by mechanical interlocking at sub- μm scales, while interfacial adhesion works through intermolecular forces or chain entanglement.

A colloid exists in a state of dispersion of polymolecular particles of the order of 1 nm to 1 μm in scale.²² A sol is a fluid colloidal system with two or more components, a gel is a network of connected macromolecular segments swollen by a liquid, and a xerogel is an open network cleared of a swelling agent. A hybrid polymer consists of inorganic and organic components.

In solids, domains are uniform in their chemical composition and physical states, and can be continuous, discontinuous, or show dual phase domain continuity. Numerous definitions exist to describe their morphology such as core-shell, cylindrical, fibrillar, lamellar, rod-like, co-continuous double gyroid, and onion.

7 Crystalline *versus* amorphous polymers²³

A crystalline polymer has a significant fraction in a crystalline state i.e., a three-dimensional, long range order on an atomic scale. An amorphous polymer exhibits an absence of long-range molecular order. The two-phase model assumes that a polymer contains only crystalline and amorphous phase domains.

8 Thermal and thermomechanical properties^{24,25}

A glass transition occurs when a polymer glass is heated and changes to a polymer melt, or on cooling, back to a polymer glass. In a semicrystalline polymer, this only occurs in parts which are in the amorphous state. A characteristic temperature can be analyzed using a differential scanning calorimeter (DSC; see Fig. 4). Annealing performed by heating a polymer without melting results in a desired change in its properties.

An elastomer displays rubber-like elasticity. A thermoplastic elastomer has a thermoreversible network. A thermosetting polymer is a prepolymer that irreversibly changes into an infusible, insoluble polymer network by curing. Viscoelasticity is the time-dependent response of a material to stress or strain, whereas creep is the time-dependent change in its dimensions due to a constant load.

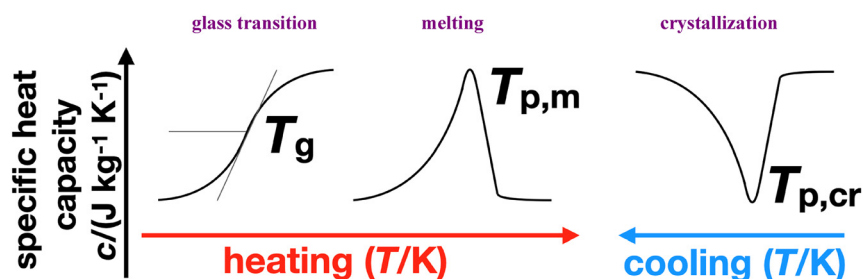


Fig. 4: Characteristic temperatures indicated by DSC: T_g , $T_{p,m}$ and $T_{p,cr}$ are the glass-transition temperature, the peak melting temperature, and the peak crystallization temperature, respectively.

9 Functional polymers¹⁷

A functional polymer has uses arising from chemical groups. For example, a compatibilizer modifies the interfaces of an immiscible polymer to stabilize a compatible polymer blend, while a polymer surfactant lowers the surface tension of a medium with another phase. Polymers can also be, for example, conducting, electroluminescent, liquid-crystalline, piezoelectric, superabsorbent, impact-modified, resists, and nonlinear optical materials, and can display shape-memory.

10 Biorelated polymers¹⁸

A biopolymer consists of biomacromolecules formed by living organisms. A synthetic biopolymer is made using abiotic routes. A biobased polymer is derived from biological products. An artificial polymer is not a biopolymer, while a green polymer conforms to concepts of green chemistry. Biocompatibility allows contact with living systems with acceptable effects.

Membership of sponsoring bodies

Membership of the IUPAC Polymer Division Committee for the period 2022–2023 was as follows:

President: C. K. Luscombe (USA). **Vice President:** I. Lacik (Slovakia). **Secretary:** P. D. Topham. **Past President:** G. T. Russell (New Zealand). **Titular Members:** M. C. H. Chan[†] (Malaysia); T. Junkers (Australia); P. E. Mallon (South Africa); J. B. Matson (USA); Y. Men (China); M. Peeters (UK); P. Théato (Germany). **Associate Members:** A. Aguiar-Ricardo (Portugal); C. M. Fellows (Australia); D. N. Haase (USA); R. Hutchinson (Canada); J. Merna (Czech Republic); M. H. Yoon (Korea). **National Representatives:** R. Adhikari (Nepal); J.-T. Chen (Taiwan); S. Guillaume (France); J. E. Imanah (Nigeria); A. Kishimura (Japan); G. Mechrez (Israel); S. Ramakrishnan (India); G. Raos (Italy); M. A. A. Tasdelen (Turkey); J. van Hest (Netherlands).

Membership of the Subcommittee on Polymer Terminology during the preparation of these Recommendations (2013–2023) was as follows:

Chair: R. G. Jones[†] (UK), 2006–2013; R. C. Hiorns (France), 2014–2020; P. Théato (Germany), from 2021; **Secretary:** R. C. Hiorns (France), 2010–2013; C. K. Luscombe (USA), 2014–2015; P. D. Topham (UK), 2016–2019; J. B. Matson (USA) and P. Théato (Germany) 2020; J. B. Matson (USA) from 2021; **Members:** V. Abetz (Germany); R. Adhikari (Nepal); G. Allegra[†] (Italy); R. Boucher (UK); B. Brettmann (USA); P. Carbone (UK); M. C. H. Chan[†] (Malaysia); T. Chang (Korea); J. Chen (USA); C. G. dos Santos (Brazil); W. Farrell (USA); C. M. Fellows (Australia); A. Fradet (France); C. F. O. Graeff (Brazil); D. N. Haase (USA); J. He (China); K. H. Hellwich (Germany); M. Hess (Germany); P. Hodge (UK); W. Hu (China); A. D. Jenkins[†] (UK); J. I. Jin (Korea); J. Kahovec (Czech Republic); D. J. Keddie (UK); T. Kitayama (Japan); P. Kratochvíl[†] (Czech Republic); P. Kubisa (Poland); M. Malinconico[†] (Italy); P. Mallon (South Africa); S. V. Meille (Italy); J. Merna (Czech Republic); G. Moad (Australia); W. Mormann (Germany); T. Nakano (Japan); C. K. Ober (USA); M. Peeters (UK); O. Philippova (Russia); M. D. Purbrick (UK); G. Raos (Italy); G. Russell (USA); F. Schué[†] (France); S. Słomkowski (Poland); L. Sosa Vargas (France); R. F. T. Stepto[†] (UK); N. Stingelin (UK); A. Sturcova (Czech Republic); D. Tabak (Brazil); J.-P. Vairon (France); M. Vert (France); J. Vohlídal (Czech Republic); M. G. Walter (USA); E. S. Wilks (USA); A. Yerin (Russia); M. H. Yoon (Korea). [†]Deceased.

Republication or reproduction of this report or its storage and/or dissemination by electronic means is permitted without the need for formal IUPAC permission on condition that an acknowledgment, with full reference to the source, along with use of the copyright symbol ©, the name IUPAC, and the year of publication, are prominently visible. Publication of a translation into another language is subject to the additional condition of prior approval from the relevant IUPAC National Adhering Organization.

Research ethics: There are no research ethics concerns associated with this work.

Informed consent: Not applicable.

Author contributions: All authors have accepted responsibility for the entire content of this manuscript and approved its submission.

Use of Large Language Models, AI and Machine Learning Tools: No LLMs were used in this work.

Conflict of interest: The authors have no conflict of interest.

Research funding: This work was funded by IUPAC under grant number 2012-048-3-400.

Data availability: Not applicable.

References

1. Hiorns, R. C.; Boucher, R. J.; Duhlev, R.; Hellwich, K.-H.; Hodge, P.; Jenkins, A. D.; Jones, R. G.; Kahovec, J.; Moad, G.; Ober, C. K.; Smith, D. W.; Stepto, R. F. T.; Vairon, J.-P.; Vohlídal, J. A Brief Guide to Polymer Nomenclature (IUPAC Technical Report). *Pure Appl. Chem.* **2012**, *84*, 2167. <https://doi.org/10.1351/PAC-REP-12-03-05>.
2. Luscombe, C. K.; Moad, G.; Hiorns, R. C.; Jones, R. G.; Keddie, D. J.; Matson, J. B.; Merna, J.; Nakano, T.; Russell, G. T.; Topham, P. D. A Brief Guide to Polymerization Terminology (IUPAC Technical Report). *Pure Appl. Chem.* **2022**, *94*, 1079. <https://doi.org/10.1515/pac-2021-0115>.
3. Topham, P. D.; Boucher, R. J.; Chang, T.; Smrčková, M. D.; Farrell, W. S.; He, J.; Hess, M.; Hu, W.; Hutchins-Crawford, H. J.; Keddie, D. J.; Mallon, P. E.; Merna, J.; Stingelin, N.; Štuncová, A.; Vohlídal, J. A Brief Guide to Polymer Characterization: Structure (IUPAC Technical Report). *Pure Appl. Chem.* **2023**, *95*, 1121. <https://doi.org/10.1515/pac-2022-0602>.
4. Jenkins, A. D.; Kratochvíl, P.; Stepto, R. F. T.; Suter, U. W. Glossary of Basic Terms in Polymer Science (IUPAC Recommendations 1996). *Pure Appl. Chem.* **1996**, *68*, 2287. <https://doi.org/10.1351/pac199668122287>.
5. Barón, M.; Hellwich, K.-H.; Hess, M.; Horie, K.; Jenkins, A. D.; Jones, R. G.; Kahovec, J.; Kratochvíl, P.; Metanowski, W. V.; Mormann, W.; Stepto, R. F. T.; Vohlídal, J.; Wilks, E. S. Glossary of Class Names of Polymers Based on Chemical Structure and Molecular Architecture (IUPAC Recommendations 2009). *Pure Appl. Chem.* **2009**, *81*, 1131–1186. <https://doi.org/10.1351/PAC-REC-08-01-30>.
6. Stepto, R. F. T. Dispersity in Polymer Science (IUPAC Recommendations 2009). *Pure Appl. Chem.* **2009**, *81*, 351. <https://doi.org/10.1351/PAC-REC-08-05-02>; Erratum. *Pure Appl. Chem.* **2009**, *81*, 779. https://doi.org/10.1351/PAC-REC-08-05-02_erratum.
7. Fradet, A.; Chen, J.; Hellwich, K.-H.; Horie, K.; Kahovec, J.; Mormann, W.; Stepto, R. F. T.; Vohlídal, J.; Wilks, E. S. Nomenclature and Terminology for Dendrimers with Regular Dendrons and for Hyperbranched Polymers (IUPAC Recommendations 2017). *Pure Appl. Chem.* **2019**, *91*, 523. <https://doi.org/10.1515/pac-2016-1217>.
8. Hess, M.; Jones, R. G.; Kahovec, J.; Kitayama, T.; Kratochvíl, P.; Kubisa, P.; Mormann, W.; Stepto, R. F. T.; Tabak, D.; Vohlídal, J.; Wilks, E. S. Terminology of Polymers Containing Ionizable or Ionic Groups and of Polymers Containing Ions (IUPAC Recommendations 2006). *Pure Appl. Chem.* **2006**, *78*, 2067. <https://doi.org/10.1351/pac200678112067>.
9. Moss, G. P. Basic Terminology of Stereochemistry (IUPAC Recommendations 1996). *Pure Appl. Chem.* **1996**, *68*, 2193. <https://doi.org/10.1351/pac199668122193>.
10. Hatada, K.; Kahovec, J.; Barón, M.; Horie, K.; Kitayama, T.; Kubisa, P.; Moss, G. P.; Stepto, R. F. T.; Wilks, E. S. Definitions Relating to Stereochemically Asymmetric Polymerizations (IUPAC Recommendations 2001). *Pure Appl. Chem.* **2002**, *74*, 915. <https://doi.org/10.1351/pac200274060915>.
11. Jenkins, A. D. Stereochemical Definitions and Notations Relating to Polymers (Recommendations 1980). *Pure Appl. Chem.* **1981**, *53*, 733. <https://doi.org/10.1351/pac198153030733>.
12. Fellows, C. M.; Hellwich, K.-H.; Meille, S. V.; Moad, G.; Nakano, T.; Vert, M. Definitions and Notations Relating to Tactic Polymers (IUPAC Recommendations 2020). *Pure Appl. Chem.* **2020**, *92*, 1769. <https://doi.org/10.1515/pac-2019-0409>.
13. Mita, I.; Stepto, R. F. T.; Suter, U. W. Basic Classification and Definitions of Polymerization Reactions (IUPAC Recommendations 1994). *Pure Appl. Chem.* **1994**, *66*, 2483. <https://doi.org/10.1351/pac199466122483>.
14. Penczek, S.; Moad, G. Glossary of Terms Related to Kinetics, Thermodynamics, and Mechanisms of Polymerization (IUPAC Recommendations 2008). *Pure Appl. Chem.* **2008**, *80*, 2163. <https://doi.org/10.1351/pac200880102163>.
15. Fellows, C. M.; Jones, R. G.; Keddie, D. J.; Luscombe, C. K.; Matson, J. B.; Matyjaszewski, K.; Merna, J.; Moad, G.; Nakano, T.; Penczek, S.; Russell, G. T.; Topham, P. D. Terminology for Chain Polymerization (IUPAC Recommendations 2021). *Pure Appl. Chem.* **2022**, *94*, 1093. <https://doi.org/10.1515/pac-2020-1211>.
16. Slomkowski, S.; Alemán, J. V.; Gilbert, R. G.; Hess, M.; Horie, K.; Jones, R. G.; Kubisa, P.; Meisel, I.; Mormann, W.; Penczek, S.; Stepto, R. F. T. Terminology of Polymers and Polymerization Processes in Dispersed Systems (IUPAC Recommendations 2011). *Pure Appl. Chem.* **2011**, *83*, 2229. <https://doi.org/10.1351/PAC-REC-10-06-03>.
17. Horie, K.; Barón, M.; Fox, R. B.; He, J.; Hess, M.; Kahovec, J.; Kitayama, T.; Kubisa, P.; Maréchal, E.; Mormann, W.; Stepto, R. F. T.; Tabak, D.; Vohlídal, J.; Wilks, E. S.; Work, W. J. Definitions of Terms Relating to Reactions of Polymers and to Functional Polymeric Materials (IUPAC Recommendations 2003). *Pure Appl. Chem.* **2004**, *76*, 889. <https://doi.org/10.1351/pac200476040889>.
18. Hatada, K.; Fox, R. B.; Kahovec, J.; Maréchal, E.; Mita, I.; Shibaev, V. P. Definitions of Terms Relating to Degradation, Aging, and Related Chemical Transformations of Polymers (IUPAC Recommendations 1996). *Pure Appl. Chem.* **1996**, *68*, 2313. <https://doi.org/10.1351/pac199668122313>.

19. Vert, M.; Doi, Y.; Hellwich, K.-H.; Hess, M.; Hodge, P.; Kubisa, P.; Rinaudo, M.; Schué, F. Terminology for Biorelated Polymers and Applications (IUPAC Recommendations 2012). *Pure Appl. Chem.* **2012**, *84*, 377. <https://doi.org/10.1351/PAC-REC-10-12-04>.
20. Stepto, R. F. T.; Chang, T.; Kratochvíl, P.; Hess, M.; Horie, K.; Sato, T.; Vohlídal, J. Definitions of Terms Relating to Individual Macromolecules, Macromolecular Assemblies, Polymer Solutions, and Amorphous Bulk Polymers (IUPAC Recommendations 2014). *Pure Appl. Chem.* **2015**, *87*, 71. <https://doi.org/10.1515/pac-2013-0201>.
21. Work, W. J.; Horie, K.; Hess, M.; Stepto, R. F. T. Definition of Terms Related to Polymer Blends, Composites, and Multiphase Polymeric Materials (IUPAC Recommendations 2004). *Pure Appl. Chem.* **2004**, *76*, 1985. <https://doi.org/10.1351/pac200476111985>.
22. Alemán, J. V.; Chadwick, A. V.; He, J.; Hess, M.; Horie, K.; Jones, R. G.; Kratochvíl, P.; Meisel, I.; Mita, I.; Moad, G.; Penczek, S.; Stepto, R. F. T. Definitions of Terms Relating to the Structure and Processing of Sols, Gels, Networks, and inorganic-organic Hybrid Materials (IUPAC Recommendations 2007). *Pure Appl. Chem.* **2007**, *79*, 1801. <https://doi.org/10.1351/pac200779101801>.
23. Meille, S. V.; Allegra, G.; Geil, P. H.; He, J.; Hess, M.; Jin, J.-I.; Kratochvíl, P.; Mormann, W.; Stepto, R. F. T. Definitions of Terms Relating to Crystalline Polymers (IUPAC Recommendations 2011). *Pure Appl. Chem.* **2011**, *83*, 1831. <https://doi.org/10.1351/PAC-REC-10-11-13>.
24. Kaye, A.; Stepto, R. F. T.; Work, W. J.; Alemán, J. V.; Malkin, A. Y. Definition of Terms Relating to the Non-ultimate Mechanical Properties of Polymers (Recommendations 1998). *Pure Appl. Chem.* **1998**, *70*, 701. <https://doi.org/10.1351/pac199870030701>.
25. Hess, M.; Allegra, G.; He, J.; Horie, K.; Kim, J.-S.; Meille, S. V.; Metanowski, V.; Moad, G.; Stepto, R. F. T.; Vert, M.; Vohlídal, J. Glossary of Terms Relating to Thermal and Thermomechanical Properties of Polymers (IUPAC Recommendations 2013). *Pure Appl. Chem.* **2013**, *85*, 1017. <https://doi.org/10.1351/PAC-REC-12-03-02>.

Supplementary Material: This article contains supplementary material (<https://doi.org/10.1515/pac-2023-0304>).