

First results of the bundle test QUENCH-L3 with optimized ZIRLO™ claddings


J. Stuckert, M. Große, J. Moch, C. Rössger, M. Steinbrück, M. Walter

QWS-21, Karlsruhe 2015

Institute for Applied Materials; Program NUKLEAR




Cross-section of the QUENCH-L3 bundle

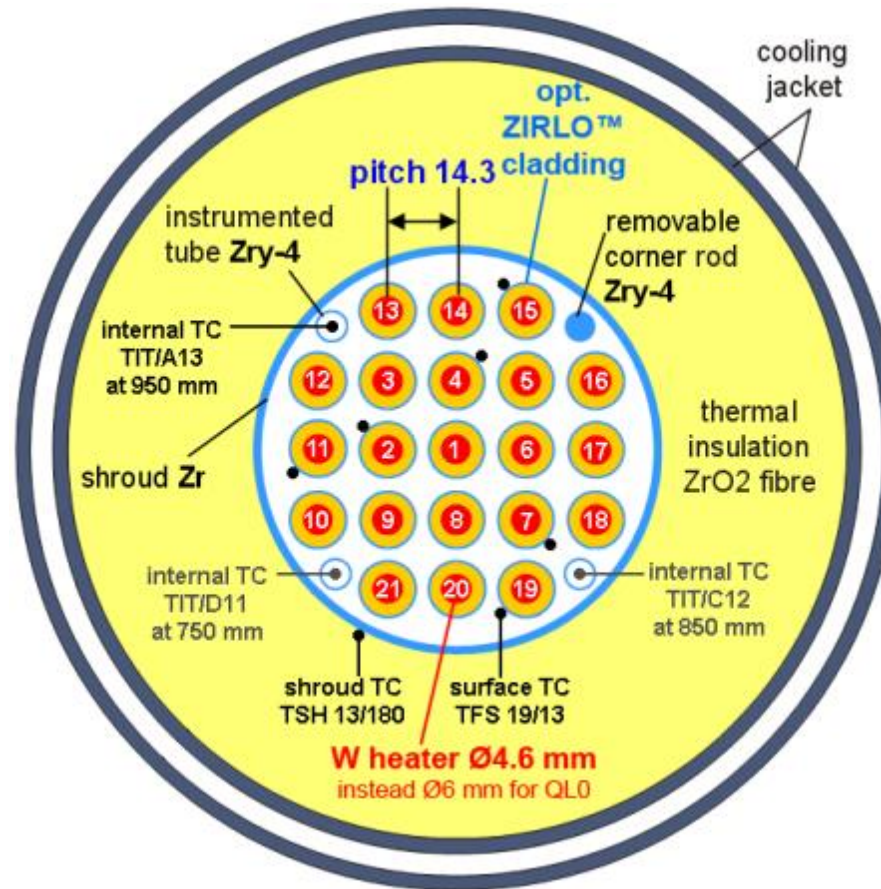


- 1) The use of **tungsten** heaters with smaller diameter (**4.6 mm**) instead tungsten heaters (QUENCH-L0) or tantalum heaters (QUENCH-L1) with diameter of 6 mm has allowed to reach a **higher heat rate**.
- 2) All rods are filled with Kr with $p=55$ bar at $T_{pct}=800$ K (similar to QUENCH-L1).

QUENCH-L3: test progress

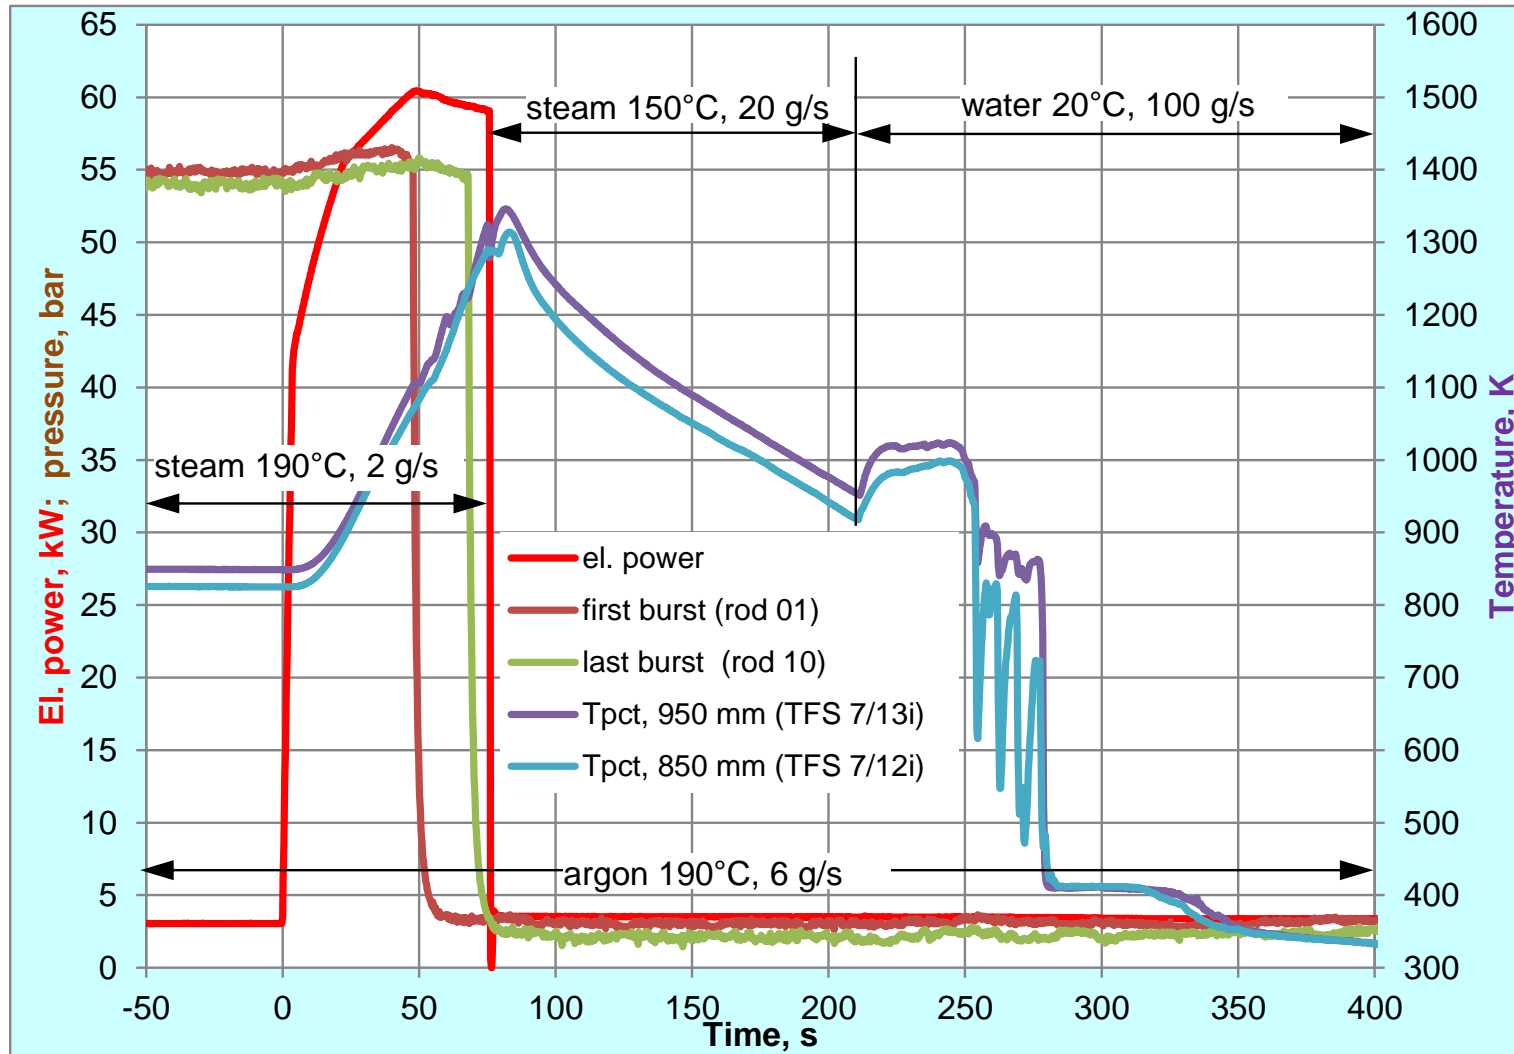


Maximal cladding temperatures of internal rods in hottest region of QUENCH-L1 (Zry-4, reference test) and -L3 bundles (elevation 950 mm)


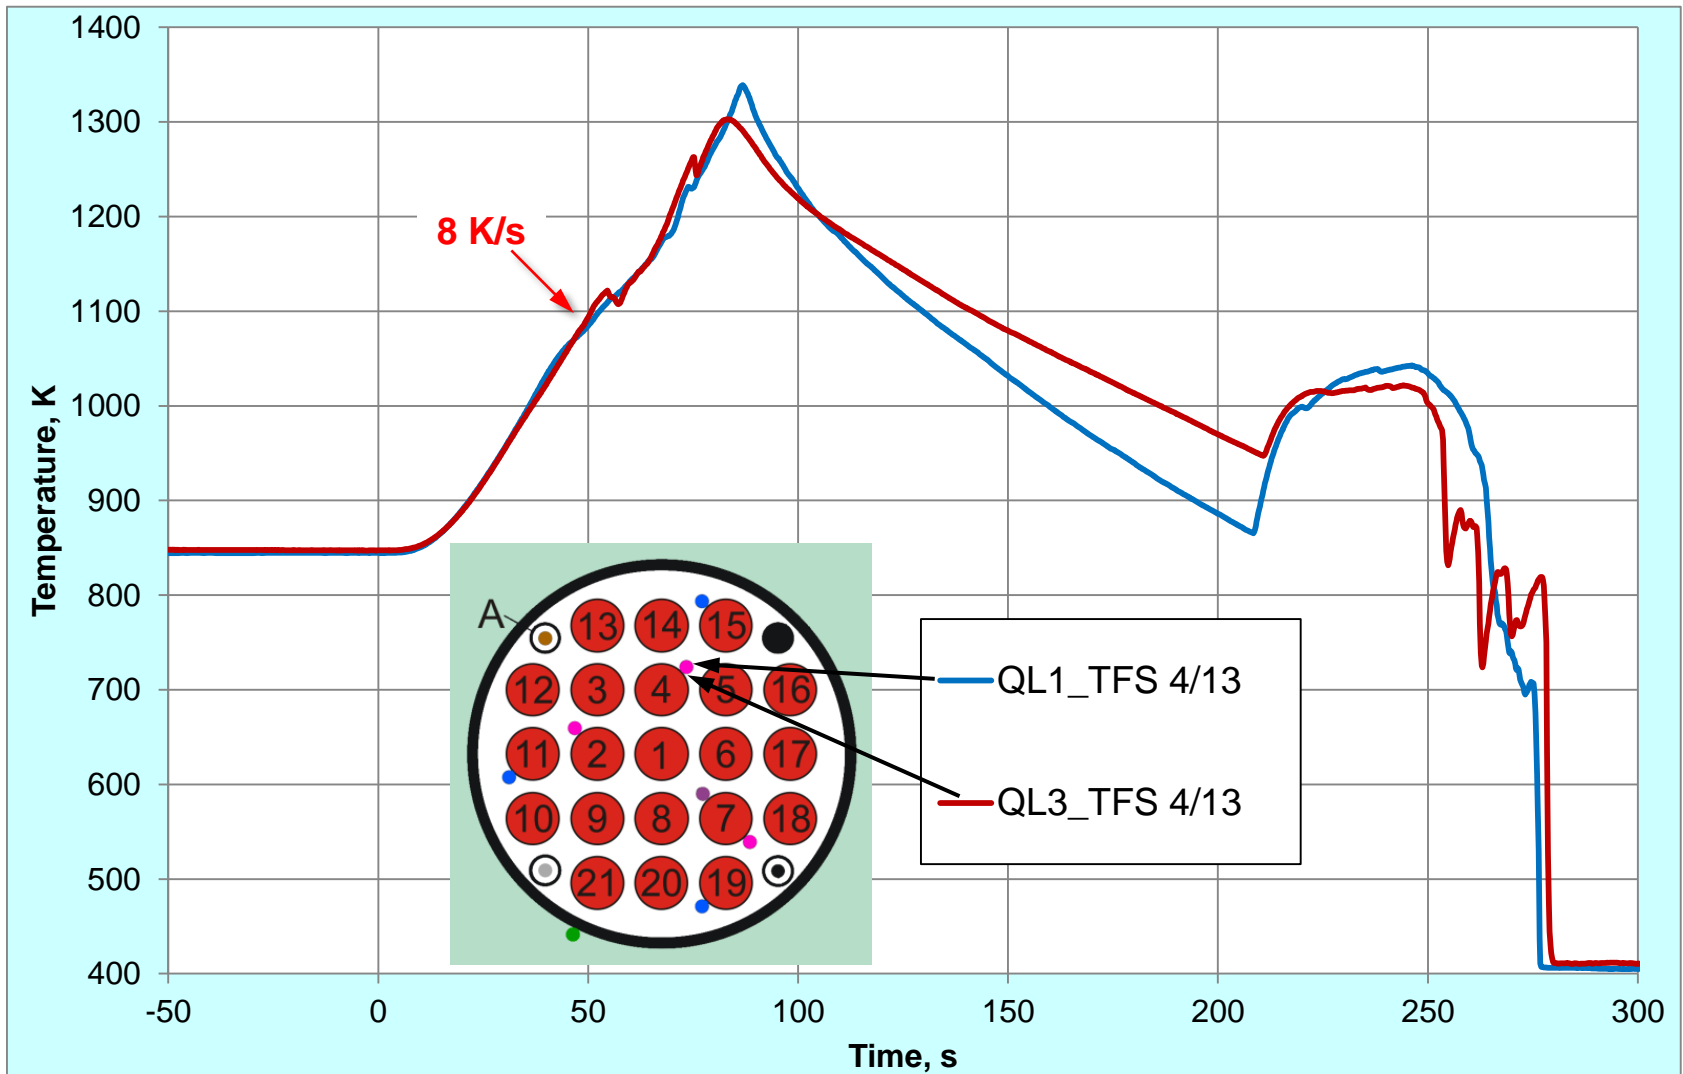


QUENCH-L3: radial temperature gradient ΔT

for rod #7 at hottest elevations 850 mm (7/12) and 950 mm (7/13)

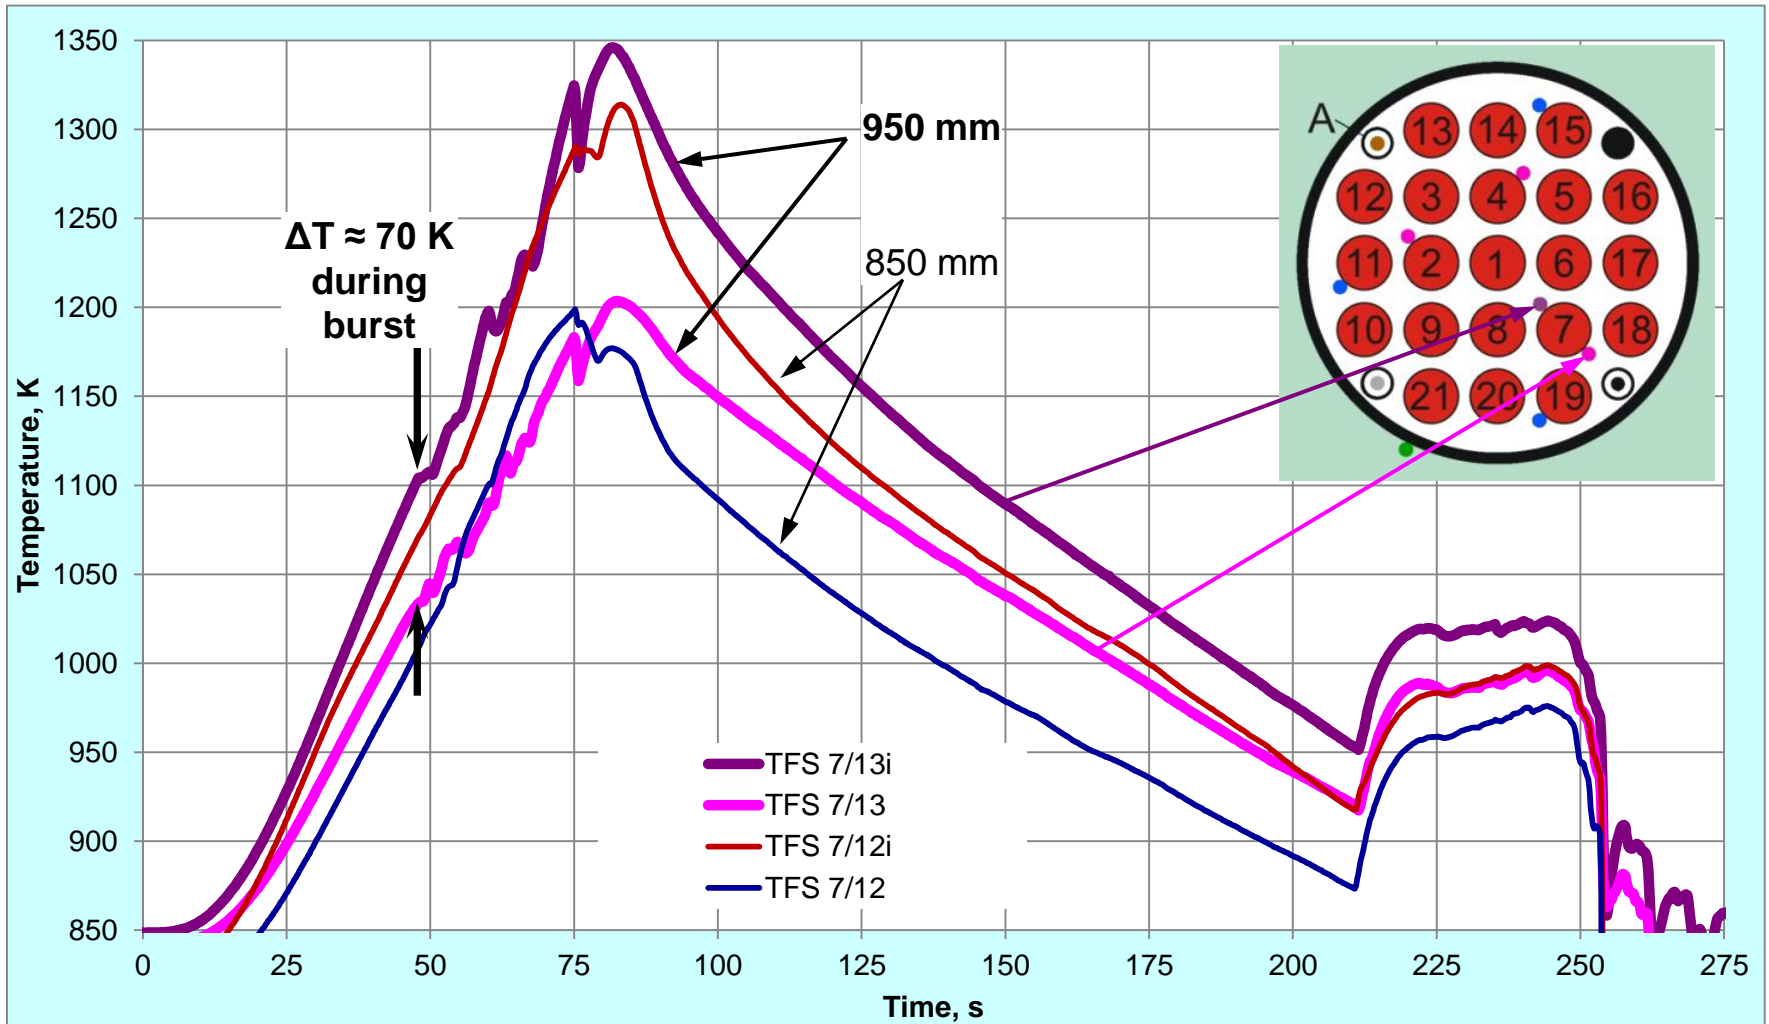


Rod pressure evolution during heating phase for QUENCH-L1 (reference test with Zry-4) and QUENCH-L3: burst time indication

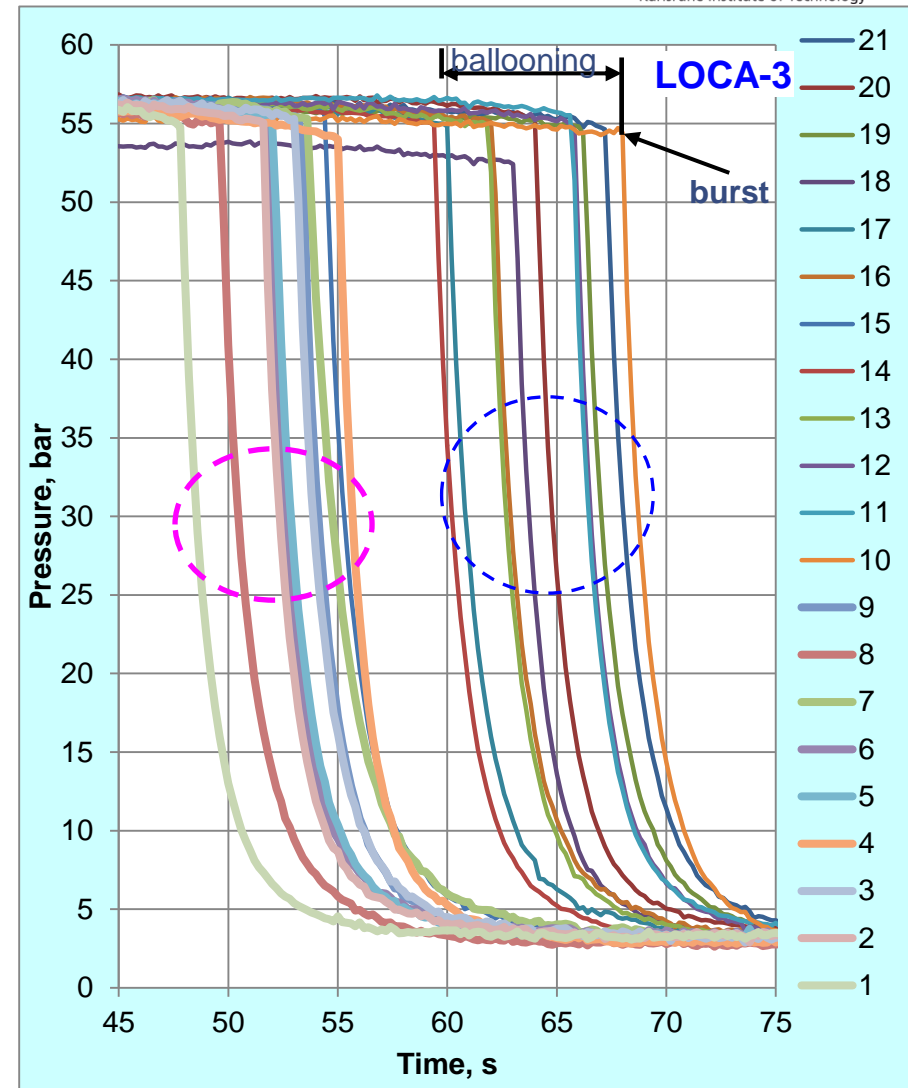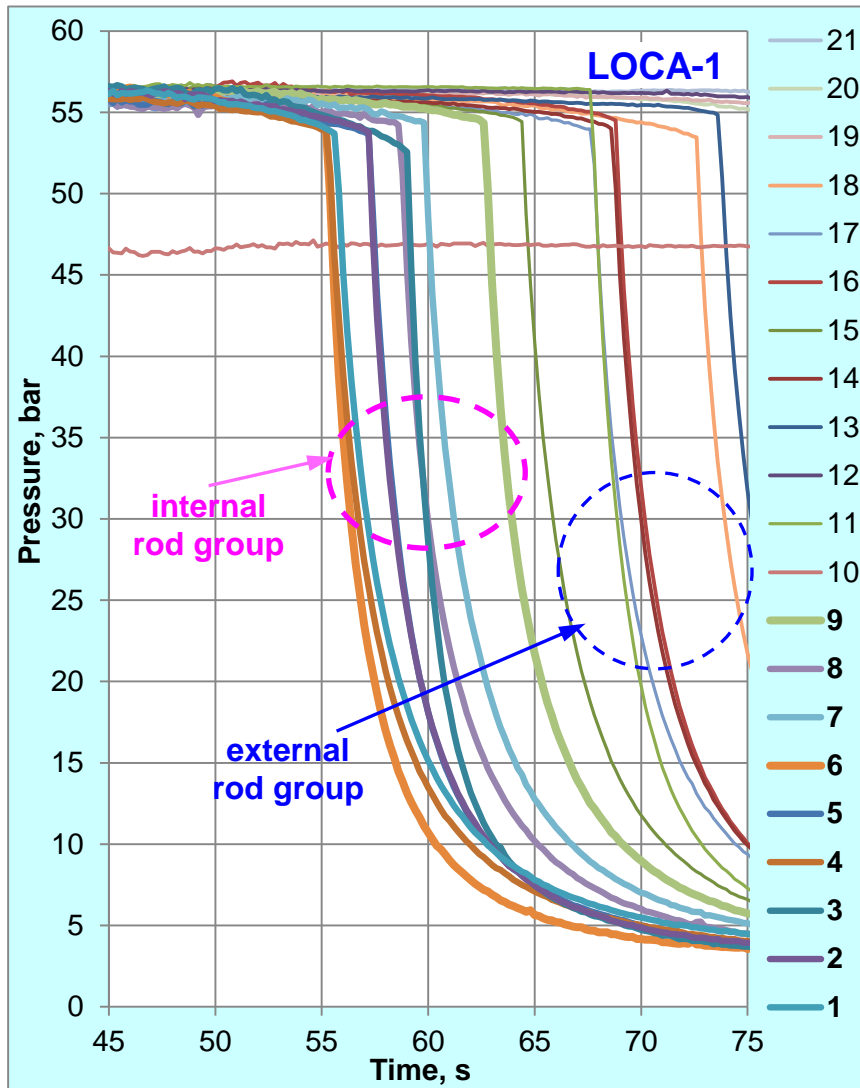

pressure decrease to system pressure: $\tau_0 \approx 38$ s

pressure decrease to system pressure: $\tau_0 \approx 30$ s

QUENCH-L3: Ballooning and burst of cladding tubes at elevation 950 mm (videoscope)

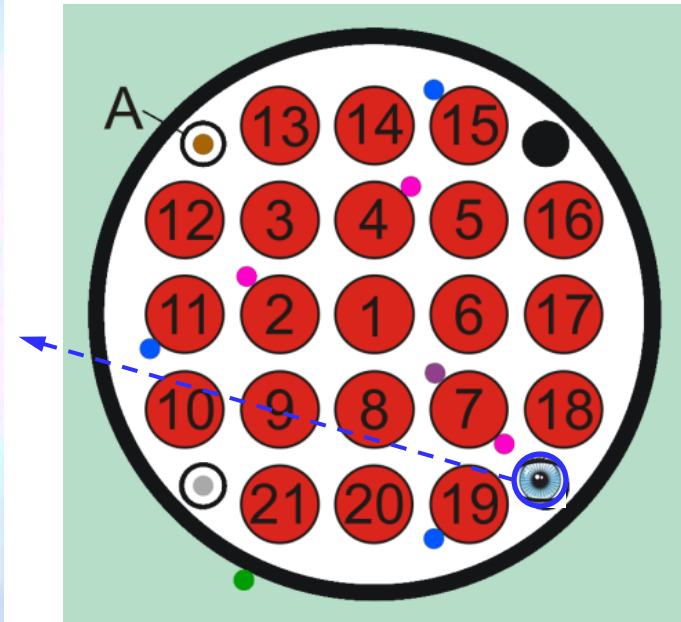

Burst parameters

LOCA-1

| Rod group | Rod # | Burst time, s | Burst temperature, interpolated, K |
|------------|-------|---------------|------------------------------------|
| Inner rods | 1 | 55.6 | 1169 (Max) |
| | 2 | 57.2 | 1132 |
| | 3 | 59.0 | 1118 |
| | 4 | 55.2 | 1154 |
| | 5 | 57.2 | 1104 |
| | 6 | 55.2 | 1110 |
| | 7 | 59.8 | 1074 (Min) |
| | 8 | 58.6 | 1132 |
| | 9 | 62.6 | 1162 |
| Outer rods | 10 | 87.6 | 1143 |
| | 11 | 67.6 | 1056 |
| | 12 | 76.8 | 1092 |
| | 13 | 73.6 | 1147 |
| | 14 | 68.6 | 1154 |
| | 15 | 64.4 | 1159 |
| | 16 | 68.8 | 1156 |
| | 17 | 67.6 | 1104 |
| | 18 | 72.6 | 1081 |
| | 19 | 83.6 | 1163 |
| | 20 | 76.0 | 1105 |
| | 21 | 80.6 | 1140 |


average burst T: $1126 \pm 33 \text{ K} = 853 \pm 33 \text{ }^\circ\text{C}$

LOCA-3


| Rod group | Rod # | Burst time, s | Burst temperature, interpolated, K |
|------------|-------|---------------|------------------------------------|
| Inner rods | 1 | 47.8 | 1103 |
| | 2 | 51.6 | 1140 |
| | 3 | 53 | 1111 |
| | 4 | 55 | 1108 |
| | 5 | 52 | 1109 |
| | 6 | 51.8 | 1112 |
| | 7 | 53.6 | 1124 |
| | 8 | 49.6 | 1107 |
| | 9 | 53.2 | 1132 |
| Outer rods | 10 | 68 | 1188 (Max) |
| | 11 | 65.6 | 1126 |
| | 12 | 65.8 | 1175 |
| | 13 | 61.8 | 1138 |
| | 14 | 59.4 | 1124 |
| | 15 | 54.4 | 1105 |
| | 16 | 62 | 1142 |
| | 17 | 60 | 1094 |
| | 18 | 63 | 1114 |
| | 19 | 66.2 | 1073 |
| | 20 | 64 | 1064 (Min) |
| | 21 | 67.2 | 1073 |

average burst T: $1117 \pm 30 \text{ K} = 844 \pm 30 \text{ }^\circ\text{C}$

QUENCH-L3: 9 inner rods


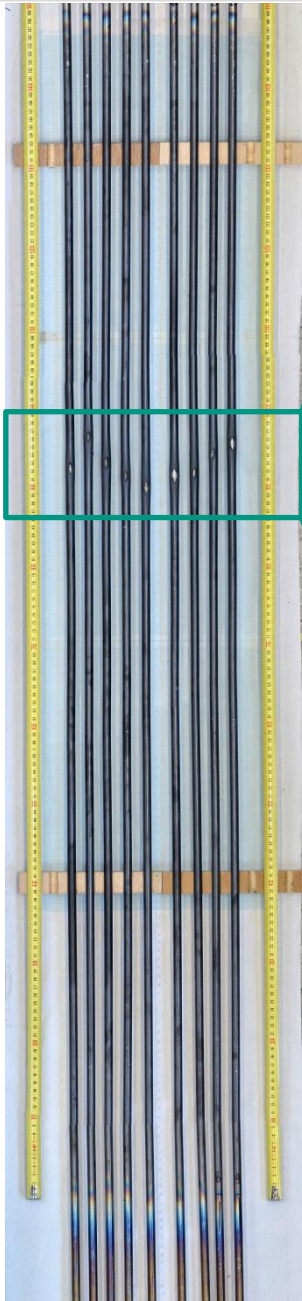


#1 #2 #3 #4 #5 #6 #7 #8 #9

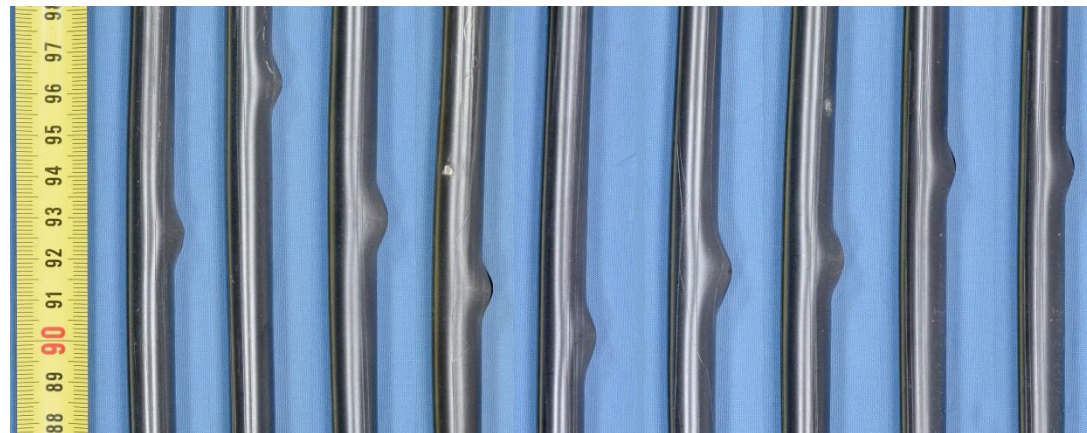

**average bending 1.1% oppositely to burst direction:
buckling due to simultaneous thermal expansion and friction at grid spacers**


QUENCH-L3: 12 outer rods

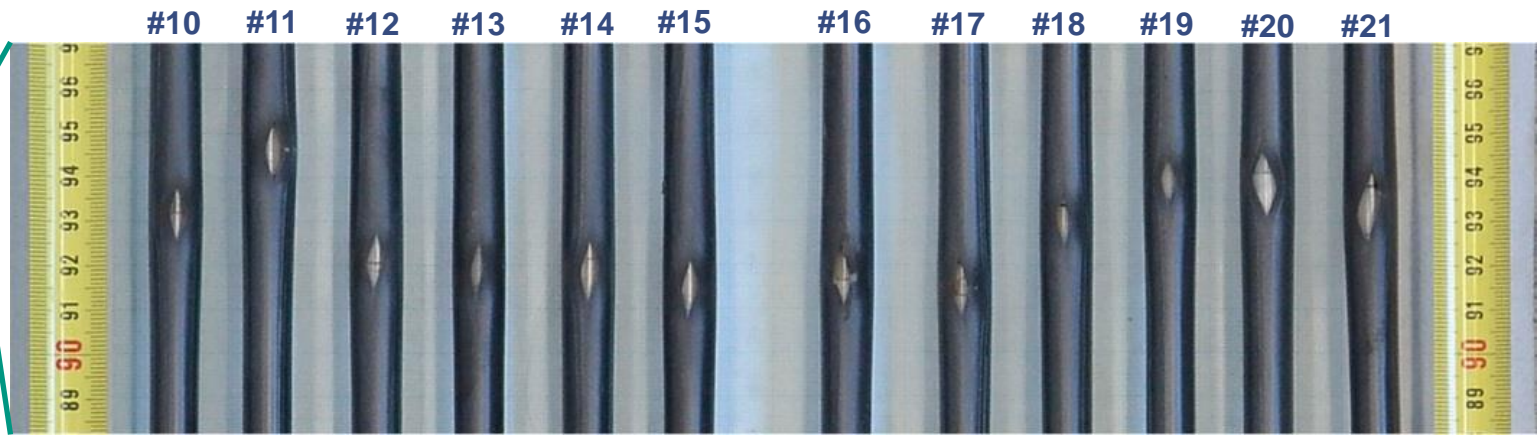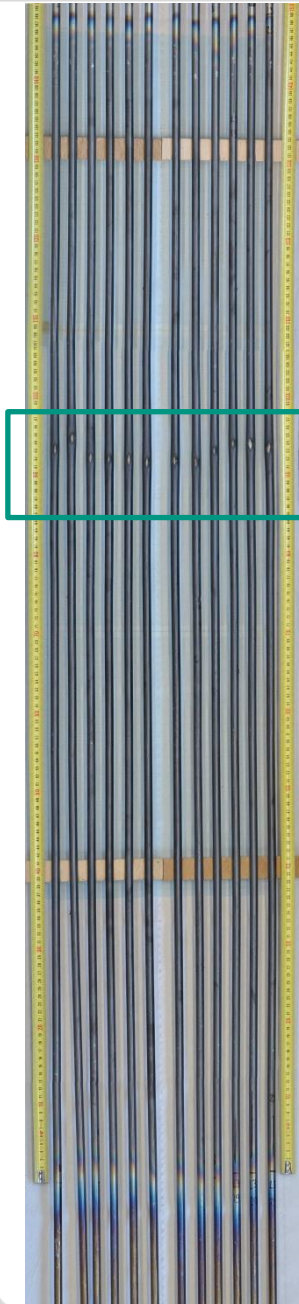


small scattering of axial positions and dimensions of burst openings

Length and axial position of burst openings


LOCA-1 (reference test with Zry-4)

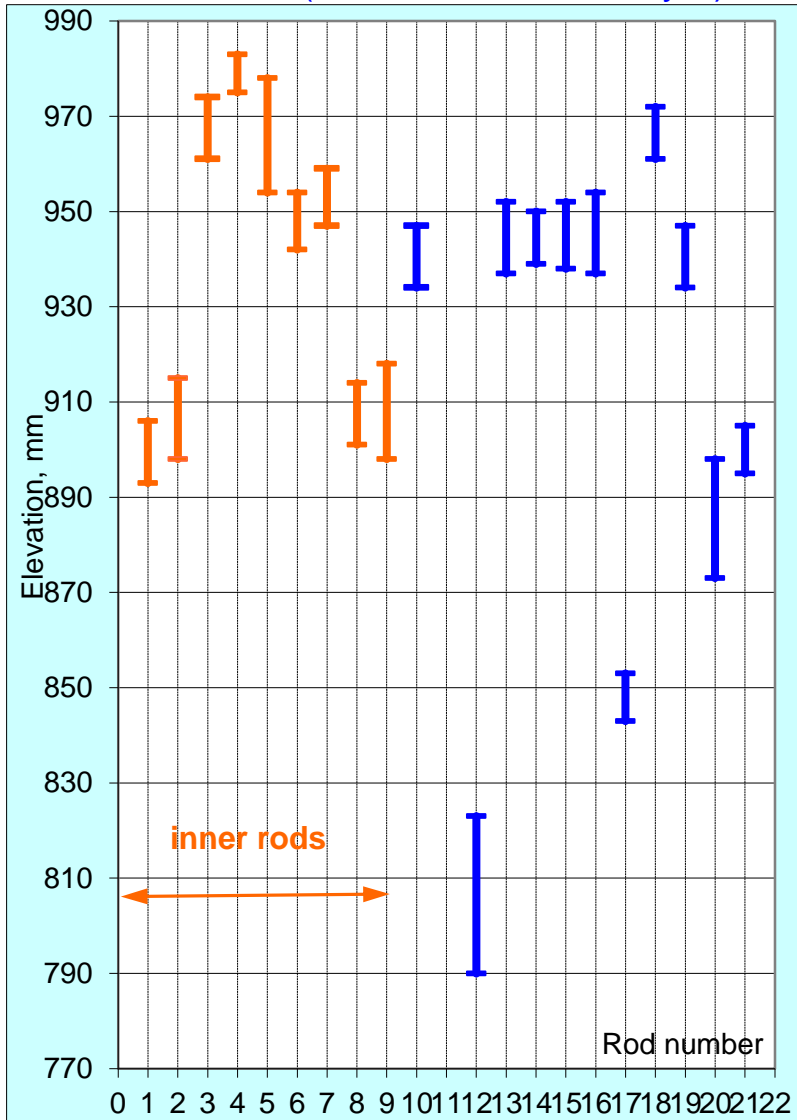


LOCA-3

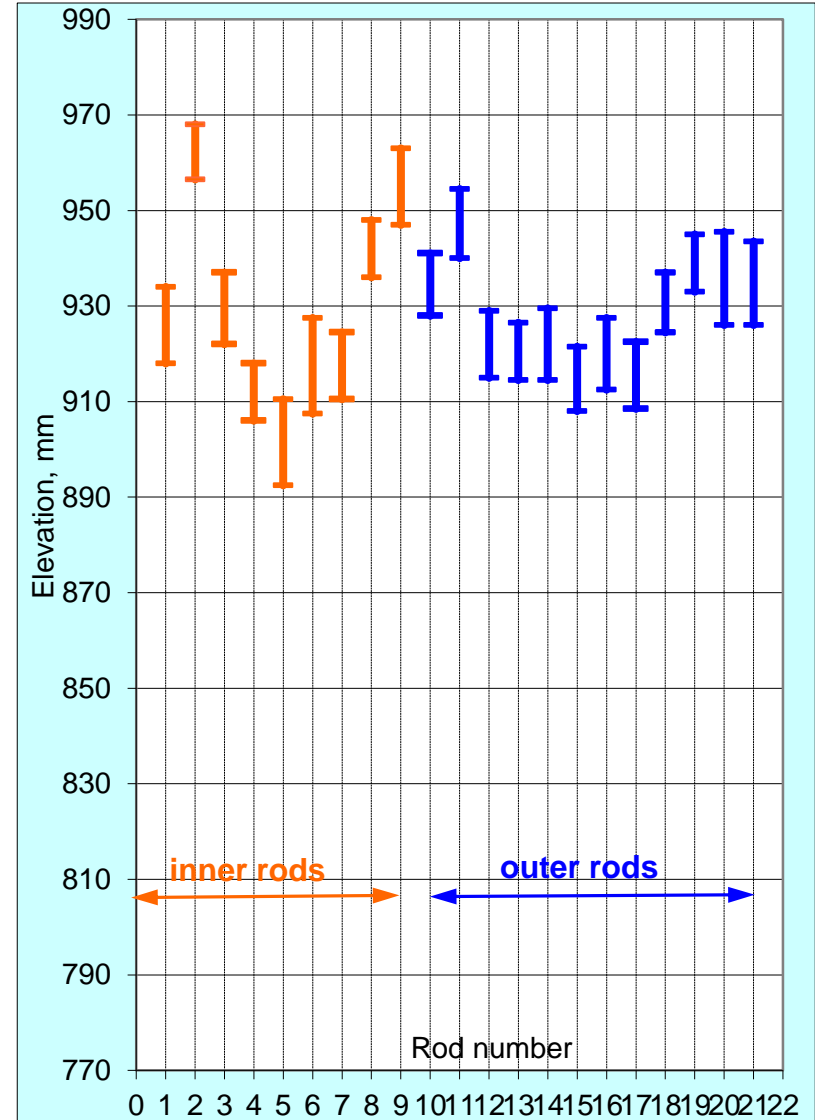

Circumferential position of burst openings

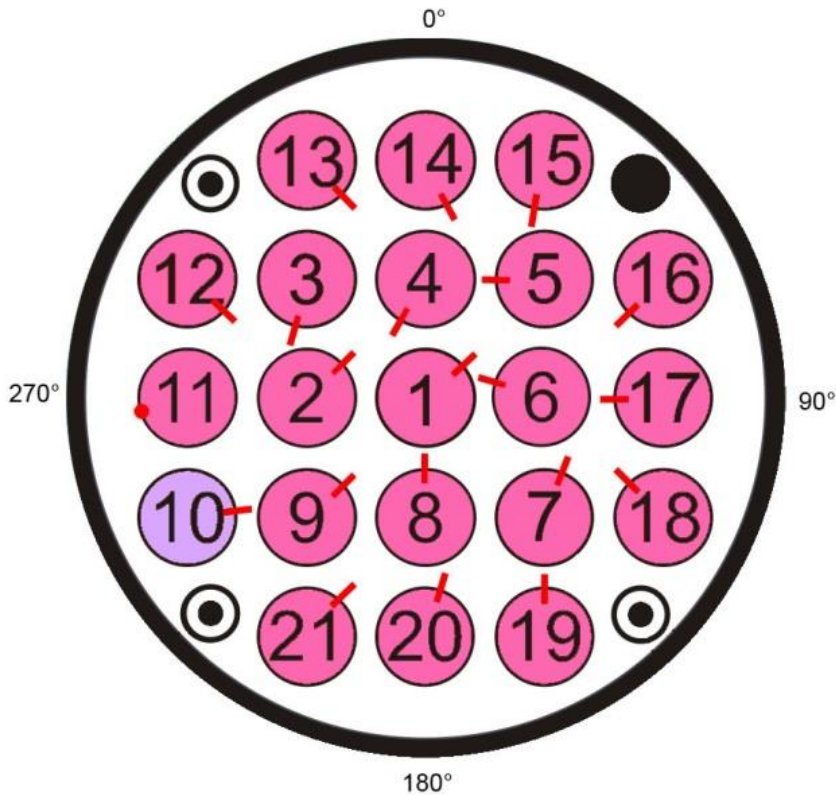


LOCA-1 (reference test with Zry-4)

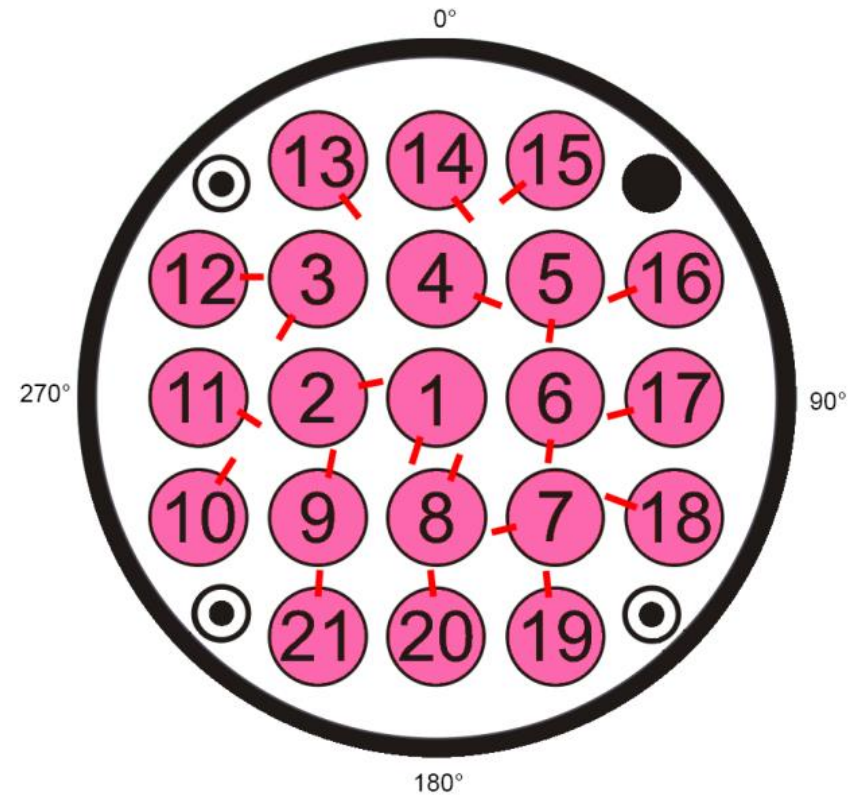


LOCA-3

burst openings oriented predominantly to bundle center due to pronounced radial temperature gradient

QUENCH-L3: Circumferential strain (laser scanner)


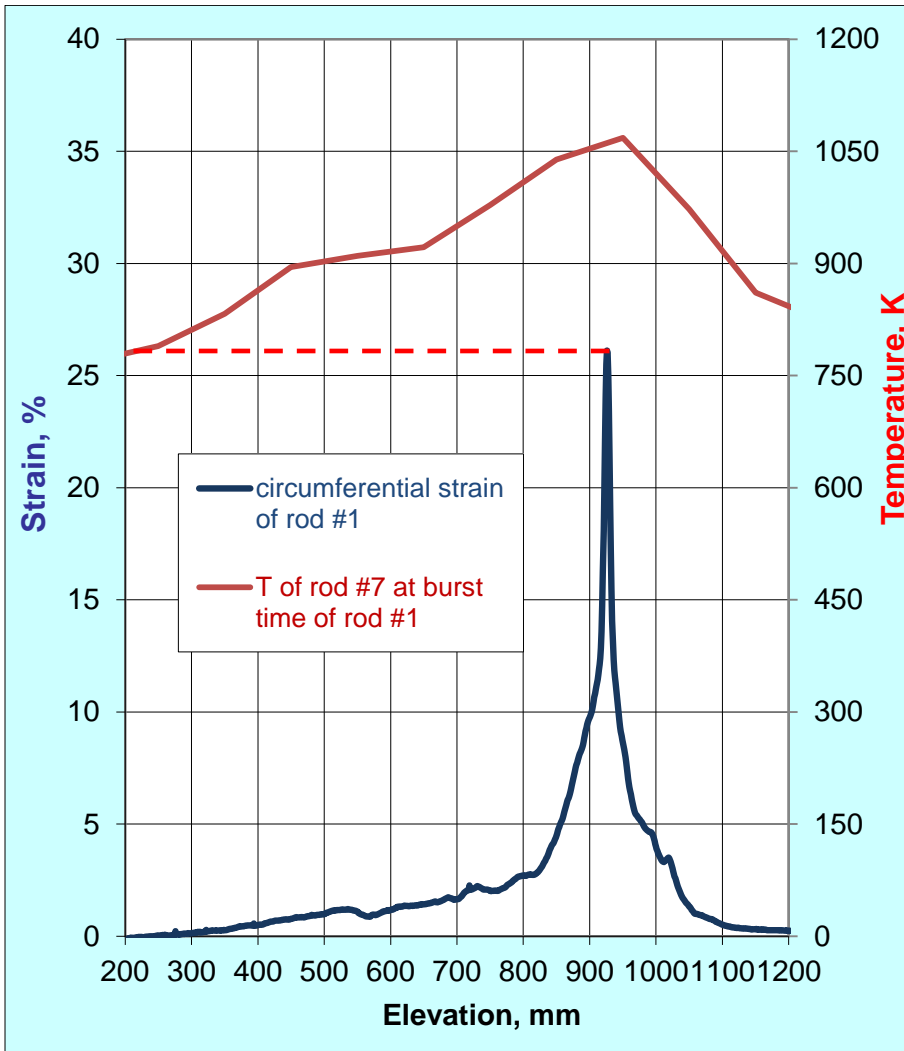


rod #1: central rod, typical strain < 27%

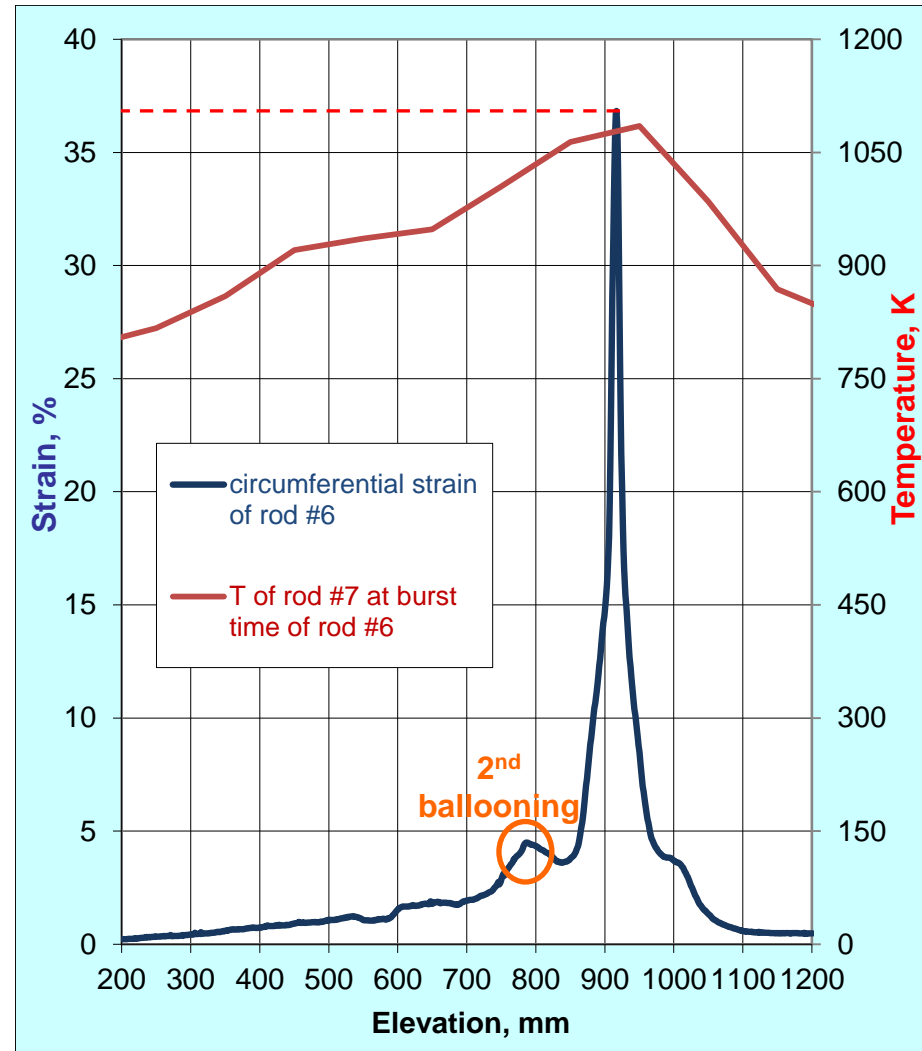


rod #6: maximal strain of 37%


QUENCH-L3: Circumferential strain (laser scanner) and burst position overview

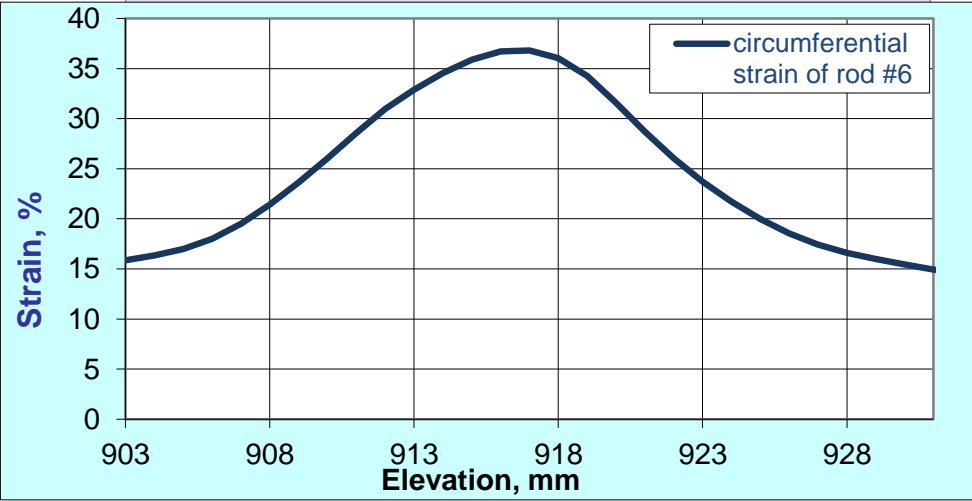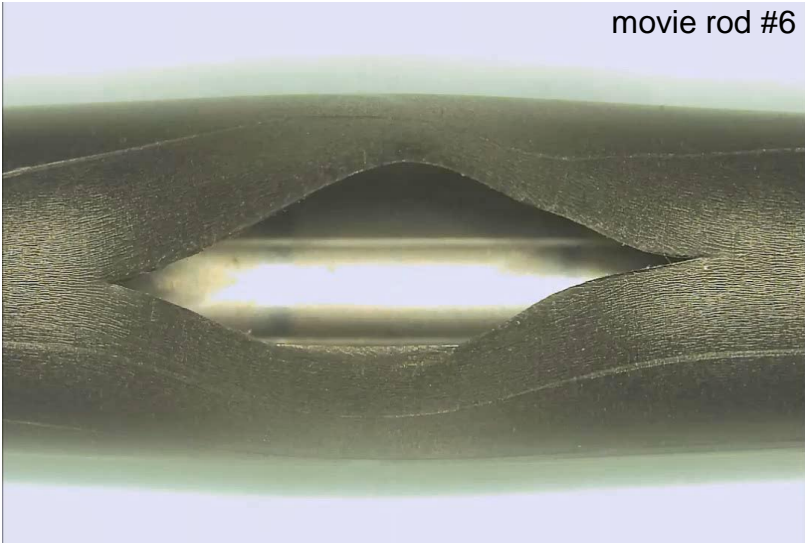


Cooling channel blockage for QL-1 and QL-3 bundles

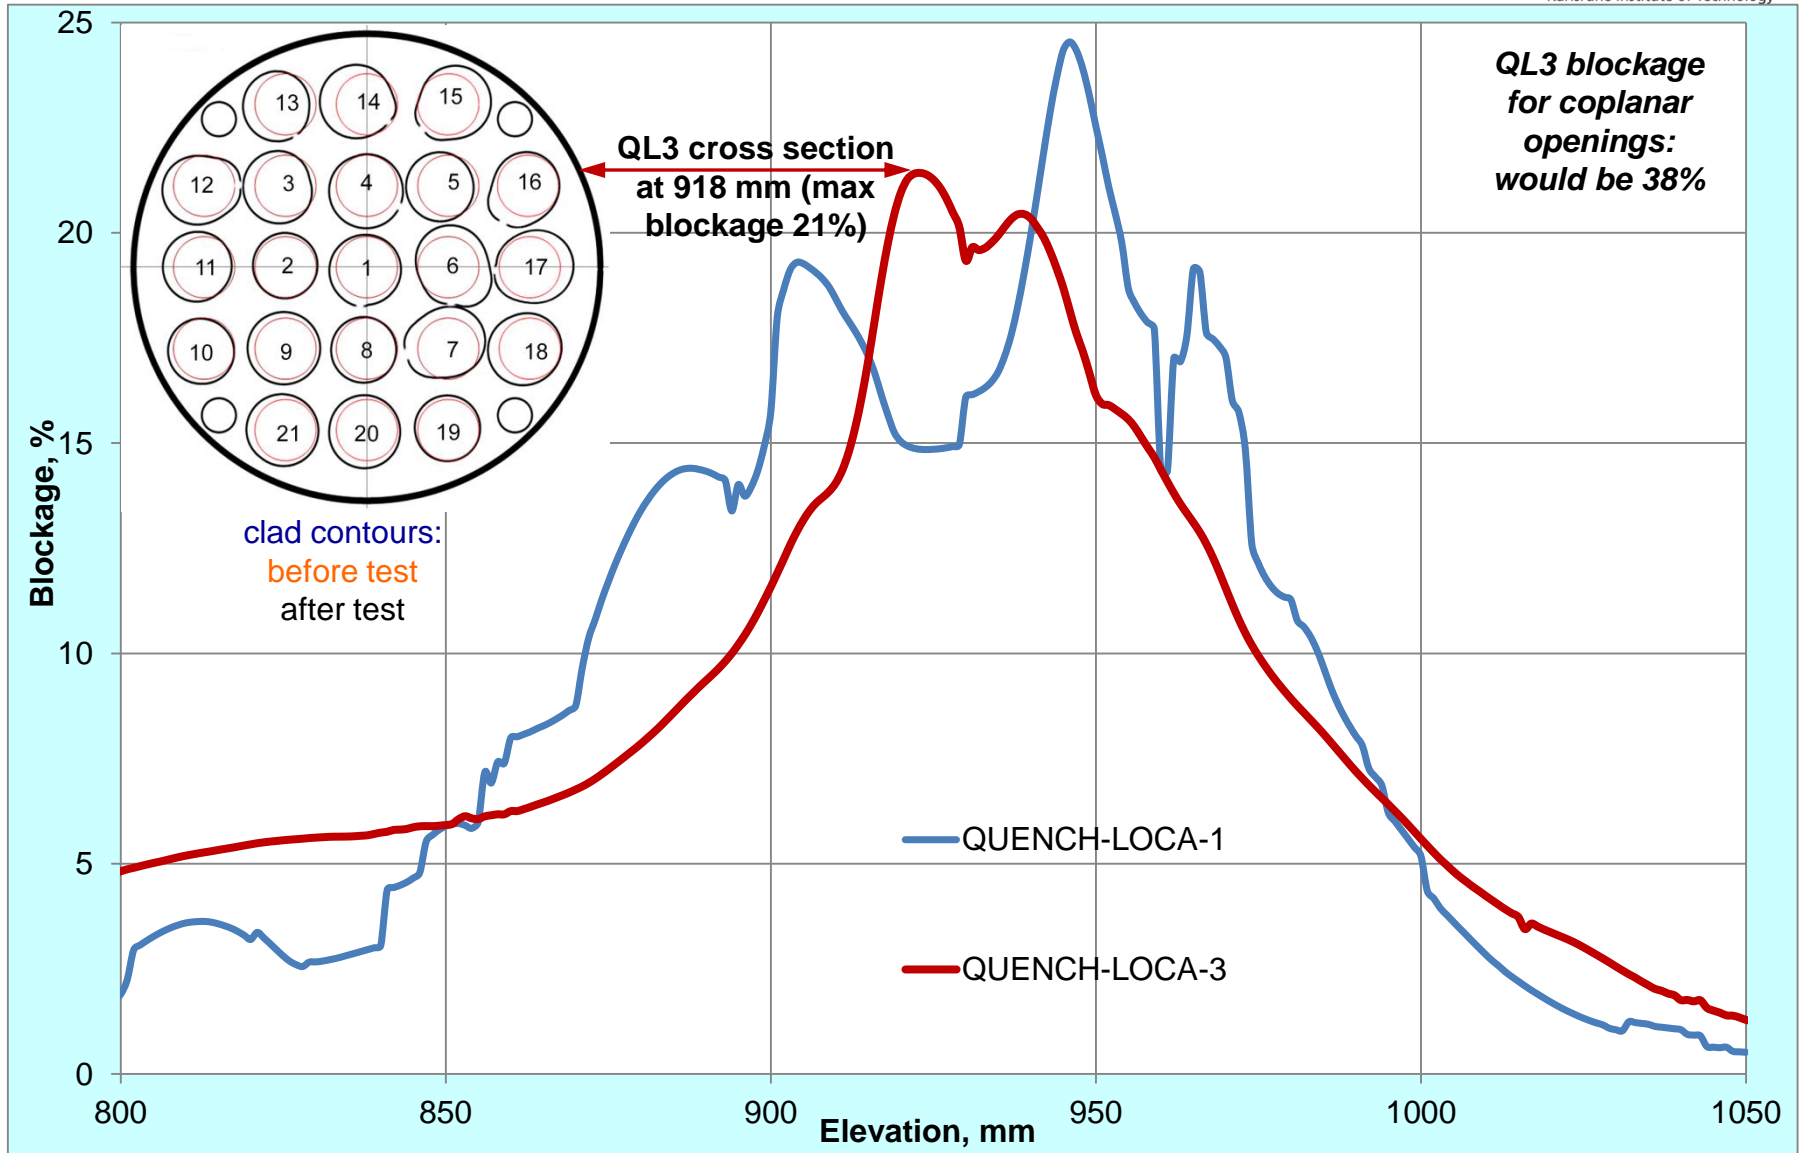


Comparison of oxidation degree for QL-1, -3, -3HT (eddy current measurements at outer clad surface)

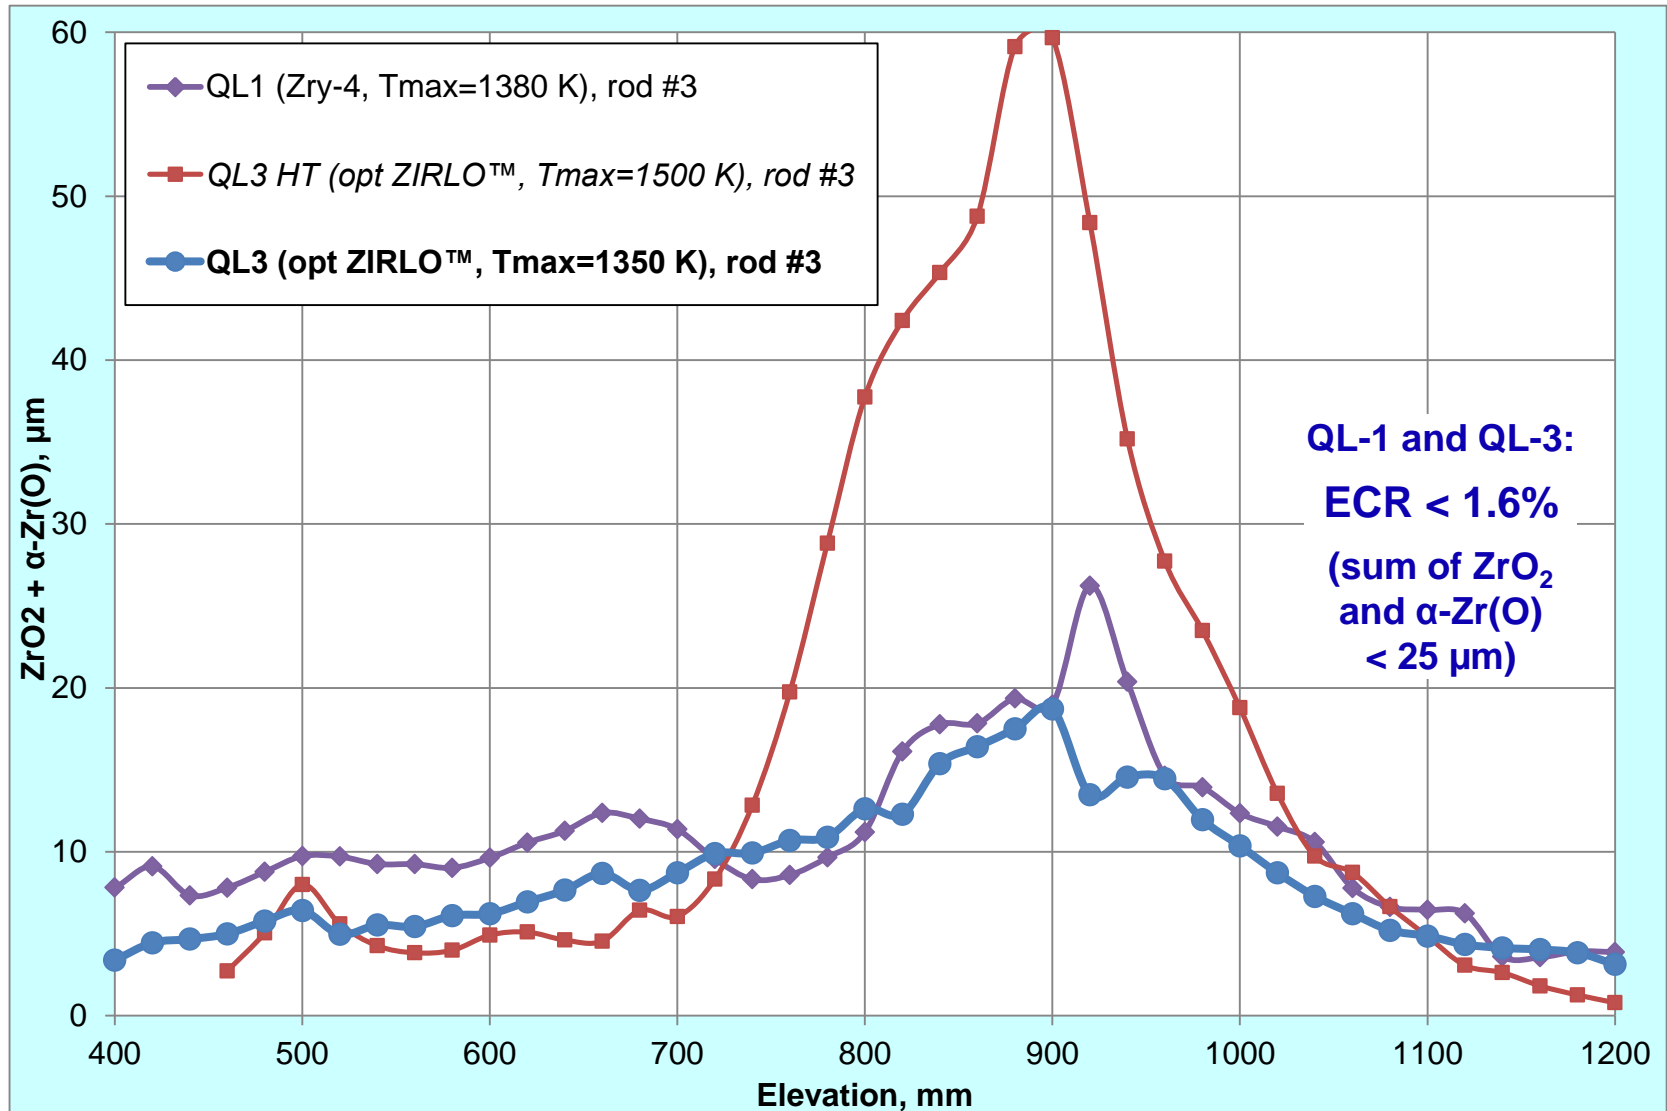


Test set-up for tensile tests with claddings from QUENCH-LOCA bundles

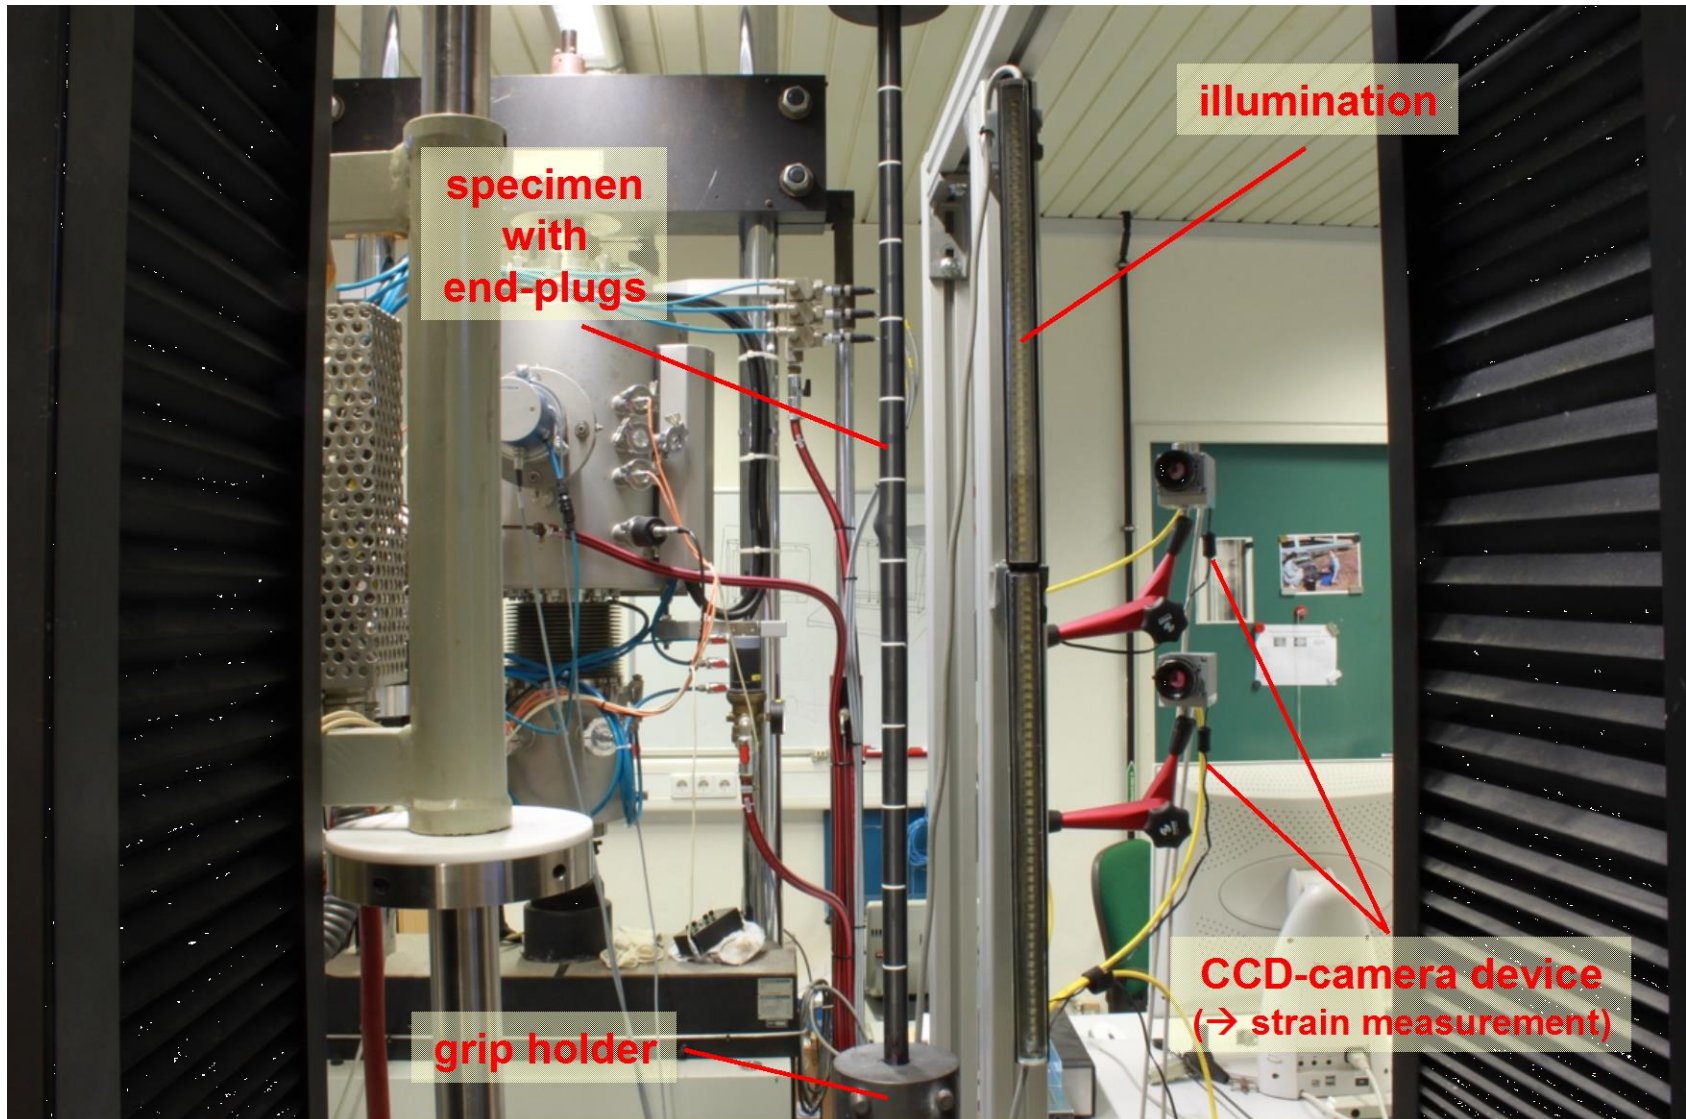

QUENCH-L3: tensile tests at RT with inner rods, fractures at H-bands (1 rod), through opening and due to necking (7 rods)

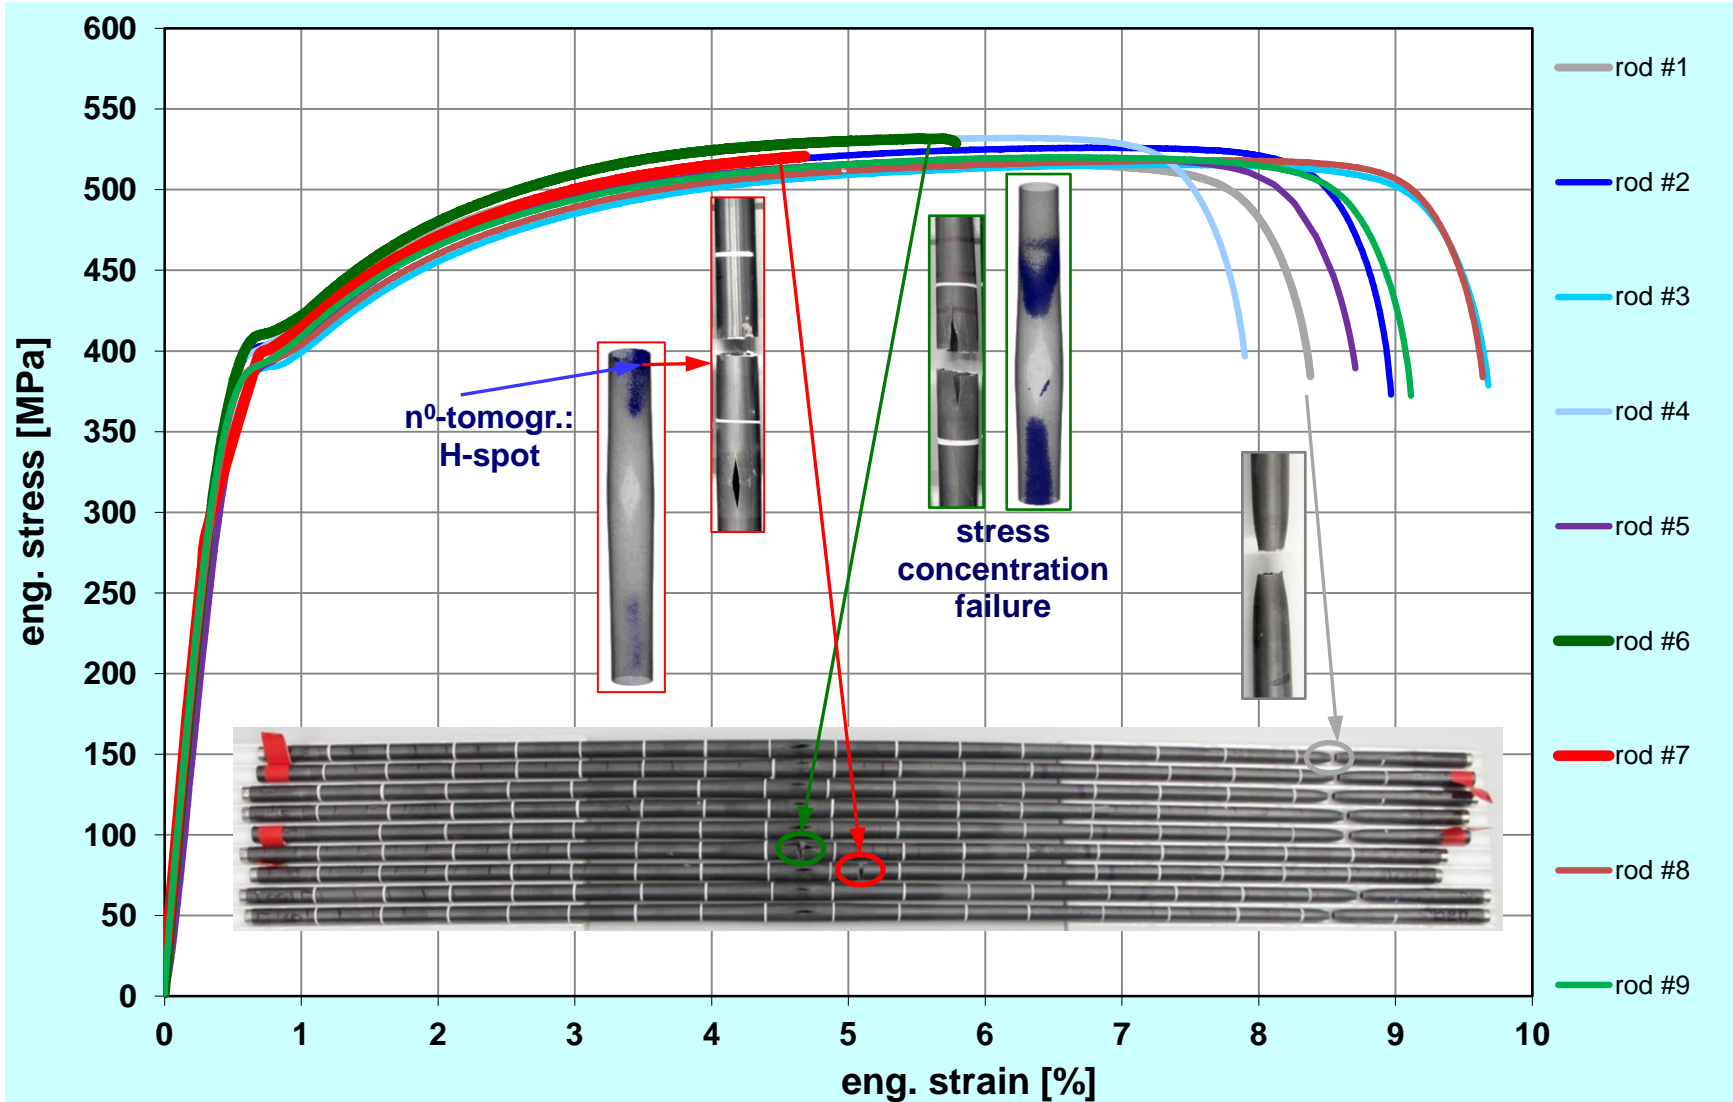



QUENCH-L3: tensile tests at RT with outer rods, fractures due to micro-cracks at the burst opening edges (6 rods) and necking (6 rods)

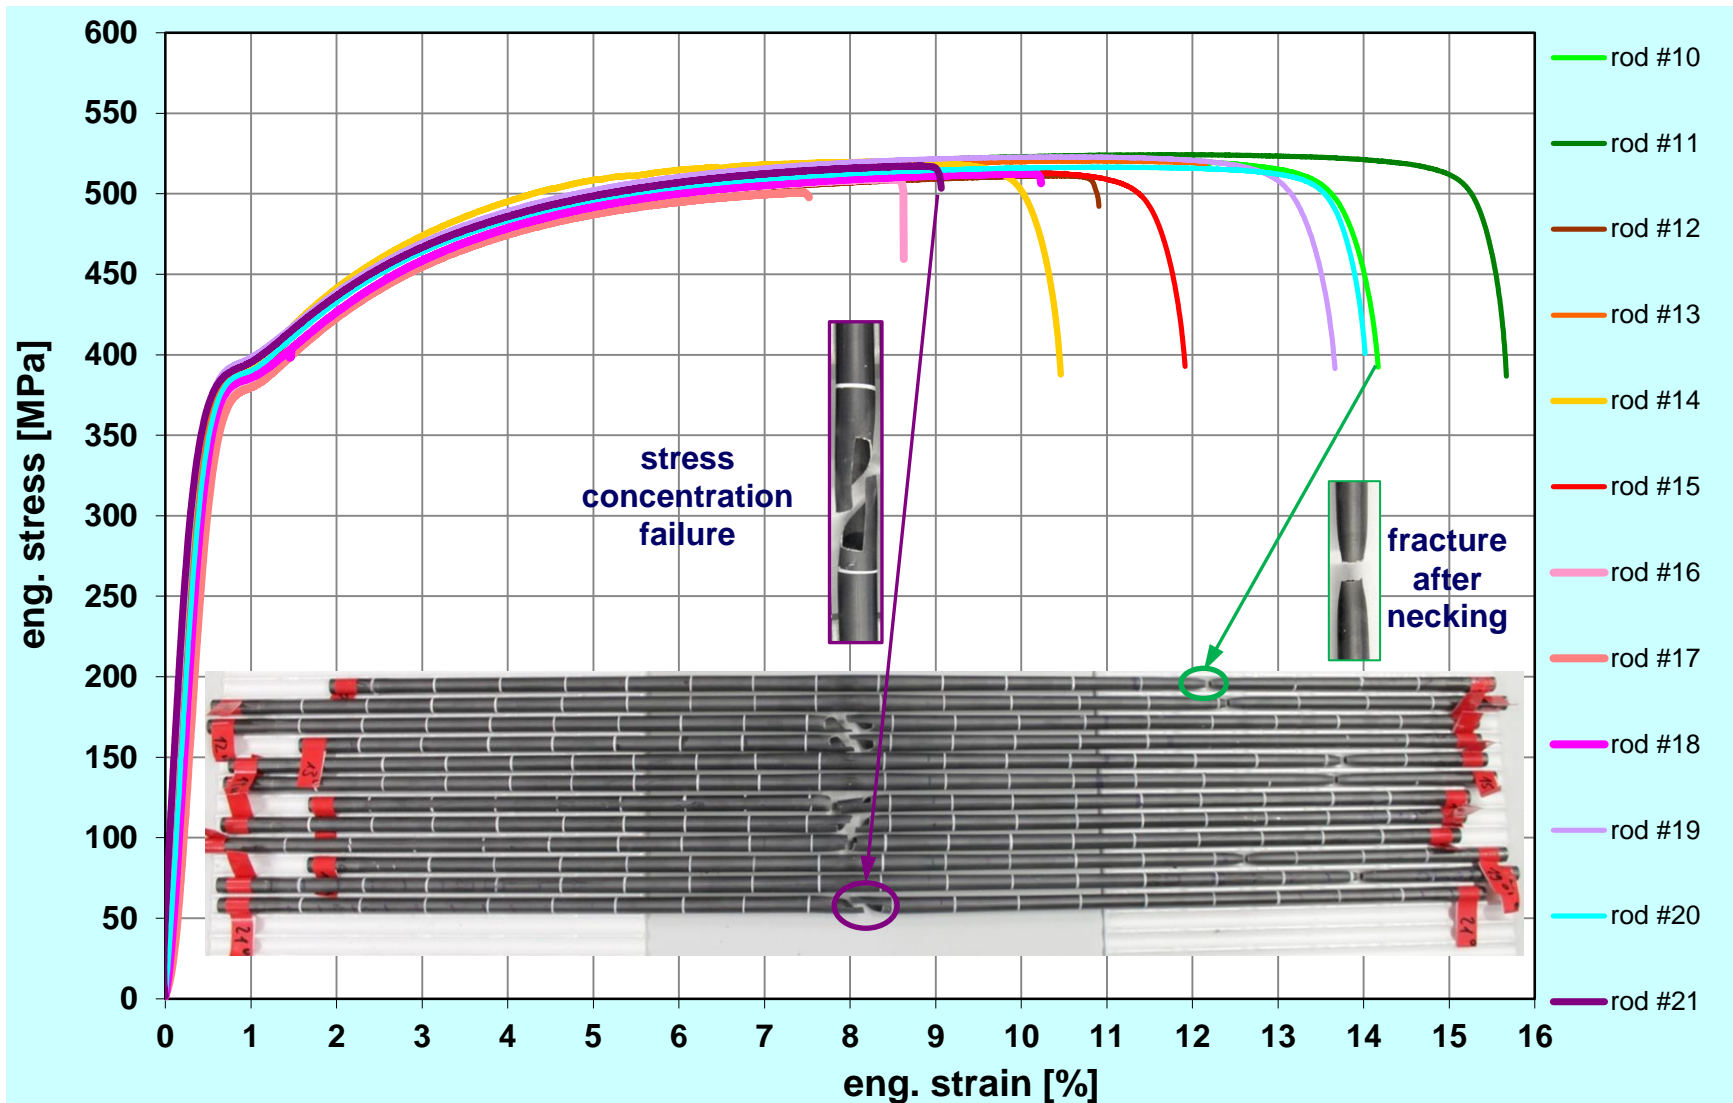

QL3 (opt. ZIRLO™)



QL1 (Zry-4)

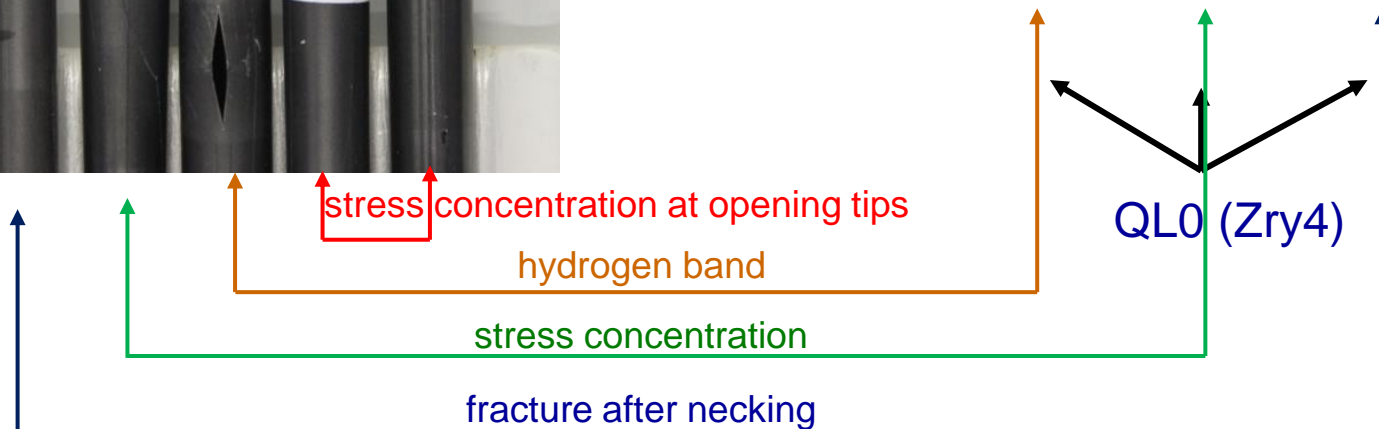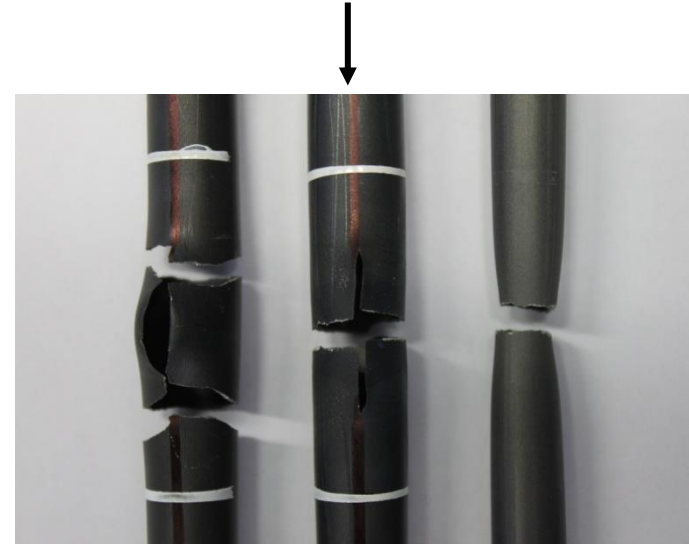

Tensile properties of opt. ZIRLO™ claddings tested after QUENCH-L3

| sample | ultimate tensile stress [MPa] | fracture stress [MPa] | elongation at fracture [%] | failure behaviour |
|----------------|-------------------------------|-----------------------|----------------------------|---|
| rod #1 | 516 | 384 | 8.4 | fracture after necking |
| rod #2 | 526 | 373 | 9.0 | fracture after necking |
| rod #3 | 515 | 379 | 9.7 | fracture after necking |
| rod #4 | 532 | 379 | 7.9 | fracture after necking |
| rod #5 | 520 | 386 | 8.7 | fracture after necking |
| rod #6 | 531 | 529 | 5.8 | stress concentration at opening middle |
| rod #7 | 521 | 521 | 4.7 | H-band |
| rod #8 | 518 | 384 | 9.6 | fracture after necking |
| rod #9 | 520 | 372 | 9.1 | fracture after necking |
| rod #10 | 521 | 392 | 14.2 | fracture after necking |
| rod #11 | 524 | 387 | 15.7 | fracture after necking |
| rod #12 | 511 | 492 | 10.9 | stress concentration at opening tips |
| rod #13 | 520 | 517 | 12.2 | stress concentration at opening tips |
| rod #14 | 520 | 388 | 10.5 | fracture after necking |
| rod #15 | 514 | 393 | 11.9 | fracture after necking |
| rod #16 | 509 | 459 | 8.6 | stress concentration at opening tips |
| rod #17 | 501 | 498 | 7.5 | stress concentration at opening tips |
| rod #18 | 512 | 506 | 10.2 | stress concentration at opening tips |
| rod #19 | 523 | 391 | 13.7 | fracture after necking |
| rod #20 | 517 | 401 | 14.0 | fracture after necking |
| rod #21 | 517 | 503 | 9.1 | stress concentration at opening tips |

fracture of clads
H-band: 1 clad,
stress conc.: 7 clads,
necking: 13 clads

Summary

- The QUENCH-LOCA-3 test with as-received opt. ZIRLO™ claddings was performed according to a temperature/time-scenario typical for a LBLOCA in a German PWR with similar test parameters as the QUENCH-LOCA-1 test with fresh Zry-4 claddings: maximal heat-up rate 8 K/s, cooling phase lasted 120 s and terminated with 3.3 g/s/rod water flooding.
- Similar to QUENCH-LOCA-1, the maximum temperature of 1350 K was reached on the end of the heat-up phase at elevation 950 mm. Circumferential temperature gradient across a rod was up to 70 K on the burst onset.
- The maximum blockage ratio of cooling channel (21% at 918 mm) was slightly lower in comparison to QUENCH-L1 (25% at 946 mm). Due to moderate blockage a good bundle coolability was kept for both bundles.
- The cladding burst occurred at temperatures between 1064 and 1188 K (QUENCH-L1: 1074 and 1169 K). Average burst temperatures: 1126 K (853°C) for QUENCH-L1 and 1117 K (844°C) for QUENCH-L3.
- During quenching, following the high-temperature phase, no fragmentation of claddings was observed (residual strengths or ductility is sufficient).
- Influence of secondary hydrogenation on results of tensile tests at RT: only one cladding failed at hydrogen band; seven claddings failed due to stress concentration at edges of burst opening (similar to all QL1 clads with <1500 wppm hydrogen); thirteen clads failed after necking far away from burst opening.

Acknowledgment

The QUENCH-LOCA experiments are supported and partly sponsored by the association of the German utilities (VGB). The unirradiated optimized ZIRLO™ claddings and spacer material were provided by WESTINGHOUSE.

The authors would like to thank Mrs. J. Laier and Mrs. U. Peters for intensive work during test preparation and post-test investigations.

Thank you for your attention

<https://www.iam.kit.edu/wpt/loca/>
<http://www.iam.kit.edu/wpt/471.php>
<http://quench.forschung.kit.edu/>